



# 1 **Mineral sequestration of CO<sub>2</sub> by aqueous carbonation of** 2 **coal combustion fly-ash**

3  
4 G. Montes-Hernandez <sup>\*,a</sup>, R. Pérez-López <sup>a,b</sup>, F. Renard <sup>a,c</sup>, J.M. Nieto <sup>b</sup>, L. Charlet <sup>a</sup>

5  
6 <sup>a</sup> LGIT, CNRS-OSUG-UJF, Université Joseph Fourier, Maison de Géosciences, BP 53, 38041  
7 Grenoble Cedex, France

8 <sup>b</sup> Department of Geology, University of Huelva, Campus 'El Carmen', 21071, Huelva, Spain

9 <sup>c</sup> Physics of Geological Processes, University of Oslo, Norway

10  
11 \* Corresponding author: German Montes-Hernandez

12 E-mail address: German.MONTES-HERNANDEZ@obs.ujf-grenoble.fr


13 german\_montes@hotmail.com  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25

## 1 **Abstract**

2


3 The increasing CO<sub>2</sub> concentration in the Earth's atmosphere, mainly caused by fossil fuel  
4 combustion, has led to concerns about global warming. A technology that could possibly  
5 contribute to reducing carbon dioxide emissions is the in-situ mineral sequestration (long term  
6 geological storage) or the ex-situ mineral sequestration (controlled industrial reactors) of CO<sub>2</sub>.  
7 In the present study, we propose to use coal combustion fly-ash, an industrial waste that  
8 contains about 4.1 wt.% of lime (CaO), to sequester carbon dioxide by aqueous carbonation.  
9 The carbonation reaction was carried out in two successive chemical reactions, firstly the  
10 irreversible hydration of lime:

11



12 secondly, the spontaneous carbonation of calcium hydroxide suspension:

13



14 A high CaO-CaCO<sub>3</sub> chemical transformation (approximately 82%) was estimated by mass  
15 balance after two hours of reaction at 30°C. The carbonation of CaO was independent on the  
16 initial pressure of CO<sub>2</sub> (10, 20, 30 and 40 bar) and it was slightly affected by the temperature  
17 of reaction (30 and 60 °C). The precipitate calcium carbonate was characterized by isolated  
18 micrometric particles and micrometric agglomerates of calcite (SEM observations). In  
19 addition, the calcite precipitation and lime dissolution were confirmed by comparison of X-  
20 ray diffraction spectra. This experimental study demonstrates that one ton of fly-ash could  
21 sequester up to 26 kg of CO<sub>2</sub>. This confirms the possibility to use the alkaline liquid-solid  
22 waste for CO<sub>2</sub> mitigation.

23 **Keywords:** Mineral sequestration of CO<sub>2</sub>; Fly-ash; Aqueous carbonation; Calcium  
24 oxide; Calcite

25

## 1 **1. Introduction**

2 The global warming of Earth's near-surface, air and oceans in recent decades is a direct  
3 consequence of anthropogenic emission of greenhouse gases into the atmosphere such as  
4 CO<sub>2</sub>, CH<sub>4</sub>, N<sub>2</sub>O and CFCs (1). The CO<sub>2</sub> emissions contribute approximately 60% to this  
5 climate change. From the time of the industrial revolution that started the 1860's, 75% of CO<sub>2</sub>  
6 emissions discharged into the atmosphere are caused by the burning of fossil fuels (26.4 ± 1.1  
7 Gt CO<sub>2</sub> yr<sup>-1</sup> for the 2000-2005 period), and the remaining 25% by land use change (1).  
8 Although oceans and terrestrial biosphere can take up high amounts of the CO<sub>2</sub> emitted, about  
9 45% remains in the atmosphere as stable specie that may stay for many thousands of years  
10 (1). The continuous increase of atmospheric CO<sub>2</sub> might lead to stress on drinking water  
11 availability, species extinction, melting of ice sheets and coastal flooding (2).

12 Motivated by concerns about climate change, technical solutions are searched to minimize  
13 these harmful consequences. The main actions include: (I) the increase of the efficiency of  
14 energy conversion, (II) the reduction of energy demand and (III) the use of carbon free energy  
15 sources (nuclear, solar, wind, geothermal and biomass energy) (3). However, fossil fuels  
16 account for 85% of world energy needs in the current energy system, and hence, rapid  
17 variations of the demand or the prices in the market may seriously harm the global economy.  
18 Likewise, the use of fossil fuels will likely continue at the next decades owing to both its low  
19 cost and high availability.

20 An alternative to reduce the CO<sub>2</sub> emission without modifying the energy production  
21 system is the retention or sequestration of carbon dioxide in stable geological reservoirs (4-7).  
22 Such a strategy, so-called geological carbon sequestration, consists of capturing gaseous CO<sub>2</sub>  
23 from emissions sources and injecting it as a supercritical fluid in terrestrial reservoirs, such as  
24 saline aquifers, depleted oil and gas fields or deep coal seams. In geological reservoirs, the  
25 supercritical CO<sub>2</sub> could be retained by stratigraphic or structural trapping (physical isolation),

1 solubility trapping (dissolved in the aqueous phase) and/or hydrodynamic trapping (associated  
2 to long residence time of dissolved CO<sub>2</sub>-bearing fluids in aquifers). However, the main  
3 scientific concerns inquiring the geological carbon sequestration applicability are the high  
4 pressure and temperature variations caused by the large CO<sub>2</sub> accumulation on the reservoirs.  
5 These thermodynamic variations could exert forces that diminish the reservoir confinement  
6 due to the formation of cracks and faults either in reservoir itself or in the cap rocks.  
7 Moreover, the CO<sub>2</sub> dissolution into the pore water and the consecutive carbonic acid  
8 formation can result in the dissolution of several minerals (mainly carbonate, oxides and  
9 hydroxide minerals) affecting the long-term confinement properties of the reservoirs (8).

10 In terrestrial reservoirs, the CO<sub>2</sub> pressure can decrease in the long term as a consequence  
11 of another retention mechanism: mineral trapping or mineralogical carbon sequestration. The  
12 stored CO<sub>2</sub> may transform to stable carbonate minerals by reactions with aqueous ions  
13 (mainly calcium, magnesium and iron) resulting from silicate weathering (9-12). Although  
14 this mechanism favours the permanent CO<sub>2</sub> sequestration, it is expected to be slow in  
15 geological formation (hundreds of years) due to the slow kinetics of silicate mineral  
16 dissolution and carbonate mineral precipitation. However, mineralogical carbon sequestration  
17 could contribute significantly to CO<sub>2</sub> sequestration in the proximity of the emission source,  
18 without the need of storing the gas into a geological reservoir.

19 Soong et al. (13) proposed the use of mineralogical carbon sequestration in controlled  
20 reactors as a viable approach to reduce CO<sub>2</sub> emissions into the atmosphere using by-products  
21 from coal combustion in power plants (fly-ash) and oil and gas production (brine solutions).  
22 Brine solutions act as calcium and magnesium source favouring the CO<sub>2</sub> retention by  
23 carbonate precipitation. Fly-ash was used to increase the pH level of the reactant brine and  
24 also as an additional source of calcium to enhance reaction efficiency for the carbonation  
25 process.

1 Coal combustion in power plants provides approximately 40% of world electricity  
2 generation. At present, the coal reserves are estimated around 900 billion ton (14).  
3 Considering that coal consumption reached 5 billion tonnes in 2003, coal-energy production  
4 will continue, and even increase, in the next centuries due to the energy demand for industrial  
5 and domestic uses (15). Therefore, the continuous building of power plants is envisaged to  
6 hold this energy production system. This may cause serious disruption to the global climate  
7 since each 500 MW coal power plant emits about 3 million tonnes of CO<sub>2</sub> per year. Likewise,  
8 the worldwide production of fly-ash, estimated currently at 600 million tonnes per year, will  
9 also increase exponentially in the near future. The main producers of fly-ashes are China,  
10 Russia and the United States of America.

11 Fly-ash material is used as cement raw material and as a partial replacement for cement in  
12 concrete. However, the global production of fly-ash exceeds their potential uses (16), and  
13 hence, it is considered a residual by-product. Only around a 30% of the total production is  
14 used as a construction material. At present, numerous investigations are focused on the search  
15 of new applications for this residue. Three main research lines use fly-ash: i) to synthesize  
16 zeolites to be applicable as filter material in water decontamination and gas retention (17,18),  
17 ii) as an effective technique in metal retention processes in contaminated soils (19,20) and, iii)  
18 for the treatment of mining wastes producers of acid mine drainage (21,22). Although Soong  
19 et al. (13) propose the use of fly ash to sequester CO<sub>2</sub>, brine solutions were the main agent  
20 acting in the carbonation process. Moreover, these authors do not calculate the amount of CO<sub>2</sub>  
21 sequestered during the process.

22 The objective of integrated waste management is the search for sustainable development,  
23 i.e. to balance the fulfilment of human needs with the protection of the natural environment in  
24 the present and indefinite future. With this in mind, the main aim of this work is precisely to  
25 quantify the CO<sub>2</sub> amount that may be sequestered by calcite precipitation using fly-ash-water

1 dispersion. This study is in our opinion especially attractive since the residual solid by-  
2 products from power plants could be used to mitigate the residual gaseous wastes produced by  
3 the same plants.

## 4 5 **2. Materials and methods**

### 6 7 **2.1 Fly-ash material**

8 The fly-ash used in the present study is a waste residue generated from coal combustion at  
9 Los Barrios power station, Cádiz, south Spain. It is a powder composed mainly of spherical  
10 microparticles collected from electrostatic precipitators located at the outlet of the chimney  
11 where combustion gasses are liberated into the atmosphere. Size distribution analysis indicates  
12 that the particles have a median diameter of 40  $\mu\text{m}$ . The specific surface area is  $0.63 \pm 0.022$   
13  $\text{m}^2 \text{g}^{-1}$  determined by BET gas adsorption method (MICROMERITICS ASAP 2000  
14 instrument). Mineral abundances are similar to those reported by Querol *et al.* (23), and show  
15 that fly-ash is composed of mullite (20.8 wt.%), quartz (4.5 %), lime (4.1%), anhydrite  
16 (1.3%), K-feldspar (2.5 %), magnetite (0.5 %) and a chalco-aluminosilicate glass phase  
17 (66.4%). The chemical composition measured by X-ray fluorescence (XRF, BRUKER  
18 PIONEER instrument) shows that Los Barrios fly-ash is a residue rich in Si (41.3 wt.%  $\text{SiO}_2$ ),  
19 Al (27.5 wt.%  $\text{Al}_2\text{O}_3$ ), C (16 wt.%  $\text{CO}_2$ ), Ca (5 wt.%  $\text{CaO}$ ), and Fe (3.3 wt.%  $\text{Fe}_2\text{O}_3$ ) with  
20 minor elements (wt.%): Sr (0.3%), Cl (0.02%), Cr (0.01%), Ni (0.02%), Zn (0.01%), V  
21 (0.01%), Cu (0.01%), Co (0.01%) and Sc (0.003%). The presence of lime ( $\text{CaO}$ , 4.1 wt%) in  
22 fly-ash accounts for the high potential of both alkalinity and dioxide carbon sequestration as  
23 discussed below.

## 2.2 CO<sub>2</sub> sequestration experiments in a stirred reactor

One litre of high-purity water with electrical resistivity of 18.2 MΩ cm and 100g of fly-ash were placed in a titanium reactor (autoclave Parr with internal volume of two litres). The fly-ash particles were immediately dispersed by mechanical stirring (450 rpm). The dispersion (solution + solid particles) was then heated to 30 or 60°C using an oven specifically adapted to the reactor. When the dispersion temperature was reached, 10, 20, 30 or 40 bar of CO<sub>2</sub> (provided by Linde Gas S.A.) was injected in the reactor (see Fig. 1). This was the initial pressure of CO<sub>2</sub> which was equal to the total initial pressure in the system. Previous experiments showed that after two hours of reaction the pressure drop was close to the thermodynamic equilibrium in the system. For this reason, we considered a reaction time of two hours for all experiments in the present study.

Obviously, both the sorption-dissociation of CO<sub>2</sub> in the solution and aqueous carbonation process produce a global pressure drop in the system,  $P_{global\_pressure-drop}$ . In order to estimate the pressure drop produced only by the process of CaO carbonation (noted  $P_{carbonation\_pressure-drop}$ ), two complementary systems were proposed for each experiment. Firstly, the pressure drop  $P_{water\_pressure-drop}$  related to the sorption-dissociation of CO<sub>2</sub> into pure water only was measured. Secondly, the pressure drop  $P_{Ca-rich\_pressure-drop}$  related to the sorption-dissociation of CO<sub>2</sub> in a Ca-rich solution was measured independently. In this second experiment, a concentration of 1g/L of calcium was chosen, that represented the average concentration after fly-ash dispersion in water. These two experiments demonstrated that the Ca-concentration (0-1g/L) has no measurable effect on the sorption-dissociation of CO<sub>2</sub> because the monitored pressure drop in pure water  $P_{water\_pressure-drop}$  was equivalent to the monitored pressure drop in presence of Ca  $P_{Ca-rich\_pressure-drop}$ . Consequently, the pressure drop produced by the carbonation process of CaO was calculated by a simple pressure balance:

$$P_{carbonation\_pressure-drop} = P_{global\_pressure-drop} - P_{water\_pressure-drop} \quad (1)$$

1 Under isothermal conditions,  $P_{global\_pressure-drop}$  and  $P_{water\_pressure-drop}$  are proportional to the  
2 initial CO<sub>2</sub> pressure.

3 At the end of the experiment, the reactor was removed from the heating system and was  
4 immersed into cold water. The reaction cell was depressurized for 15 minutes during the  
5 water cooling period. Then, water cooling at 30°C the reactor was disassembled, and the solid  
6 product was separated by centrifugation (30 minutes at 12,000 rpm), decanting the  
7 supernatant solutions. Finally, the solid product was dried directly in the centrifugation flasks  
8 for 48 h at 65°C. The supernatant solutions were filtered through a 0.2- $\mu$ m Teflon filter.  
9 Adsorption on the filter and filter holder was considered negligible. The filtered solutions  
10 were immediately acidified for measurement of [Ca], [Ni], [Zn], [Cu] and [Sr] by Inductively  
11 Coupled Plasma Atomic Emission Spectrometry (ICP-AES).

### 13 2.3 Characterization of the solid phase

14 The mineralogical characterization of the starting material and solid products was carried  
15 out by X-ray diffraction (XRD, powder method) using a D501 SIEMENS diffractometer.  
16 Working conditions were CoK $\alpha$  monochromatic radiation ( $\lambda=1.7902 \text{ \AA}$ ), 37.5 mA and 40 kV.  
17 The experimental measurement parameters were 12s counting time per 0.02° 2 $\theta$  step in the 5-  
18 80° 2 $\theta$  range. The detection is performed by a kevox Si(Li) detector. Morphological analyses  
19 were also characterized by means of a scanning electron microscopy (SEM), with a JEOL  
20 JSM-5410 instrument, equipped with an energy dispersive system (EDS) for the chemical  
21 microanalysis.

### 3. Results and discussion

A previous investigation showed that the carbonation of calcium hydroxide suspension at high pressure of CO<sub>2</sub> (initial P<sub>CO<sub>2</sub></sub>=55 bar) and moderate and high temperature (30 and 90°C) is a potential method to synthesize fine particles of calcite (24). In addition, the reported results have important ecological implications for the ex-situ mineral sequestration of CO<sub>2</sub> by alkaline liquid-solid waste such as fly-ash, bottom ash, Ca/Mg-rich silicates, alkaline waste water, etc. For this reason, the current study was focussed on the mineral sequestration of CO<sub>2</sub> by aqueous carbonation of fly-ash. In the following sub-sections, the chemical reactions of CO<sub>2</sub> sequestration by fly-ash and, the calculation of the sequestered quantity of CO<sub>2</sub> by calcite precipitation and kinetic modelling of sequestered CO<sub>2</sub> in a fly-ash-water suspension are described and discussed.

#### 3.1 Chemical reactions of CO<sub>2</sub> sequestration by fly-ash

The SEM images of solid product (Figure 2), the comparison of x-ray diffraction spectra of the starting material and the solid product (Figure 3) and ICP-AES analysis in the solutions, suggest a simple reaction mechanism for CO<sub>2</sub> mineral sequestration by fly-ash in two successive steps: firstly the irreversible hydration of calcium oxide or lime:



secondly, the spontaneous carbonation of calcium hydroxide suspension:



The precipitate calcium carbonate is characterized by isolated micrometric particles and micrometric agglomerates of calcite (Figure 2). In addition, the calcite precipitation and lime (CaO) dissolution were confirmed by comparison of X-ray diffraction spectra (Figure 3).

1 Finally, the chemical-element concentrations for Ca, Ni, Zn, Cu and Sr in the solution after  
 2 two hours of fly-ash-pure water-carbon dioxide interactions suggest a preferential and rapid  
 3 dissolution of lime phase and possibly a slight dissolution of the glass phase ( $[Ca] \approx$   
 4  $800\text{mg/L}$ ) (22). Concerning, the trace elements (contained initially in the fly-ash) only the  
 5 strontium was detected in the solution by ICP-AES ( $[Sr] \approx 8\text{mg/L}$ ). Consequently, the  
 6 concentrations of Ni, Zn and Cu were considered to be smaller than 6 ppb (detection limit).  
 7 This demonstrates that the fly-ash dispersion into pure water did not favour the liberation of  
 8 toxic metallic ions after two hours of solid-fluid interaction at moderate temperature. In fact,  
 9 preliminary experiments show that the carbonation process favours the co-precipitation and/or  
 10 incorporation of the dissolved impurities into the calcite crystallographic network.

### 12 3.2 The sequestered quantity of $\text{CO}_2$ by calcite precipitation

13 A simplified method was developed to estimate the sequestered quantity of  $\text{CO}_2$  by carbonate  
 14 precipitation. This method was partially described in the section 2.2. Herein, the pressure drop  
 15 produced by the carbonation process of CaO (Eqs. 2 and 3) in the system was calculated by a  
 16 simple pressure balance (Eq. 1). The carbonation pressure drop,  $P_{\text{carbonation\_pressure-drop}}$  was  
 17 equal to 1.5 bar for all experiments (Figure 4b). It was independent on the initial pressure of  
 18  $\text{CO}_2$  (10, 20, 30, 40 bar) and was slightly affected by the temperature of reaction (30 and  
 19  $60^\circ\text{C}$ ). The results of the pressure drop kinetics for 30 bar (as initial pressure of  $\text{CO}_2$ ) are  
 20 shown on Figure 4a. Here, it was observed that the equilibrium of pressure drop was reached  
 21 after about five hours of solid-fluid interaction.

22 Considering that  $\text{CO}_2$  is an ideal gas, the quantity of  $\text{CO}_2$  consumed by the carbonation  
 23 process can be calculated as follows:

$$24 \quad n_{\text{CO}_2} = \frac{P_{\text{carbonation\_pressure\_drop}} V}{RT} \quad (4)$$

1 where, the  $V$  is the reactor volume occupied with gas (1L),  $T$  is the temperature of reaction  
 2 ( $\approx 303^\circ\text{K}$ ) and  $R$  is the gas constant (0.08314472 L.bar/ $^\circ\text{K}$ .mol). Using the measured value  
 3  $P_{\text{carbonation\_pressure-drop}} = 1.5$  bar, we calculated that 0.05954 mol of  $\text{CO}_2$  were consumed by the  
 4 carbonation process. Taking into account reactions (2-3) and the fact that the fly-ash contains  
 5 4.1wt.% of lime (CaO), the carbonation efficiency  $CE$  can be calculated by the following  
 6 expression:

$$7 \quad CE = \frac{n_{\text{CO}_2} * M_{\text{CO}_2}}{\frac{w_{\text{CaO}}}{M_{\text{CaO}}} * M_{\text{CO}_2}} * 100 \quad (5)$$

8 where,  $n_{\text{CO}_2}$  is the mol number of consumed  $\text{CO}_2$ , calculated by Eq. 4 (0.05954 mol),  $M_{\text{CO}_2}$  is  
 9 the molar mass of  $\text{CO}_2$  (44.01 g/mol),  $w_{\text{CaO}}$  is the starting mass of CaO in the reactor (4.1g)  
 10 and  $M_{\text{CaO}}$  is the molar mass of CaO (56.077g/mol). The carbonation efficiency was equal to  
 11 82% after two hours of solid-fluid interactions at 30 and 60°C.

12 Theoretically one ton of fly-ash containing 4.1% of lime could sequester 32.17kg of  $\text{CO}_2$ .  
 13 With our experimental protocol, 26.19kg of  $\text{CO}_2$  per ton of fly-ash could be successfully  
 14 sequestered into stable calcite. Indeed, this is an attractive result concerning the ex-situ  
 15 mineral sequestration of  $\text{CO}_2$ .

### 17 3.3 Kinetic modelling of sequestered $\text{CO}_2$ in a fly-ash-water suspension

18 The monitoring of the pressure drop for any controlled system under ideal gas conditions  
 19 allows the kinetic modelling of sequestered  $\text{CO}_2$  after gas injection in a solid-liquid system  
 20 (fly-ash-water dispersion for this study). This can be done using a simple correlation function,  
 21  $n_{\text{total\_CO}_2} = f(t)$ , where  $n_{\text{total\_CO}_2}$  is the total mol quantity of sequestered  $\text{CO}_2$  in the fly-ash-water  
 22 dispersion and  $t$  is the time after gas injection.

23 Several kinetic models including first-order, pseudo-first-order, second-order, pseudo-second-  
 24 order, parabolic diffusion and power function kinetic expressions are reported in the literature

1 for fitting the kinetic experimental or calculated data of the solid-fluid interaction processes.  
 2 For this study, the kinetic modelling concern the total sequestered quantity of CO<sub>2</sub> in a fly-  
 3 ash-water dispersion, i.e. the CO<sub>2</sub> sorption-dissociation in water, possibly the CO<sub>2</sub> adsorption  
 4 on the fly-ash and, sequestered CO<sub>2</sub> by carbonation process. For this case, the best fit (attested  
 5 by a correlation factor close to 1) of the experimental-calculated data was achieved when  
 6 using a pseudo-second-order kinetic model according to the following expression:

$$7 \quad \frac{dn_{total\_CO2,t}}{dt} = k_s (n_{total\_CO2,max} - n_{total\_CO2,t})^2 \quad (6)$$

8 where  $k_s$  is the rate constant of sequestered CO<sub>2</sub> [1/mol s] for a given initial pressure of CO<sub>2</sub>  
 9 in the system,  $n_{total\_CO2,max}$  is the maximum sequestered quantity of carbon dioxide at  
 10 equilibrium [mol],  $n_{total\_CO2,t}$  is the sequestered quantity of carbon dioxide at any time,  $t$ ,  
 11 [mol].

12 The integrated form of Equation (6) for the boundary conditions  $t = 0$  to  $t = t$  and  $n_{total\_CO2,t} =$   
 13  $0$  to  $n_{total\_CO2,t} = n_{total\_CO2,t}$  is represented by a hyperbolic equation:

$$14 \quad n_{total\_CO2,t} = \frac{n_{total\_CO2,max} * t}{\left( \frac{1}{k_s * n_{total\_CO2,max}} \right) + t} \quad (7)$$

15 In order to simplify the fitting of experimental-calculated data, we have defined the constant  
 16  $t_{1/2} = 1/k_s * n_{total\_CO2,max}$ . Physically,  $t_{1/2}$  represents the time after which half of the maximum  
 17 sequestered quantity of carbon dioxide was reached and is called “half-sequestered CO<sub>2</sub>  
 18 time”. It can be used to calculate the initial rate of sequestered CO<sub>2</sub>,  $v_{0,s}$ , [mol/s].

$$19 \quad v_{0,s} = \frac{n_{total\_CO2,max}}{t_{1/2}} = k_s (n_{total\_CO2,max})^2 \quad (8)$$

20 The numerical fit of the experimental-calculated kinetic curve at 30 bar and 30°C ( $n_{total\_CO2,t}$   
 21 vs.  $t$ ) using Eq. (7) is shown on Figure 5. The parameters  $t_{1/2}$  and  $n_{total\_CO2,max}$  were estimated  
 22 by applying a non-linear regression using the least-squares method. The initial rate of

1 sequestered CO<sub>2</sub> was calculated using Eq. 8 ( $v_{0,s} = 8.28 \times 10^{-4}$  mol/s) at 30°C. This value  
2 indicates that the mass transfer of compressed CO<sub>2</sub> in contact with solid-water dispersion is  
3 higher than CO<sub>2</sub> transfer at atmospheric conditions or at low pressure (25-26).  
4

### 5 3.4 Conclusion

6 The results presented in this study showed that the ex-situ mineral sequestration of CO<sub>2</sub> by  
7 aqueous carbonation of fly-ash could be an attractive and potential method to reduce the CO<sub>2</sub>  
8 emission in the atmosphere from power plants. This experimental investigation demonstrated  
9 that one ton of fly-ash, an industrial waste that contains about 4.1 wt.% of lime (CaO), could  
10 sequester up to 26 kg of CO<sub>2</sub>. This confirms the possibility to use the alkaline liquid-solid  
11 waste for CO<sub>2</sub> mitigation.  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25

1 **Acknowledgements**

2

3 The authors are grateful to the National Research Agency, ANR (GeoCarbone-  
4 CARBONATATION project) and the National Research Council (CNRS), France, for  
5 providing a financial support for this work. Delphine Tisserand and Nicolas Geoffroy are  
6 thanked for their technical assistance.

7

8

9

10

11

12

13

14

15

16

17

18

19

20

21

22

23

24

25

## 1 **References**

2

3 (1) IPCC (Intergovernmental Panel on Climate Change). Climate Change 2007: The  
4 Physical Science Basis: Summary for Policymakers, 2007, [http://ipcc-](http://ipcc-wg1.ucar.edu/wg1/Report/AR4WG1_Pub_SPM-v2.pdf)  
5 [wg1.ucar.edu/wg1/Report/AR4WG1\\_Pub\\_SPM-v2.pdf](http://ipcc-wg1.ucar.edu/wg1/Report/AR4WG1_Pub_SPM-v2.pdf)

6 (2) IPCC (Intergovernmental Panel on Climate Change). Climate Change 2007: Climate  
7 Change Impacts, Adaptations, and Vulnerability, 2007, <http://ipcc-wg2.org/index.html>

8 (3) Schrag, D. P. Confronting the Climate-Energy Challenge. *Elements* **2007**, *3*, 171-178.

9 (4) Bachu, S. Sequestration of CO<sub>2</sub> in geological media: criteria and approach for site  
10 selection in response to climate change. *Energy Convers. Manage.* **2000**, *41*, 953-970.

11 (5) Bachu, S. Sequestration of CO<sub>2</sub> in geological media in response to climate change: road  
12 map for site selection using the transform of the geological space into the CO<sub>2</sub> phase  
13 space. *Energy Convers. Manage.* **2002**, *43*, 87-102.

14 (6) Bachu, S; Adams, J. J. Sequestration of CO<sub>2</sub> in geological media in response to climate  
15 change: capacity of deep saline aquifers to sequester CO<sub>2</sub> in solution. *Energy Convers.*  
16 *Manage.* **2003**, *44*, 3151–3175.

17 (7) Friedmann, S. J. Geological Carbon Dioxide Sequestration. *Elements* **2007**, *3*, 179-184.


18 (8) Kharaka, Y. K.; Cole, D. R.; Hovorka, S. D.; Gunter, W. D.; Knauss, K. G.; Friefeld, B.  
19 M. Gas-water-rock interactions in Frio Formation following CO<sub>2</sub> injection: Implications  
20 for the storage of greenhouse gases in sedimentary basins. *Geology* **2006**, *34*, 577-580.

21 (9) Gunter, W. D.; Perkins, E. H.; Hutcheon, I. Aquifer disposal of acid gases: modeling of  
22 water–rock reactions for trapping of acid wastes. *Appl. Geochem.* **2000**, *15*, 1085-1095.

23 (10) Kaszuba, J. P.; Janecky, D. R.; Snow, M. G. Carbon dioxide reaction processes in a  
24 model brine aquifer at 200 °C and 200 bars: implications for geologic sequestration of  
25 carbon. *Appl. Geochem.* **2003**, *18*, 1065-1080.


- 1 (11) Kaszuba, J. P.; Janecky, D. R.; Snow, M. G. Experimental evaluation of mixed fluid  
2 reactions between supercritical carbon dioxide and NaCl brine: Relevance to the  
3 integrity of a geologic carbon repository. *Chem. Geol.* **2005**, *217*, 277-293.
- 4 (12) Giammar, D. E.; Bruant, R. G.; Peters, C. A. Forsterite dissolution and magnesite  
5 precipitation at conditions relevant for deep saline aquifer storage and sequestration of  
6 carbon dioxide. *Chem. Geol.* **2005**, *217*, 257-276.
- 7 (13) Soong, Y.; Fauth, D. L.; Howard, B. H.; Jones, J. R.; Harrison, D. K.; Goodman, A. L.;  
8 Gray, M. L.; Frommell, E. A. CO<sub>2</sub> sequestration with brine solution and fly ashes.  
9 *Energy Convers. Manage.* **2006**, *47*, 1676-1685.
- 10 (14) BP (British Petroleum). Statistical Review of World Energy, 2006,  
11 <http://www.bp.com/productlanding.do?categoryId=6848&contentId=7033471>
- 12 (15) Energy Information Administration. International Energy Annual. Department of  
13 Energy, Washington, DC, 2006, [www.eia.doe.gov/iea](http://www.eia.doe.gov/iea)
- 14 (16) Manz, O. E. Worldwide production of coal ash and utilization in concrete and other  
15 products. *Fuel* **1997**, *76*, 691-696.
- 16 (17) Querol, X.; Umaña, J. C.; Plana, F.; Alastuey, A.; Lopez-Soler, A.; Medinaceli, A.;  
17 Valero, A.; Domingo, M. J.; Garcia-Rojo, E. Synthesis of zeolites from fly ash at pilot  
18 plant scale. Examples of potential applications. *Fuel* **2001**, *80*, 857-865.
- 19 (18) Cama, J.; Ayora, C.; Querol, X.; Ganor, J. Dissolution kinetics of synthetic zeolite NaP1  
20 and its implication to zeolite treatment of contaminated waters. *Environ. Sci. Technol.*  
21 **2005**, *39*, 4871-4877.
- 22 (19) Brake, S. S.; Jensen, R. R.; Mattox, J. M. Effects of coal fly ash amended soils on trace  
23 element uptake in plants. *Environ. Geol.* **2003**, *45*, 680-689.
- 24 (20) Dermatas, D.; Meng, X. Utilization of fly ash for stabilization/solidification of heavy  
25 metal contaminated soils. *Eng. Geol.* **2003**, *70*, 377-394.

- 1 (21) Pérez-López, R.; Nieto, J. M.; Almodóvar, G. R. Immobilization of toxic elements in  
2 mine residues derived from the mining activities in the Iberian Pyrite Belt (SW Spain):  
3 laboratory experiments. *Appl. Geochem.* **2007**, in press,  
4 doi:10.1016/j.apgeochem.2007.03.055.
- 5 (22) Pérez-López, R.; Cama, J.; Nieto, J. M.; Ayora, C. The iron-coating role on the  
6 oxidation kinetics of a pyritic sludge doped with fly ash. *Geochim. Cosmochim. Acta*  
7 **2007**, *71*, 1921-1934.
- 8 (23) Querol, X.; Umaña, J. C.; Alastuey, A.; Ayora, C.; Lopez-Soler, A; Plana, F. Extraction  
9 of soluble major and trace elements from fly ash in open and closed leaching systems.  
10 *Fuel* **2001**, *80*, 801-813.
- 11 (24) Montes-Hernandez, G., Renard, F., Geoffroy, N., Charlet, L., Pironon, J. Calcite  
12 precipitation from CO<sub>2</sub>-H<sub>2</sub>O-Ca(OH)<sub>2</sub> slurry under high pressure of CO<sub>2</sub>. *J. Cryst.*  
13 *Growth* **2007**, *308*, 228-236
- 14 (25) Akanksha, Pant, K. K., Srivastava, V. K. Mass transport correlation for CO<sub>2</sub> absorption  
15 in aqueous monoethanolamine in a continuous film contactor. *Chem. Eng. Process.*  
16 **2007**, doi:10.1016/j.cep.2007.02.008.
- 17 (26) Haubrock, J., Hogendoorn, J. A., Versteeg G. F. The applicability of activities in kinetic  
18 expressions: A more fundamental approach to represent the kinetics of the system CO<sub>2</sub>-  
19 OH<sup>-</sup>-salt in terms of activities. *Chem. Eng. Sci.* **2007**, doi:10.1016/j.ces.2007.06.018.
- 20  
21  
22  
23  
24  
25

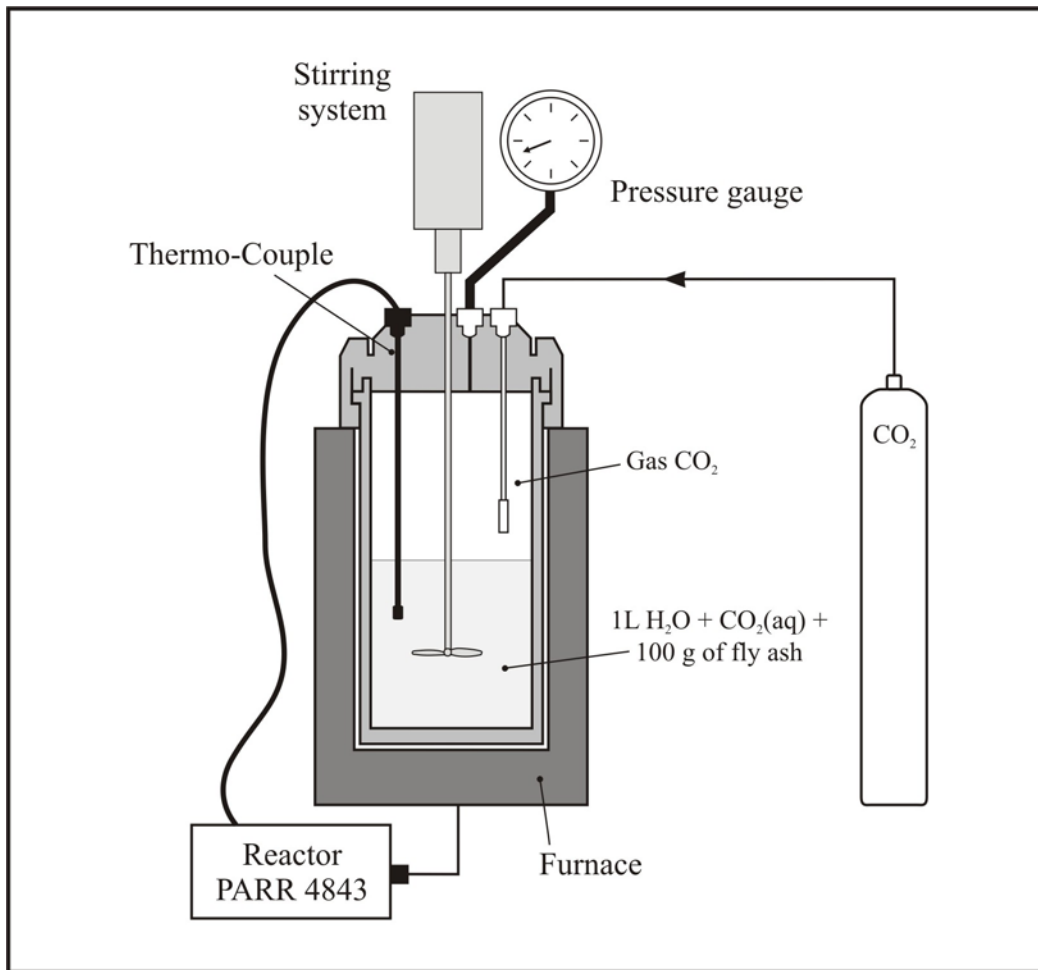


1  
 2  
 3  
 4  
 5  
 6  
 7  
 8  
 9  
 10  
 11  
 12  
 13

Figure 1. Schematic experimental system for mineral sequestration of CO<sub>2</sub> by aqueous carbonation of fly-ash in a stirred reactor.

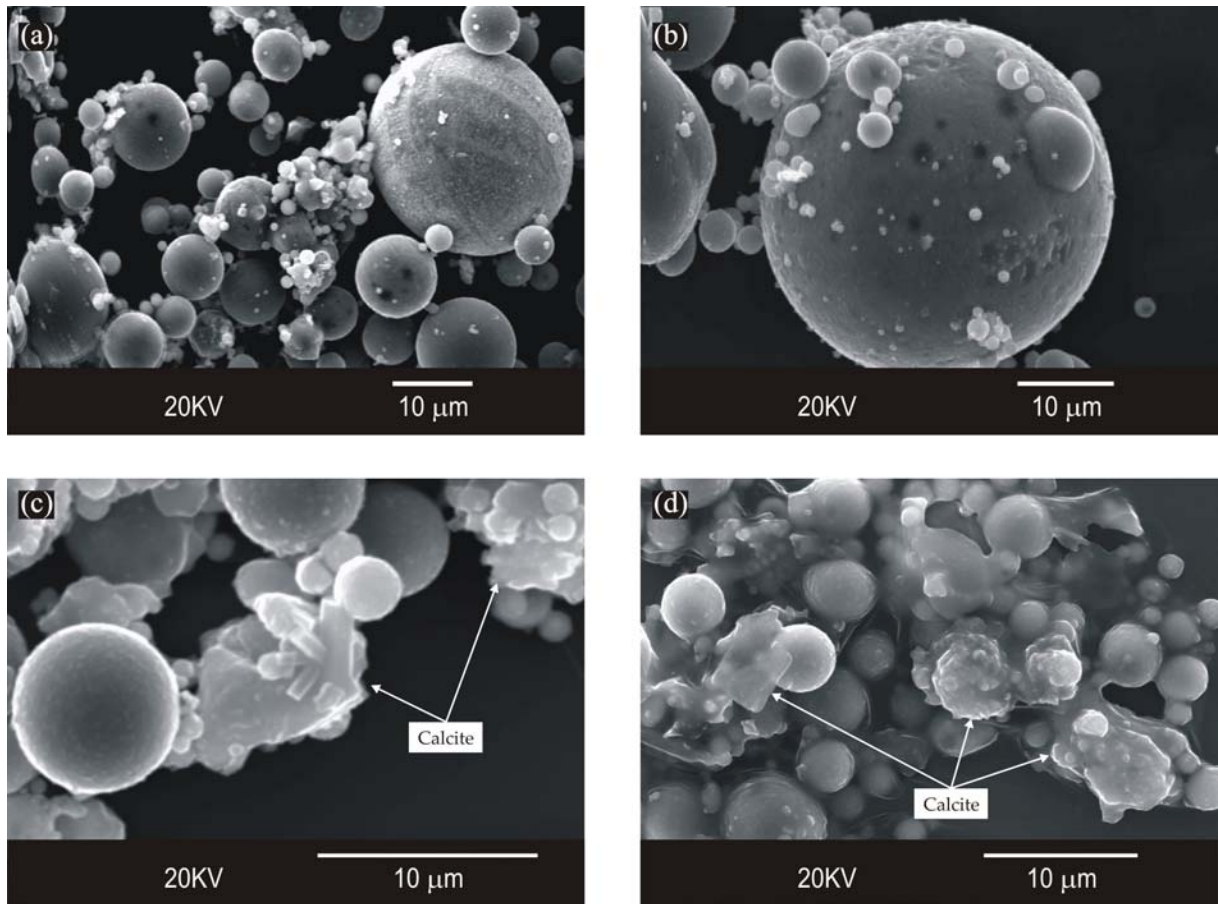



1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14

Figure 2. (a-b) SEM images of fly-ash before reaction. (c-d) Calcite particles precipitated during CO<sub>2</sub> sequestration experiments.

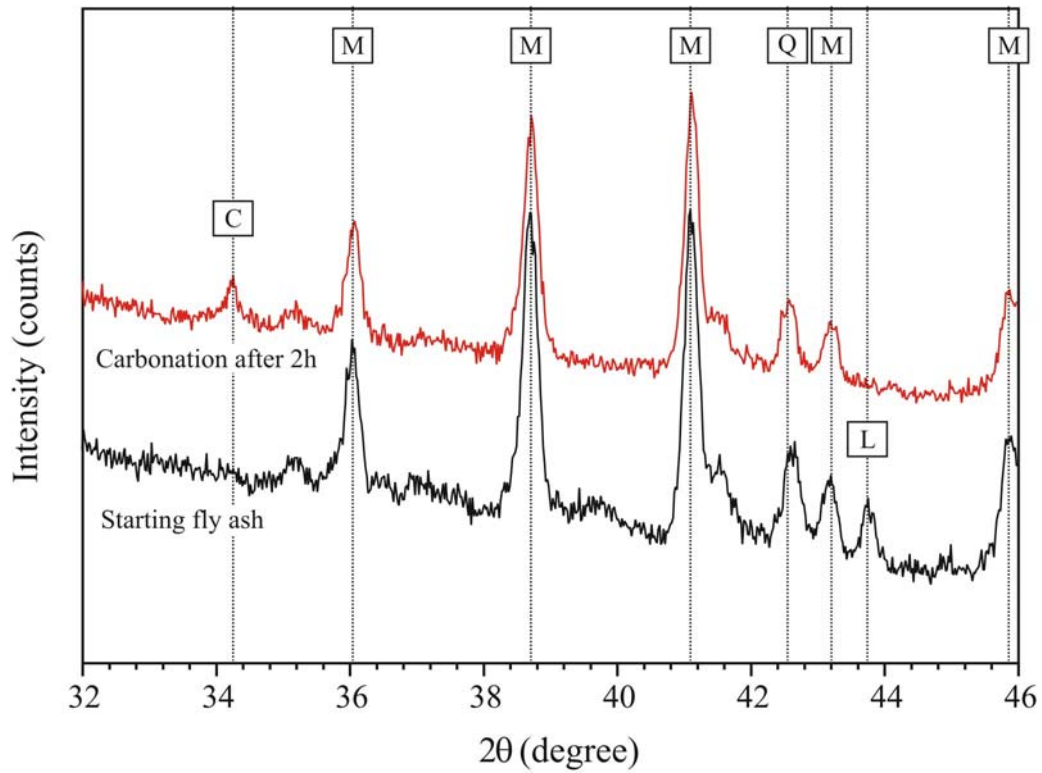


1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15

Figure 3. XRD spectra of starting fly-ash and solid products after carbonation during 2 h. C: Calcite, M: Mullite, Q: Quartz, L: Lime. These spectra demonstrate the total consumption of lime and the production of calcite.

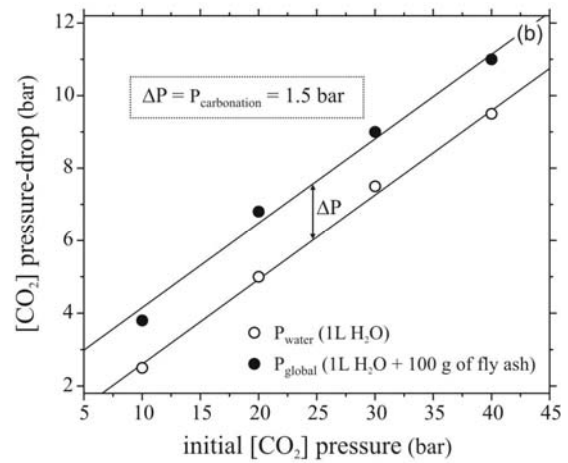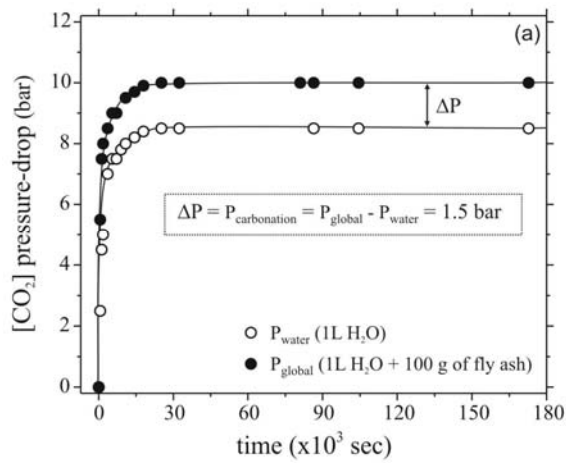

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18

Figure 4. (a) Kinetic behaviour of pressure decrease in the reactor at 30°C and for 30 bar initial pressure of CO<sub>2</sub>. (b) Linear correlation between the pressure decrease at equilibrium and the initial pressure of CO<sub>2</sub>.

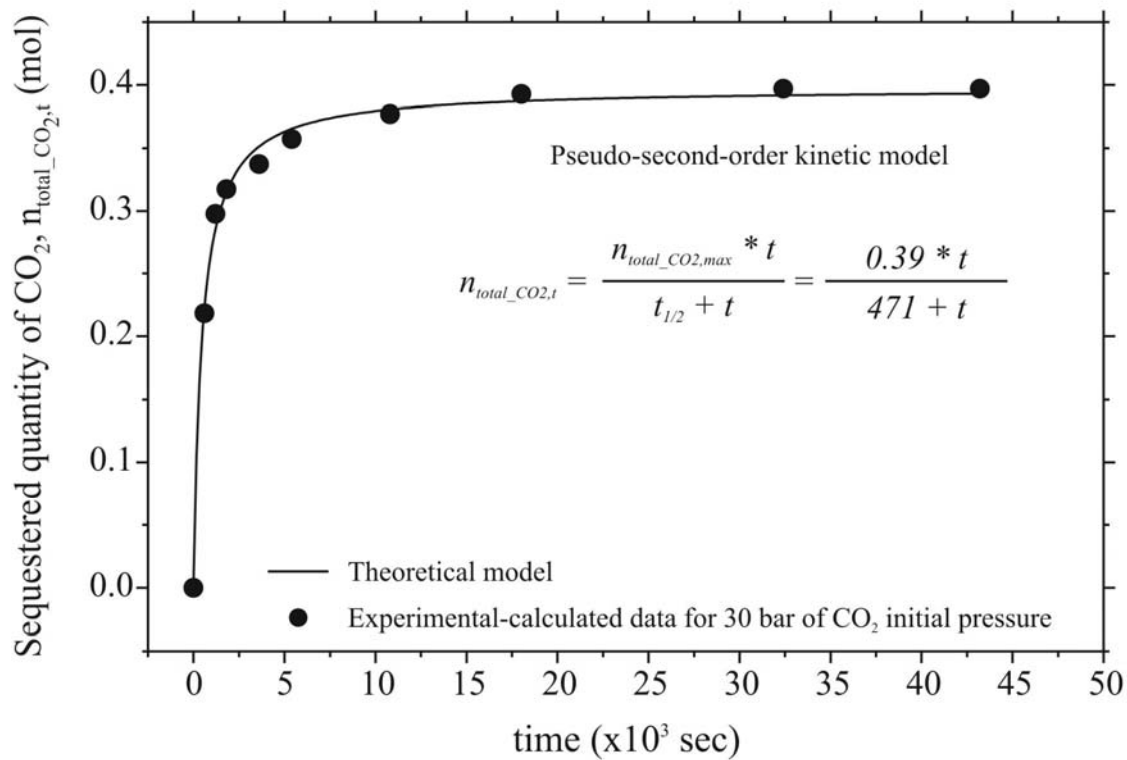

1  
2  
3  
4  
5  
6  
7  
8  
9  
10

Figure 5. Kinetic modeling of sequestered CO<sub>2</sub> in a fly-ash-water suspension for 30 bar initial pressure of CO<sub>2</sub>.