

Nematic droplets in aqueous dispersions of carbon nanotubes

Nicolas Puech, Eric Grelet, Philippe Poulin, Christophe Blanc, Paul van der Schoot

► **To cite this version:**

Nicolas Puech, Eric Grelet, Philippe Poulin, Christophe Blanc, Paul van der Schoot. Nematic droplets in aqueous dispersions of carbon nanotubes. *Physical Review E: Statistical, Nonlinear, and Soft Matter Physics*, American Physical Society, 2010, 82 (2), pp.020702(R). hal-00512715v2

HAL Id: hal-00512715

<https://hal.archives-ouvertes.fr/hal-00512715v2>

Submitted on 6 Oct 2010

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Nematic Droplets in Aqueous Dispersions of Carbon Nanotubes

Nicolas Puech,¹ Eric Grelet,¹ Philippe Poulin,¹ Christophe Blanc,² and Paul van der Schoot³

¹*Centre de Recherche Paul-Pascal, CNRS-Université Bordeaux 1,
115 Avenue Schweitzer, 33600 Pessac, France*

²*Laboratoire des Colloïdes, Verres et Nanomatériaux,
CNRS-Université Montpellier II, Place E. Bataillon, 34090 Montpellier, France*

³*Faculteit Technische Natuurkunde, Technische Universiteit Eindhoven,
Postbus 513, 5600 MB Eindhoven, Netherlands,
and Instituut voor Theoretische Fysica, Universiteit Utrecht,
Leuvenlaan 4, 3584 CE Utrecht, Netherlands*

(Dated: July 28, 2010)

Abstract

Aqueous dispersions of exfoliated, bile-salt stabilized single-wall carbon nanotubes exhibit a first order transition to a nematic liquid-crystalline phase. The nematic phase presents itself in the form of micron-sized nematic droplets also known as tactoids, freely floating in the isotropic host dispersion. The nematic droplets are spindle-shaped and have an aspect ratio of about four, irrespective of their size. We attribute this to a director field that is uniform rather than bipolar, which is confirmed by polarization microscopy. It follows that the ratio of the anchoring strength and the surface tension must be about four, which is quite larger than predicted theoretically but in line with earlier observations of bipolar tactoids. From the scatter in the data we deduce that the surface tension of the coexisting isotropic and nematic phases must be extremely low, that is, of the order of nN/m.

PACS numbers: 61.30.Hn, 61.30.Dk, 82.70.Dd

Carbon nanotubes or CNTs are colloidal particles with a very large aspect ratio, typically in the range from many tens to hundreds up to even thousands. Hence, it is not surprising that, provided they are properly stabilized against aggregation, fluid dispersions containing CNTs exhibit an Onsager-type isotropic-nematic transition [1–6]. This happens at concentrations in excess of a critical value that depends on the aspect ratio of the rods. The relevant concentration scale here is the volume or packing fraction because the driving force for the spontaneous alignment is the anisotropic volume exclusion between the particles. For the nematic to become stable the volume fraction of CNTs should be in excess of a few times the reciprocal of some average of their aspect ratios [7].

It follows that the nematic transition must occur at very low concentrations of, say, one per cent of CNTs. This, by and large, is in agreement with experimental observation, allowing for instance for the effects of polydispersity [1–6]. Often, before isotropic-nematic phase separation occurs on a macroscopic scale in dispersions of elongated colloidal particles, the nematic phase establishes itself in the form of droplets called tactoids. Tactoids have been observed in many dispersions, such as tobacco mosaic virus [8, 9], boehmite rods [10], poly(butyl glutamate), self-assembled chromonics [11], *fd* virus [12], f-actin [13], vanadium pentoxide [14, 15]. These droplets have in common their unusual elongated, spindle-like shape.

This shape can be explained by the preferential planar anchoring of the nematic director at the interface with the isotropic phase. The competition between surface tension and the elastic deformation of the bipolar director field that accommodates this preferential planar anchoring plausibly determines the optimal aspect ratio (Figure 1). If the director field of a tactoid is indeed bipolar with field lines connecting two boojum surface defects, then its shape, as described, e.g., by the aspect ratio or the tip angle, depends on its physical dimensions. This seems to be the case in all systems investigated so far. Indeed, information on the ratio of (an average of) the elastic constants and the surface tension can be obtained from the measured relation between, say, the aspect ratio and length of the droplets [13, 15–18].

In this letter, we show that aqueous dispersions of surfactant-stabilized carbon nanotubes deviate from the usual picture of a bipolar director field. The tactoids that we observe in these dispersions are also quite elongated, but display a uniform director field as it is evidenced by polarization microscopy. This ties in with our finding that the aspect ratio of

the tactoids is independent of their size, at least for the one decade range of sizes present in our samples. Theoretically, the aspect ratio of tactoids is predicted to be independent of their size if dictated by the surface tension anisotropy [16]. This is plausible if the director field is uniform and as a result of that the anchoring conditions at the surface of the drops are suboptimal. From our observations we find that the anchoring strength is about four times larger than the bare surface tension. We put forward that the surface tension must be very small indeed, possibly as low as 1 nN/m.

We prepared our CNT tactoid dispersions from an aqueous suspension of single-wall carbon nanotubes (furnished by Elicarb batch K3778) and dispersed by bile salts, at respective concentrations of 0.5% w/w CNTs and 0.5% w/w bile salts. To exfoliate the CNT bundles, sonication was applied to the suspension for three hours. A purification process by selective centrifugation was then performed on the CNT suspensions. After removing CNT aggregates by centrifugation at low speed (30 min, 3500 rpm), the longest carbon nanotubes exhibiting some entanglements and defects were removed by ultracentrifugation (45 min, 45000 rpm). A second ultracentrifugation (180 min, 45000 rpm) was applied to the CNT suspensions to obtain the nematic liquid crystalline phase, which appeared as a black pellet on the bottom of the centrifugation tube. Finally, CNT tactoids were obtained by diluting the nematic phase up to the coexistence region with the isotropic phase. Thin samples of only a few μm thick were prepared at the isotropic-nematic phase coexistence between cover slip and glass slide. The CNT tactoids were observed by optical microscopy at different magnifications between crossed polarizers.

Figure 2 shows an image by polarization microscopy of the kind of tactoids that we find in our carbon nanotube dispersions. The background is dark because the tactoids float in the coexisting isotropic liquid phase. The tactoids are indeed quite elongated and have the typical spindle-like shape. A perfect extinction is observed when the tactoids are aligned along the polarizer or analyzer direction, demonstrating that the director field is uniform, as shown on a typical tactoid in figure 3. A further study under confocal Raman microscopy also confirms that the director field is aligned along the tactoid long axis [19], which coincides with the main optical axis.

In figure 4 the aspect ratios of a large collection of tactoids is plotted against their length, which, within experimental error, is constant as advertised. Apparently, the mean aspect ratio of the tactoids is about four for tactoids up to 36 μm in length. This result

is consistent with a uniform director field in the droplets, as the aspect ratio of the drops is then dictated by the ratio of the anchoring strength and surface tension. Applying an inverse Wulff construction [20] to the shape of a typical tactoid, we have been able to probe the anisotropy of the surface free energy, σ . Shown in figure 5 is $\sigma(\theta)/\tau$, where, τ is the bare surface tension and θ the angle between the surface tangent and the director field. We find that this angle dependence is consistent with the often-used Rapini-Papoular model for the surface free energy, i.e., $\sigma = \tau(1 + \omega \sin^2 \theta)$ with ω the ratio of the anchoring energy and surface tension [21]. For the tactoid shown in the figure, we find $\omega \approx 3.4$.

From the Wulff construction, we can in fact predict the aspect ratio of a nematic drop that within a Rapini-Papoular model must be equal to $2\sqrt{\omega}$ if $\omega \geq 1$ [16]. It follows from figure 4 that for our coexisting isotropic and nematic phases of CNTs in water, $\omega = 4 \pm 1$. This is quite larger than theoretical predictions according to which $0.5 \leq \omega \leq 1.5$, at least for cylindrical particles interacting via a harshly repulsive potential [22–25].

Additional information that we can deduce from figure 4 can be obtained by realizing that according to recent calculations [16], a tactoid changes its director field from a uniform to a bipolar one if its volume $V \approx (4\pi/3)(L/2)(D/2)^2$ is larger than $(K/\tau)^3(6.25/\omega)^{18/5}$, with K an average of the Frank elastic constants. Remarkably, this crossover has so far only been observed in computer simulations [26]. It seems that even the largest tactoid in our samples with a length of $36 \mu\text{m}$, has a uniform director field. This implies that a lower bound for the ratio K/τ of the nematic of CNTs is approximately $5 \mu\text{m}$. Interestingly, this lower bound is comparable to values found for vanadium pentoxide and fd virus [15–17], although that tactoids in these two systems do exhibit a bipolar field if larger than a few μm . It is not quite clear why single-wall CNTs behave so differently from other types of elongated particle. Indeed, CNTs exhibit a phase behavior that is in good agreement with the behavior expected for bulk suspensions of rod-like particles [3]. But the structure of tactoids results from a delicate interplay of bulk and surface properties. Therefore the difference of CNTs from other materials may arise from features that could more specifically affect the surface properties. They could include particular forms of the interaction potential or specific features of the size distribution. CNTs are polydisperse and a small fraction of very long or very short particles could affect the surface properties with a little effect on the bulk behavior. Of course this is still speculative and further work will be needed to confirm whether or not the size distribution of the CNTs confined at the I-N interface differs from

that in bulk.

Finally, the scatter in the data of figure 4 potentially provides physical information because in part it must be caused by thermal fluctuations of the aspect ratio of the tactoids. The Wulff construction provides only the optimal aspect ratio but does not give an indication of its variance. Using a simple scaling Ansatz based on the Rapini-Papoular surface free energy [16] and making use of the equipartition of free energy, we find that the standard deviation of the aspect ratio must approximately be equal to $(k_B T / \tau L^2)^{1/2} \omega^{3/4}$, so depend on the size of the tactoids. In figure 4 we have indicated around the estimated average aspect ratio the standard deviation presuming a surface tension of 0.5 nN/m. The prediction follows the magnitude and size dependence of the experimental scatter in the data reasonably well. Obviously, we should not over interpret this result because we have ignored any influence of the intrinsic error in the size measurement of the tactoids.

If we accept the very small value of the surface tension that we find at face value, then it is very much smaller than values in the range of tenths to tens of $\mu\text{N}/\text{m}$ typically found for coexisting isotropic and nematic phases in dispersions of rod-like particles [27]. Values of nN/m have been found for coexisting isotropic and nematic phases but only in dispersions of colloidal platelets [28]. Clearly, the scaling theory does not give the numerical pre-factor, and this could increase the found surface tension by another factor of, say, ten. Still, this by no means takes our value within the range of the other experimentally found values.

One might of course conclude from this, that the presumption that the scatter in the data is dominated by thermal fluctuations must be wrong. Indeed, some flow can occur just after sample preparation, which can induce droplet alignment and some shape distortion. The latter is clearly seen in the largest CNT tactoids, see also figure 2. Explicit surface tension measurements, e.g., by the capillary rise method [28] on macroscopic interfaces between coexisting isotropic and nematic phases are necessary to confirm our finding, but these are outside the scope of the present paper.

In conclusion, we find nematic tactoids of aqueous dispersions of surfactant-stabilized single-wall carbon nanotubes that have a uniform director field. Our observation accounts that the aspect ratio of about four is independent of the size of these tactoids at least for lengths up to 36 μm . The crossover to a bipolar director field must occur for sizes much larger than this value, but we have not been able to confirm this.

Acknowledgments

PvdS gratefully acknowledges the hospitality and a supporting grant from Université Bordeaux 1.

- [1] S. J. Zhang and S. Kumar, *Small* **4**, 1270 (2008).
- [2] W. H. Song, I. A. Kinloch, and A. H. Windle, *Science* **302**, 1363 (2003).
- [3] S. Badaire, C. Zakri, M. Maugey, A. Derré, J. N. Barisci, G. Wallace, and P. Poulin, *Adv. Mater.* **17**, 1673 (2005).
- [4] P. K. Rai, R. A. Pinnick, A. N. G. Parra-Vasquez, V. A. Davis, H. K. Schmidt, R. H. Hauge, R. E. Smalley, and M. Pasquali, *J. Am. Chem. Soc.* **128**, 591 (2006).
- [5] C. Zamora-Ledezma, C. Blanc, M. Maugey, C. Zakri, P. Poulin, and E. Anglaret, *Nano Lett.* **8**, 4103 (2008).
- [6] V. A. Davis *et al.*, *Nature Nanotechnol.* **4**, 830 (2009).
- [7] L. Onsager, *Ann. N.Y. Acad. Sci.* **51**, 627 (1949).
- [8] J. D. Bernal and I. Fankuchen, *The journal of General Physiology* **25**, 111 (1941).
- [9] H. Maeda, *Langmuir* **13**, 4150 (1997).
- [10] M. P. B. van Bruggen, H. N. W. Lekkerkerker, G. Maret, and J. K. G. Dhont, *Phys. Rev. E* **58**, 7668 (1998).
- [11] Yu. A. Nastishin, H. Liu, T. Schneider, V. Nazarenko, R. Vasyuta, S. V. Shiyonovskii, and O. D. Lavrentovich, *Phys. Rev. E* **72**, 041711 (2005).
- [12] Z. Dogic and S. Fraden, *Phil. Trans. R. Soc. Lond. A* **359**, 997 (2001).
- [13] P. W. Oakes, J. Viamontes, and J. X. Tang, *Phys. Rev. E* **75**, 061902 (2007).
- [14] A. S. Sonin, *J. Mater. Chem.* **8**, 2557 (1998).
- [15] A. V. Kaznacheev, M. M. Bogdanov, and S. A. Taraskin, *J. Exp. Theor. Phys.*, **95**, 57 (2002).
- [16] P. Prinsen and P. van der Schoot, *Phys. Rev. E* **68**, 021701 (2003).
- [17] P. Prinsen and P. van der Schoot, *Eur. Phys. J. E* **13**, 35 (2004).
- [18] A. V. Kaznacheev, M. M. Bogdanov, and A. S. Sonin, *J. Exp. Theor. Phys.*, **97**, 1159 (2003).
- [19] N. Puech *et al.*, *Preprint*.
- [20] G. Wulff, *Z. Kristallogr.* **34**, 449 (1901).

- [21] A. Rapini and M. J. Papoular, *J. Phys. Paris, Colloq.* **30**, C4-54 (1969).
- [22] Z. Y. Chen and J. Noolandi, *Phys. Rev. A* **45**, 2389 (1992).
- [23] S.-M. Cui, O. Akcakir, and Z. Y. Chen, *Phys. Rev. E* **51**, 4548 (1995).
- [24] D. L. Koch and O. G. Harlen, *Macromolecules* **32**, 219 (1999).
- [25] P. van der Schoot, *J. Phys. Chem. B* **103**, 8804 (1999).
- [26] Yu. Trukhina, S. Jungblut, P. van der Schoot, and T. Schilling *J. Chem. Phys.* **130**, 164513 (2009).
- [27] W. Chen and D. G. Gray *Langmuir* **18**, 633 (2002).
- [28] D. van der Beek, H. Reich, P. van der Schoot, M. Dijkstra, T. Schilling, R. Vink, M. Schmidt, R. van Roij, and H. Lekkerkerker, *Phys. Rev. Lett.* **97**, 087801 (2006).

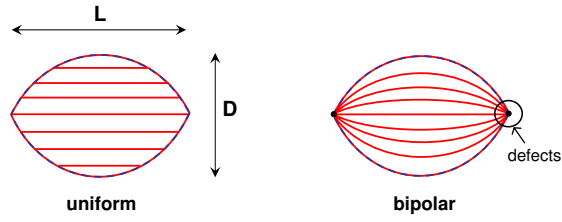


FIG. 1: (Color online) Schematic representation of the shape and director field in a uniform (left) and a bipolar (right) tactoid.

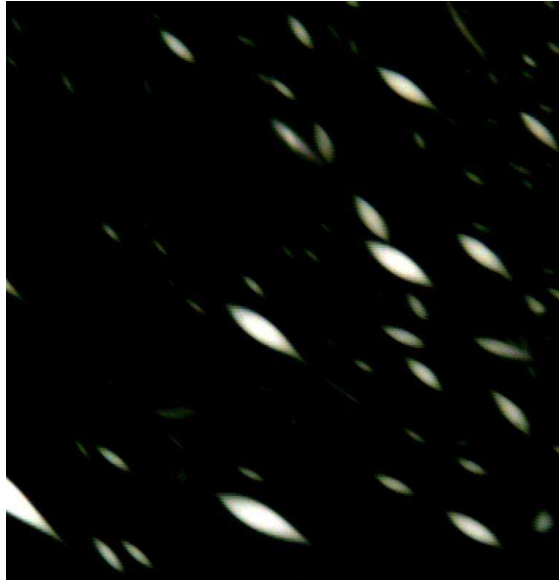


FIG. 2: Polarization microscopic image with crossed polarizers, showing a collection of tactoids in aqueous dispersion of bile-salt stabilized single-wall carbon nanotubes. The image size is $97 \mu\text{m} \times 100 \mu\text{m}$.

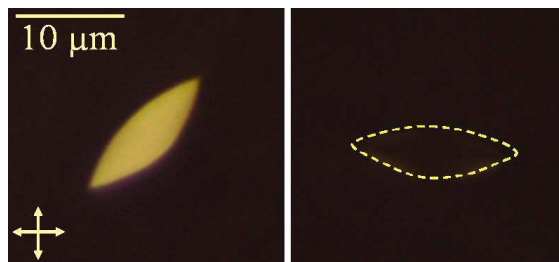


FIG. 3: (Color online) Observation by polarization microscopy of a tactoid with the main body axis at 45 degrees relative to the polarizers (left) and along one of the polarizers (right). Indicated by the dashed line is the outline of the tactoid if oriented at 45 degrees with respect to the polarizers.

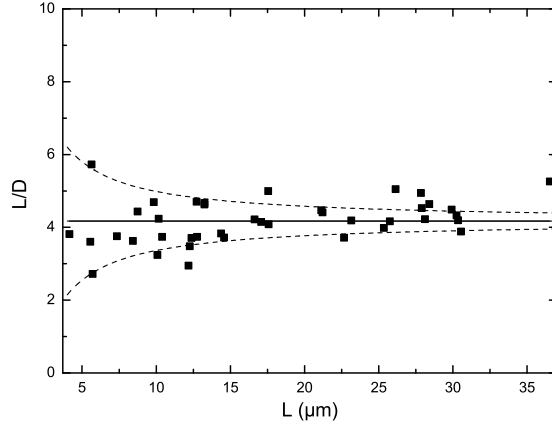


FIG. 4: Aspect ratio of the tactoids versus their length in microns. Full squares: experimental data points. Drawn line: average value deduced from the experiments. Dashed lines: predicted standard deviation presuming that the surface tension is equal to 0.5 nN/m.

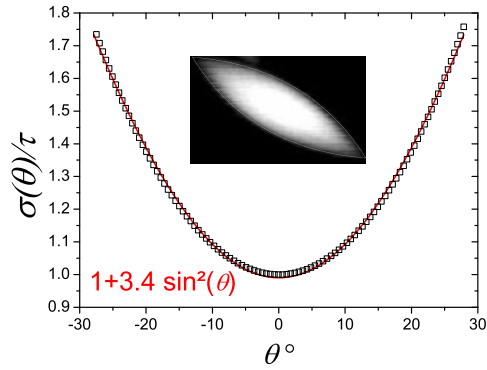


FIG. 5: (Color online) Inverse Wulff construction applied to a tactoid providing the form of surface tension anisotropy. The experimental data points (indicated by the squares) are well fitted with a Rapini-Papoular anchoring expression (drawn line).