



Ultrafast Light-Induced Spin-State Trapping Photophysics Investigated in Fe(phen) 2 (NCS) 2 Spin- Crossover Crystal

Roman Bertoni, Marco Cammarata, Maciej Lorenc, Samir F. Matar,
Jean-François Létard, Henrik T. Lemke, Eric Collet

► To cite this version:

Roman Bertoni, Marco Cammarata, Maciej Lorenc, Samir F. Matar, Jean-François Létard, et al..
Ultrafast Light-Induced Spin-State Trapping Photophysics Investigated in Fe(phen) 2 (NCS) 2 Spin-
Crossover Crystal. Accounts of Chemical Research, American Chemical Society, 2015, 48 (3), pp.774-
781. 10.1021/ar500444d . hal-01118869

HAL Id: hal-01118869

<https://hal.archives-ouvertes.fr/hal-01118869>

Submitted on 20 Feb 2015

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Ultrafast Light-Induced Spin-State Trapping

Photophysics Investigated in Fe(phen)₂(NCS)₂ Spin-Crossover Crystal

*Roman Bertoni,^{†1} Marco Cammarata,¹ Maciej Lorenc¹, Samir F. Matar,² Jean-François Létard,² Henrik T. Lemke,³ Eric Collet^{*1}*

¹Institut de Physique de Rennes, UMR CNRS 6251 Université Rennes 1, 35042 Rennes cedex, France.


²CNRS, Université de Bordeaux, ICMCB, 87 avenue du Dr. A. Schweitzer, Pessac, 33608 France.

³LCLS, SLAC National Laboratory, Menlo Park, 94025, CA, USA.

^{*}Author to whom correspondence should be addressed. eric.collet@univ-rennes1.fr

[†]currently at : Fritz Haber Institute of the Max Planck Society, 14195 Berlin, Germany.

Few photo-active molecules undergo a complete transformation of physical properties (magnetism, optical absorption ...) when irradiated with light. Such phenomena can happen on the time scale of fundamental atomic motions leading to an entirely new state within less than one picosecond following light absorption. Spin crossover (SCO) molecules are prototype systems having the ability to switch between low spin (LS) and high spin (HS) molecular states both at thermal equilibrium or after light irradiation. In the case of a FeII (3d6) complexes in nearly octahedral ligand field, the two possible electronic distributions among the 3d split orbitals are $S = 0$ for the LS diamagnetic state and $S = 2$ for the HS paramagnetic state. In crystals, such photo-excited states can be long-lived at low temperature, as it is the case for the photoinduced HS state of the $[\text{Fe}(\text{phen})_2(\text{NCS})_2]$ SCO compound investigated here. We first show how such bistability between the diamagnetic and paramagnetic states can be characterized at thermal equilibrium or after light irradiation at low temperature. Complementary techniques provide invaluable insights into relationship between changes of electronic states and structural reorganization. But the development of such light-active materials requires the understanding of the basic mechanism following light excitation of molecules, responsible for trapping them into new electronic and structural states. We therefore discuss how we can observe a photomagnetic molecule during switching and catch on the fly electronic and structural molecular changes with ultra-fast x-ray and optical absorption spectroscopies. In addition, there is a long debate regarding the mechanism behind the efficiency of such a light-induced process. Recent theoretical works suggest that such speed and efficiency are possible thanks to the instantaneous coupling with the phonons of the final state. We discuss here the first experimental proof of that statement as we observe the instantaneous activation of one key phonon mode precluding any recurrence towards the initial state. Our studies show that the structural molecular reorganization trapping the photoinduced electronic state occurs in two sequential steps: the molecule elongates first (within 170 femtosecond) and bends afterwards. This dynamics is caught via the coherent vibrational energy transfer of the two main structural modes. We discuss the transformation pathway connecting the initial photo-excited state to the final state, which involves several key reaction coordinates. These results shows the need for replacing the classical single coordinate picture employed so far by a more complex multi-dimensional energy surface.

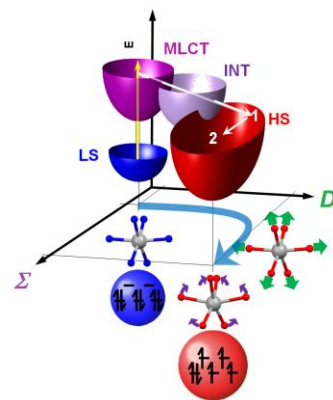

I. Introduction

The response of matter to light on ultrafast (i.e., picosecond and femtosecond) time scales represents a relatively new area in Materials Science. Electronic and/or structural changes are at the origin of light-activated functions in molecular [1], biophysical [2] or solid [3] materials. The past two decades saw remarkable technological advances in ultrafast laser systems and ultrafast science, making it possible to watch the dynamics and to understand the mechanisms of light-induced transformations.

Spin CrossOver (SCO) molecules [4] are of particular interest because of their ability to switch between low spin (LS) and high spin (HS) molecular states not only under light excitation, but also at thermal equilibrium. In the case of a Fe^{II} ($3d^6$) complexes, such as $[\text{Fe}(\text{phen})_2(\text{NCS})_2]$ investigated here, two possible electronic distributions among the 3d split orbitals in a nearly octahedral ligand field correspond to the LS ($S=0$) or HS ($S=2$) states (Fig. 1). The switching from LS to HS after light irradiation is referred to as the Light Induced Excited-Spin State Trapping phenomenon (LIESST). It was thoroughly investigated in crystals; under continuous light irradiation at low temperature where a complete photo-conversion can be easily reached [5,6,7,8], or after pulsed irradiation at high temperature [9,10,11]. Light-induced SCO dynamics was also studied for molecules in solution, by the groups of McCusker, McGarvey, Hendrickson, Chergui, Mathies, Schoenlein. The use of ultrafast optical, X-ray or Raman spectroscopies gave a comprehensive dynamical description of the changes of electronic states and the structural reorganization [12-25]. Our studies of LIESST in Fe^{III} and Fe^{II} SCO crystals [26-31], as well as reverse-LIESST [32], indicated a photoswitching dynamics at the molecular level in nano- or micro-crystals [11] similar to solution. After introducing how to investigate LIESST effect, we

discuss its dynamics, including the coherent structural response recently revealed in $[\text{Fe}(\text{phen})_2(\text{NCS})_2]$ [33].

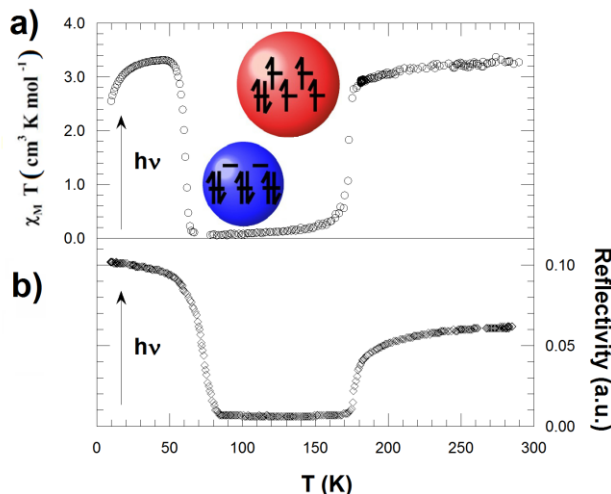


Figure 1. a) Thermal evolution of the $\chi_m T$ product of $[\text{Fe}(\text{phen})_2(\text{NCS})_2]$ showing a change of spin state around 180 K. The value above 180 K ($\chi_m T \approx 3.3 \text{ cm}^3 \cdot \text{K} \cdot \text{mol}^{-1}$) is typical of paramagnetic Fe^{II} HS state, whereas the very small value below 180 K is typical of LS diamagnetic state. Below 60 K, the HS state is reached by *cw* light excitation of the LS state at 650 nm. b) Evolution of the diffuse reflectivity signal recorded at 650 nm and generating LIESST below 60 K.

II Thermal and photoinduced spin-state conversion in $\text{Fe}(\text{phen})_2(\text{NCS})_2$

$[\text{Fe}(\text{phen})_2(\text{NCS})_2]$ (phen=1,10-phenanthroline) is an archetypal bistable Fe^{II} SCO crystal [6,33-37]. The diamagnetic LS state of electronic structure $t_{2g}^6 e_g^0 L^0$ (where L corresponds to the LUMO of the ligand) is the ground state. It is of lower entropy than the paramagnetic HS ($t_{2g}^4 e_g^2 L^0$) state observed at high temperature. This change of magnetic state is well characterized by SQUID experiments (Fig 1a). The value of the $\chi_M T$ product (χ_M being the molar magnetic susceptibility and T the temperature) approaching $3.3 \text{ cm}^3 \cdot \text{K} \cdot \text{mol}^{-1}$ is characteristic of the

paramagnetic HS ($S=2$) state above 180 K, while below this temperature it corresponds to the diamagnetic LS ($S=0$) state. Below 60 K, cw light-excitation at 650 nm completely transforms the system to the HS state [38]. The change of electronic state also modifies optical properties (Fig 1b). At 650 nm, the higher absorption (lower reflectivity) in the LS state is due to the Metal to Ligand Charge Transfer (MLCT) band of the LS state. The electronic redistribution between the LS and HS states is accompanied by an increase of absorption below 620 nm and above 720 nm [33].

Density Functional Theory [39,40] calculations (Fig. 2) performed with Gaussian 09 package [41] show that in the LS state the highest occupied molecular orbital (HOMO) and lowest unoccupied molecular orbitals (LUMO) on both sides of the energy gap are respectively of t_{2g} - and e_g -like character. The t_{2g} - e_g energy gap is around 1.8 eV in LS state and 1.6 eV (775 nm) in the HS state. The LUMO lying ≈ 1.9 eV above the t_{2g} -like LS HOMO has electron density on the ligand phenanthroline groups only. The LS excitation at 650 nm corresponds then to a MLCT (green arrow in Fig. 2).

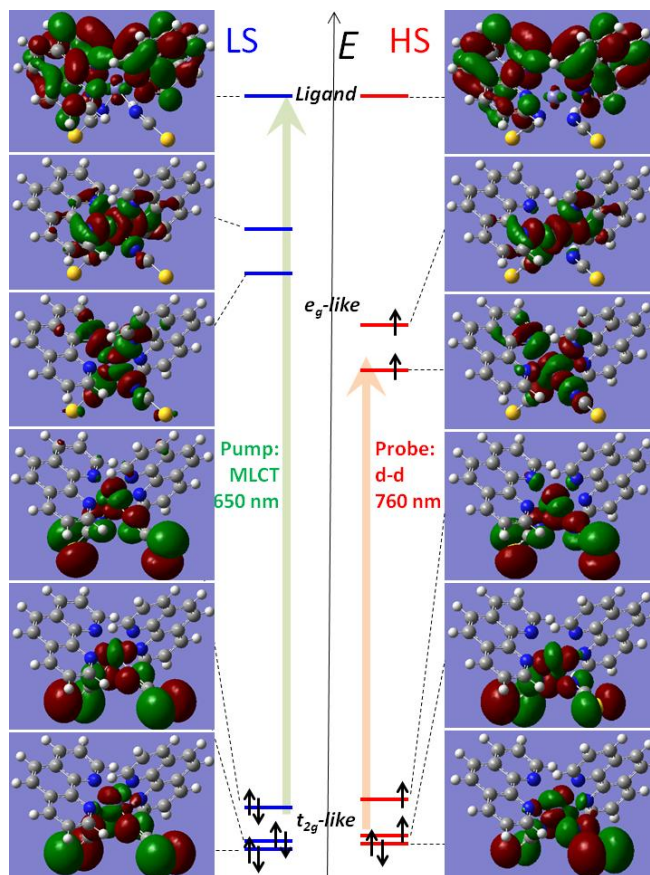


Figure 2. Schematic energy diagram and molecular orbitals obtained from DFT calculations. The MLCT process in the LS state with the pump at 650 nm promotes electrons from t_{2g} -like to ligand orbitals (L), whereas the probe at 760 nm corresponds to HS t_{2g} -like to e_g -like d-d transition. The Fe atom is in the center, N atoms are blue, C atoms are grey, S atoms are yellow, H atoms are white.

X-ray diffraction reveal important changes of the molecular structure between LS and HS states. The molecule and the Fe atom are located on a 2-fold symmetry axis (Fig 3) of the *Pbcn* (orthorhombic) space group [6,33]. The Fe atom is bonded to N atoms of the two NCS groups and four N atoms of the two phenanthroline groups. The main structural deformations shown in Fig. 3 around the FeN_6 octahedron are:

- the average Fe-N distance: $\langle Fe-N \rangle = \frac{1}{6} \sum_{i=1}^6 Fe-N_i$ changes from $\langle Fe-N \rangle_{LS} \approx 1.97 \text{ \AA}$ to $\langle Fe-N \rangle_{HS} \approx 2.16 \text{ \AA}$.

- the distortion Σ of the FeN_6 octahedron, determined by the sum of the deviation from 90° of the 12 N-Fe-N cis ϕ angles in the coordination sphere: $\Sigma = \sum_{i=1}^{12} |90 - \phi_i|$ changes from $\Sigma_{LS} \approx 35^\circ$ to $\Sigma_{HS} \approx 65^\circ$.

These structural parameters (Fig 3b) are related to the spin state, and the photoinduced state generated at low temperature is very similar to the HS one [4,13,15,20,21,22,24]. The $\langle Fe-N \rangle$ elongation in the HS state is associated with the electronic population of less bonding e_g orbitals. The increase of Σ , due to N-Fe-N bending, was underlined as essential for stabilizing the photoinduced HS state at higher T(LIESST) [6]. Consequently, the equilibrium position in the HS potential is moved away from that of LS [8]. This electronic conversion accompanied by deformations of the FeN_6 octahedron, result in important changes of the XANES (x-ray absorption near edge structure) spectrum around the Fe K-edge (Fig. 3c).

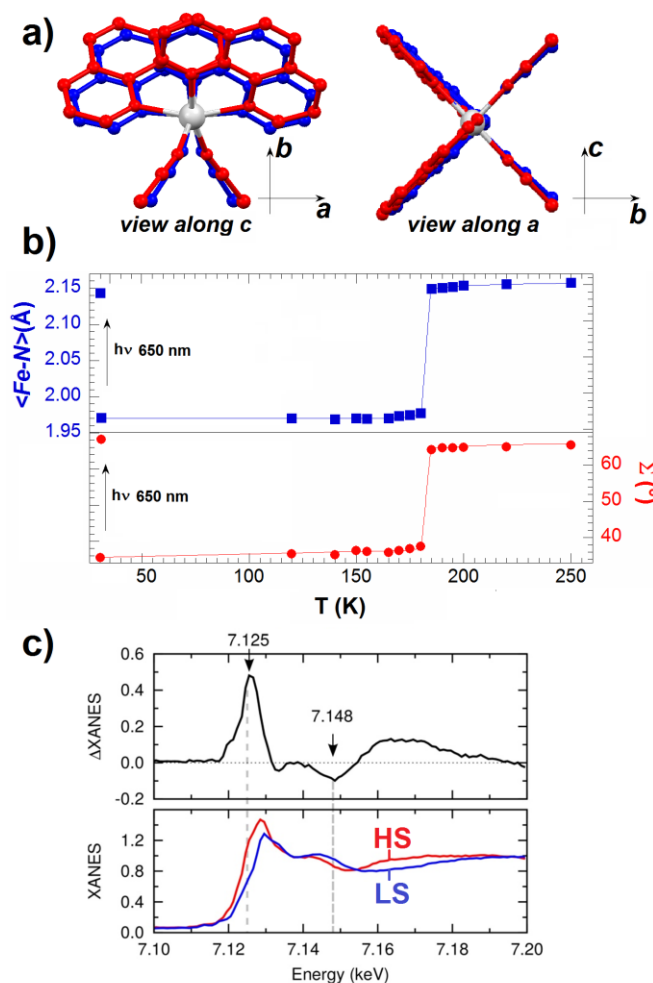


Figure 3. (a) LS (140 K, blue) and HS (200 K, red) structures of [Fe(phen)₂(NCS)₂]. (b) Temperature dependence of *Fe-N* bonds and Σ parameter, showing the first-order phase transition around 180 K between LS and HS states. The parameters obtained after cw irradiation at 650 nm are identical to those of the HS state at high temperature. (c) XANES spectra and variation Δ XANES measured between the HS (200K) and LS (140K) states. Adapted with permission from ref. 33. Copyright (2014) American Physical Society.

Magnetic susceptibility directly probes the HS fraction of the crystal. Unfortunately this technique is too slow for investigating the photo-switching dynamics on the timescale of elementary electronic, atomic or molecular motions, typically falling in the sub-picosecond range. This limitation is overcome by ultrafast optical and X-ray spectroscopies that can now

routinely achieve 100 fs time resolution. Here we take advantage of the optical and x-ray fingerprints of electronic and structural changes to investigate the photo-switching dynamics from LS to HS states.

III Ultrafast photophysics in $\text{Fe(phen)}_2(\text{NCS})_2$ crystals

III.1 Femtosecond optical and x-ray absorption spectroscopy studies

We recently reported on the ultrafast spin state photoswitching dynamics studies in $[\text{Fe(phen)}_2(\text{NCS})_2]$ performed with two complementary pump-probe techniques: XANES, and optical spectroscopy. A ≈ 50 fs pump laser pulse (650 nm) switches LS state to HS via a metal-to-ligand charge-transfer process (MLCT). The changes in XANES are recorded with ≈ 30 fs x-ray pulses at the XPP station of the LCLS X-FEL, while changes in optical reflectivity (OR) and transmission (OT) in visible-infrared range are recorded with ≈ 50 fs pulse. For both experiments the time resolution was ≈ 110 fs and more details can be found in ref 33. The measurements presented hereafter were performed at 140K in the pure LS state. For optical measurements we used single crystals of losange shape (Fig. 4) with *a* and *b* crystalline axis as respectively smallest and longest diagonals. The 2-fold symmetry axis of the molecule is oriented along the *b* axis. The *c* axis corresponds to the crystal thickness. The pump pulse was polarized along the *b* axis, whereas both polarizations were used for the probe to measure reflectivity. XANES measurements were done on powder films for maximizing x-ray penetration.

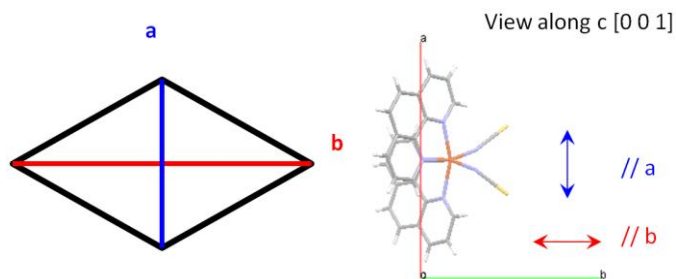


Figure 4. Schematic representation of the single crystals of $[\text{Fe}(\text{phen})_2(\text{NCS})_2]$ with the orientation of the crystal axes. The two-fold molecular axis is along the b axis.

The change of molecular structure is monitored by femtosecond XANES around the K edge of iron, which is very sensitive to the change of Fe-N bond length (Fig. 3c). Fig 5 shows the time evolution of x-ray absorption at 7125 eV (increase) and 7148 eV (decrease) after excitation, which are the clear fingerprints of the formation of the HS molecular structure. The resulting dynamics can be fit by an exponential rise convoluted with a Gaussian Instrument Response Function [33]. The extracted time constant of $\tau_{\langle \text{Fe-N} \rangle} = 170(20)\text{fs}$ for the $\langle \text{Fe-N} \rangle$ elongation is similar to the timescales reported for other SCO molecules in solution [20,22].

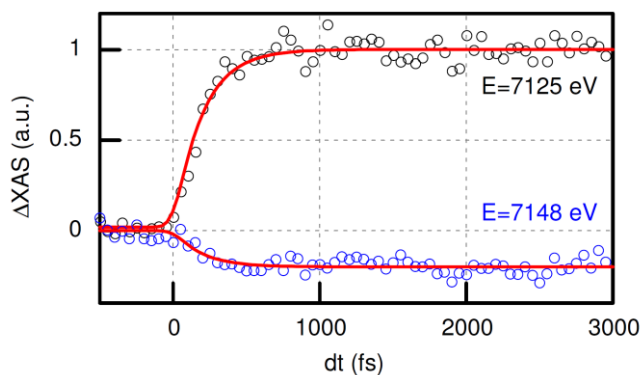


Figure 5. Time resolved change of X-ray absorption at 7125eV and 7148eV. Red lines are fit to single exponential rise with time constant $\tau_{\langle \text{Fe-N} \rangle} = 170(20)\text{fs}$. Adapted with permission from ref. 33. Copyright (2014) American Physical Society.

Fig. 6 shows optical changes observed on single-crystals, when the probe polarization is parallel to the **b** axis. At the energy of 1.6 eV (760nm) both transmission and reflectivity show a decreasing signal related to the absorption of the HS state, which corresponds to d-d transitions (see part III.2). The LS state is optically silent at 760nm since the lowest t_{2g} -like HOMO and e_g -like LUMO is at higher energy (Fig. 2). The absorption of the HS state at 1.6 eV results therefore from the d-d gap narrowing [33]. Data at 760 nm show that this change occurs within $\tau_{\text{gap}} = 140$ (20) fs. Since this ligand field weakening is related to the elongation of the $\langle\text{Fe-N}\rangle$ bond length, τ_{gap} correlates well with $\tau_{\langle\text{Fe-N}\rangle} = 170$ (20) fs measured by XANES. Our results demonstrate that by probing a transition sensitive to the ligand field, by means of optical spectroscopy, it is possible to gain some insight into structural dynamics of the Fe-N_6 octahedron. The electronic peak observed at 850 and 900nm, corresponds to the photoexcited singlet $^1\text{MLCT}$ state ($t_{2g}^5 e_g^0 L^1$). It decays within less than 50 fs and cannot be well resolved with 100 fs time resolution [33]. Other intermediate (INT) states can be involved in the inter-system crossing (ISC) and the $^1,^3\text{MLCT} \rightarrow ^3\text{T} \rightarrow \text{HS}$ sequence dominates [42].

The optical kinetic traces shown in Fig. 6 also exhibit oscillating components both in reflectivity and transmission geometries. They are the signatures of molecular vibrations accompanying the LIESST and similar oscillations were observed first in $\text{Fe}(\text{bpy})_3$ by Chergui *et al* [19]. The oscillating components shown in Fig. 7 were extracted from the fit of the data shown in Fig. 6 [33]. The time-dependent fast Fourier transform trace at 760 nm reveals a main mode at around 113cm^{-1} , which is only observed during the first picosecond. Other reflectivity traces reveal another oscillation around 85cm^{-1} , in-phase for all the probing wavelengths and observed both in transmission and reflectivity.

Different wavelengths are sensitive to different degrees of freedom. The response at 760 nm is – as discussed above – mostly sensitive to the Fe-N core expansion, while the signal at 900 nm is mostly sensitive to the bending of the molecules (This remarkable difference is rationalized by using time dependent DFT calculations as discussed below). The exponential fits of optical reflectivity at these wavelengths show significantly different time scales thus suggesting a non-simultaneous expansion and distortion of the molecule as depicted in Figure 7h where the two exponential time constants (from OR 760 nm and OR 900 nm) are used to reconstruct the

average evolution of the two structural parameters. To test this hypothesis even further we have modeled a simple coupled-oscillator whereby the initial elongation of the Fe-N core induces the octahedral distortion. This model discussed in detail in reference 33 can reproduce fairly well the oscillating part of the experimental data as shown in Fig. 7, panels b and c.

To further this investigation, we present in Fig. 8 new measurements at 760 nm with probe light polarized parallel or perpendicular to the crystal axis ***b***, while keeping all other experimental parameters identical. The data for the parallel configuration reproduces well the ones already published in ref 33 (Fig. 7), indicating the activation and damping of a mode around 113 cm^{-1} during the first ps. However, the data for the polarization perpendicular to ***b***, show a different behavior as the frequency of the observed mode is 85 cm^{-1} .

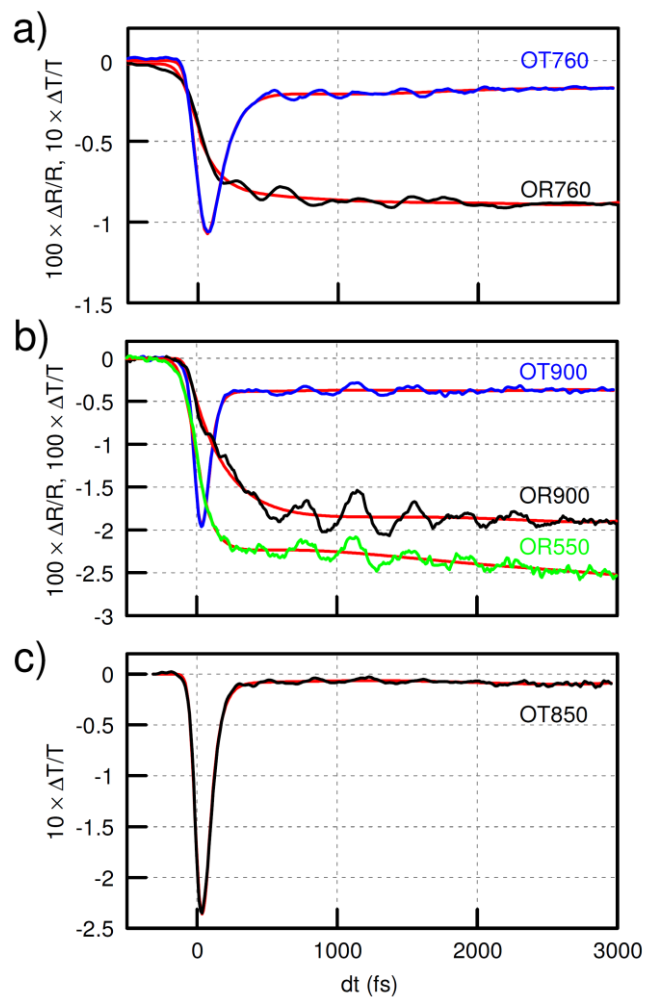


Figure 6. a) Time resolved traces of optical transmission (OT) and reflectivity (OR) at 760nm, b) 900 nm and 550 nm, c) and 850nm with probe polarization parallel to b axis. All traces were fitted (red lines) with a single exponential function accounting for the fast dynamic and a fifth order polynomial to take into account for slower processes such as vibrational cooling. Adapted with permission from ref. 33. Copyright (2014) American Physical Society.

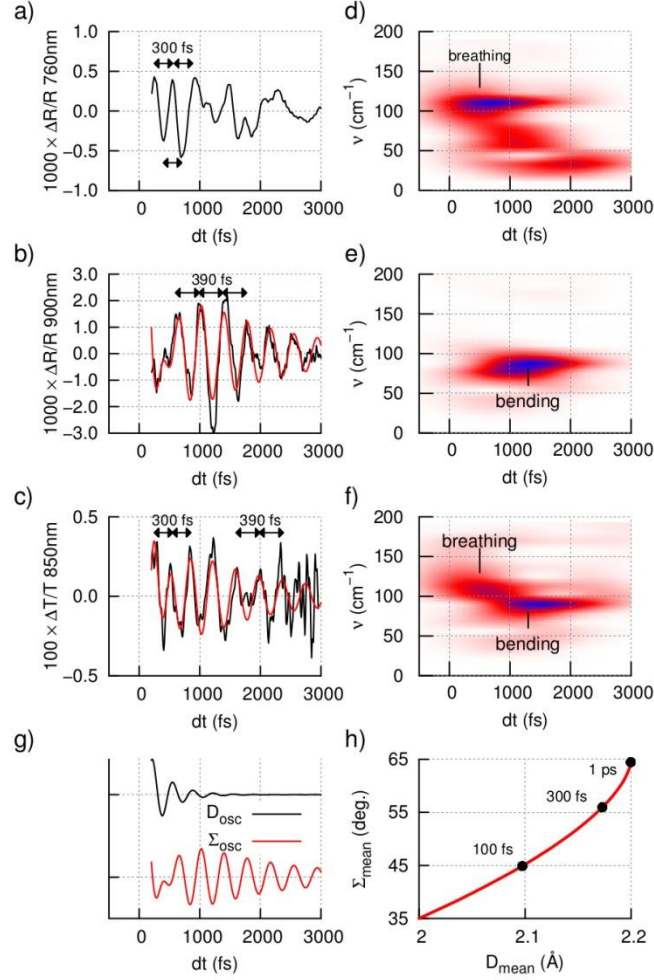


Figure7. (a-c), oscillating component of OR at 760 nm, OR at 900 nm and OT at 850 nm. (d-f), time dependent FFT of the experimental data, showing the activation of the breathing mode and the delayed activation of the bending mode. Combined fits of OR at 900 nm and OT at 850 nm (red line) by the coupled oscillator model, which show the contribution of the bending (Σ) mode (b) and the superposition of bending (Σ) and breathing (D) modes (c). The time course of the oscillating component D_{osc} (300 fs) and Σ_{osc} (390 fs) obtained by the fit in (b) and (c) are displayed in (g) and the average evolutions of D_{mean} and Σ_{mean} obtained by the fit in Fig. 3 are displayed in (h). Adapted with permission from ref. 33. Copyright (2014) American Physical Society.

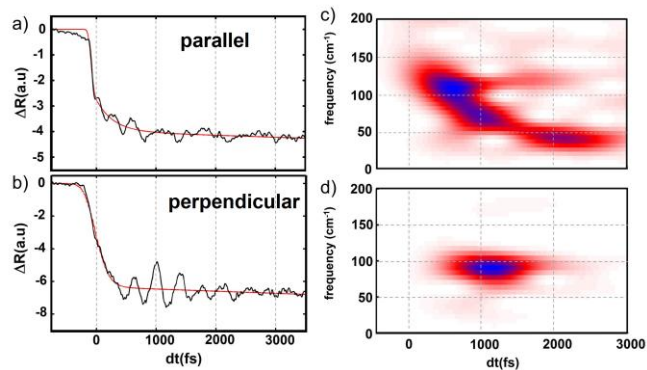


Figure 8. Time resolved change of reflectivity at 760nm (1.6eV) for probe polarization parallel (a) or perpendicular (b) to the molecular 2 fold symmetry axis. Red lines are fits obtain with single exponential rise plus a fifth order polynomial. c) & d) associated TD-FFT showing both breathing and bending depending on the polarization.

III.2 Discussion

Recent theoretical studies by van Veenendaal discuss the mechanism behind the extremely fast and efficient ISC during LIESST in terms of dephasing of the photoexcited state into the HS phonon states [43,44]. The change from LS to HS states, which strongly differ in both electronic configuration and molecular structure (metal-ligand distance), is mediated by the spin-orbit coupling. The ultrafast ISC is displacive as the $\langle \text{Fe-N} \rangle$ bond elongation drives the system into the HS potential. Its strong damping is associated with the efficient self-trapping of the photo-induced HS state, as schematically shown in figure 9a. Our results shown in Fig. 6 and 7 strongly support this mechanism. The 113 cm^{-1} mode is activated just after light excitation, as Fe-N elongates, and corresponds to the molecular breathing mode: a totally symmetric Fe-N stretching with respect to the 2-fold molecular axis [33,45,46]. This eigenvector of symmetry A in the C_2 point group of the complex is hereafter referred to as the breathing coordinate D . Fig. 6b and 6c

also revealed the activation of a second mode at 85 cm^{-1} , corresponding to the butterfly mode [33,45,46], which bends the ligand and the N-Fe-N angles without significantly changing Fe-N distances. We will refer to this mode as a bending coordinate Σ . Unlike the breathing mode, activated instantaneously, the bending mode with 390 fs period appears only after 500fs and has a maximal amplitude around 1200fs (Figures 7-8). Such delayed activation of other modes results from the fact that the HS potential is reached with excess energy. Then the non-equilibrium vibrational energy relaxation in the product HS state activates other modes. Fig. 7 & 8 show a spectral weight transfer from breathing to bending. The structural stabilization occurs over two steps with a sequential activation of breathing then bending via coherent energy transfer.

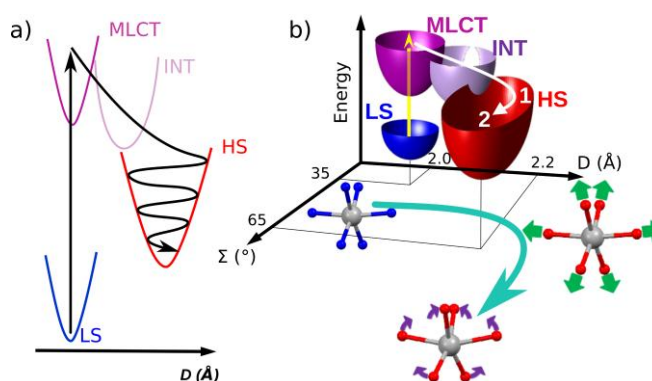


Figure 9. (a) Schematic representation of the elongation and damping of the breathing mode along the D coordinate. (b) Classical trajectory in the (D, Σ) space. Molecules in the LS (blue) potential reach $^1\text{MLCT}$ state by light excitation. Fast ISC, through possible INT states, drives D elongation during step 1 with the generation and damping of breathing phonon, followed by activation of additional bending phonons such as distortion Σ , during step 2. The sequence is sketched at the bottom. Adapted with permission from ref. 33. Copyright (2014) American Physical Society.

For understanding why the observation of specific vibrational modes depends on the probe energy and/or polarization, an accurate description of excited states is needed. The time dependent DFT (TD-DFT) approach has proved an excellent tool used in quantum chemistry [47]. The results obtained within TD-DFT lead to the so-called ‘natural transition orbitals’ NTO through an account for hole–particle pairs which are then used to interpret the excited states corresponding to the absorption of the probe light. TD-DFT as implemented in the Gaussian 09 package [41] was applied for obtaining the NTO of HS [Fe(phen)₂(NCS)₂] starting from geometry optimized molecule with UB3LYP/6-31g(*d,p*) functional-basis set. Fig. 10a shows the NTO corresponding to the hole–particle transition state around 760 nm for polarization parallel to the *b* axis. The strong weight of the particle orbital on the Fe-N bonds explains its sensitivity to the breathing mode, for which the Fe-N elongation is the main characteristic. Fig. 10b shows the transition state around 760 nm for polarization perpendicular to the *b* axis, Fig. 10c and 10d shows the transition state around 550 and 900 nm respectively for polarization parallel to the *b* axis. For these last three cases, the sensitivity to the bending mode observed in Fig. 6b is explained by the weight of the particle orbital mainly located on the ligand (not on the Fe-N bonds). This selectivity in terms of light polarization, which can be used in the solid state, opens interesting opportunities for disentangling complex transformation dynamics where different degrees of freedom are involved.

III.3 Curved trajectory on the potential energy surface

We can now summarize all these results in a global picture for describing the photophysics of LIESST. An ultrafast ISC from the MLCT state ($\tau < 50$ fs) occurs and the less bonding HS potential is rapidly reached, defining a new equilibrium Fe-N bond length. Intermediate states serving as mediators appear in the process but are difficult to identify here.

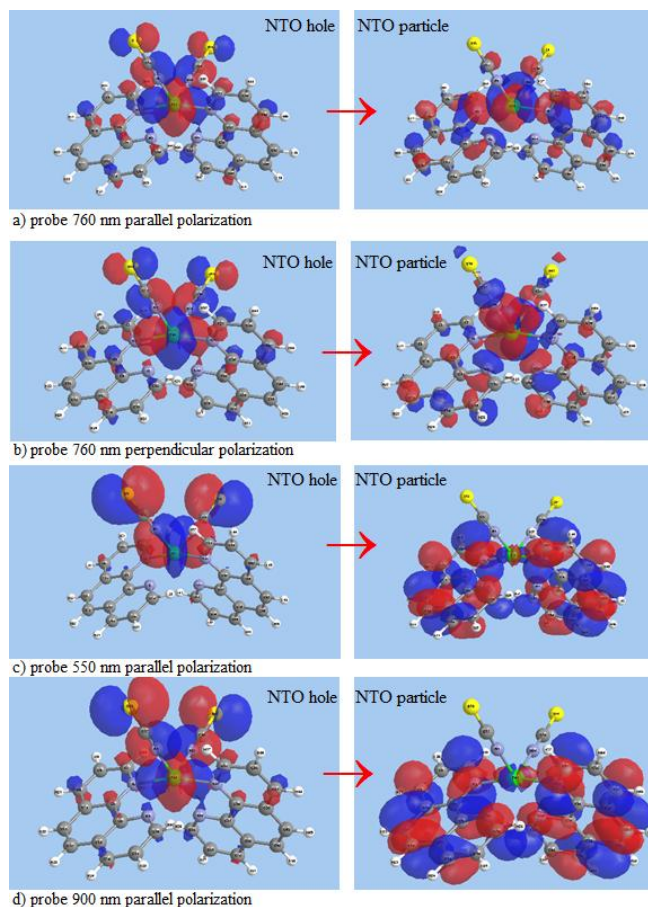


Figure 10. NTO of hole and particle for different light polarization indicated in figure, with respect to the 2-fold molecular symmetry axis, around 760 nm calculated at 1.668 eV (a), around 760 nm and calculated at 1.667 eV (b), around 550 nm and calculated at 2.2 eV (c) and around 900 nm and calculated at 1.32 eV (d).

For reaching the minimum of the HS potential this bond elongation, corresponding to the reaction coordinate D , occurs within ≈ 170 (20) fs. But as the HS potential is reached with excess kinetic (vibrational) energy, the molecule oscillates along the D coordinate as schematically represented in Fig. 9a. The single Fe-N elongation is not enough for stabilizing the HS state, because the minimum of the HS potential corresponds to a distorted structure with different value of Σ . The delayed activation of the bending mode indicates a two-step process

where the coherent dynamics along Σ occurs well after the initial elongation of D . The transformation from the initially excited LS state to the trapped HS state can be described on a potential energy surface (PES) where D and Σ are the two main reaction coordinates. Fig. 9b is a cartoon of such a PES of $[\text{Fe}(\text{phen})_2(\text{NCS})_2]$, where the LS potential has minimum at ($D_{LS}=1.97$ Å, $\Sigma_{LS}=35^\circ$) and the one of the HS state at ($D_{HS}=2.16$ Å, $\Sigma_{HS}=65^\circ$) (Figure 3b). The analysis of XANES, OT and OR data [33] gave an average elongation $D_{mean}(t)$ with a ≈ 170 fs time constant, whereas the average torsion $\Sigma_{mean}(t)$ occurs with a 250 fs time constant (Fig. 7h). The system therefore follows a curved trajectory in the (D, Σ) coordinate space of the PES, with a sequential activation of the key modes. This process involves a very fast energy transfer: the breathing mode is damped on a timescale of 160 fs (Fig. 7g). This strong damping hinders recurrence to the initial state and explains why the structural trapping is so efficient.

IV Conclusion

This comprehensive study allows drawing an elaborate scenario explaining the speed and efficiency of LIESST, underlying the importance of structural dynamics and energy dissipations. The curved trajectory on PES, involving coherent structural dynamics, reveals the basic dynamical transformation mechanism associated with a deterministic process.

In order to understand the physical processes allowing functionalization with light, probes sensitive to specific degrees of freedom are mandatory. Ultrafast techniques allow now to follow and disentangle the dynamical changes of electronic and structural degrees of freedom. Such multi-probe ultrafast studies will become routine in the field of light-functionalized materials and

the present results pave the way for investigating more complex phenomenon. As it is now possible to reach a time resolution better than elementary molecular motions, processes driven by coherent structural dynamics can be deeply investigated. It will represent an important topic in light-activated functions, as this mechanism allows to reach the shortest time-scale for the structural trapping, corresponding to the elementary molecular deformations.

Funding Sources

This work was supported by the Institut Universitaire de France, Rennes Métropole, Région Bretagne (CREATE 4146), ANR (ANR-13-BS04-0002), CNRS (PEPS SASLELX) and Europe (FEDER). Portions of this research were carried out at the Linac Coherent Light Source (LCLS) at SLAC National Accelerator Laboratory. LCLS is an Office of Science User Facility operated for the U.S. Department of Energy Office of Science by Stanford University.

REFERENCES

- [1] Zewail, A. H. Femtochemistry: Atomic-Scale Dynamics of the Chemical Bond Using Ultrafast Lasers. *Angew. Chem. Int. Ed.* 2000, 112, 2688.
- [2] Polli, D.; Altoè, P.; Weingart, O.; Spillane, K. M.; Manzoni, C.; Brida, D.; Tomasello, G.; Orlandi, G.; Kukura, P.; Mathies, R. A.; Garavelli, M.; Cerullo, G. Conical intersection dynamics of the primary photoisomerization event in vision. *Nature*. 2010, 467, 440–443.
- [3] Nasu, K. Photoinduced Phase transitions . Ed. World Scientist. Singapore, 2004.
- [4] Ed. M. A. Halcrow ,Spin-Crossover Materials: Properties and Applications, John Wiley & Sons, 2013.
- [5] Decurtins, S.; Güthlich, P.; Köhler, C. P.; Spiering, H.; Hauser, A. Light-induced excited spin state trapping in a transition-metal complex: The hexa-1-propyltetrazole-iron (II) tetrafluoroborate spin-crossover system. *Chem. Phys. Lett.* 1984, 105, 1.
- [6] Marchivie, M.; Guionneau, P.; Howard, J. A. K.; Chastanet, G.; Létard, J. F.; Goeta, A. E.; Chasseau, D Structural Characterization of a Photoinduced Molecular Switch. *J. Am. Chem. Soc.* 2002, 124, 194-195.
- [7] Collet, E.; Watanabe, H.; Bréfuel, N.; Palatinus, L.; Roudaut, F.; Toupet, L.; Tanaka, K.; Tuchagues, J. P.; Fertey, P.; Ravy, S.; Toudic, B.; Cailleau, H. Aperiodic Spin State Ordering of Bistable Molecules and Its Photoinduced Erasing. *Phys. Rev. Lett.* 2012, 109, 257206.
- [8] Buron-Le Cointe, M.; Hébert, J.; Baldé, C.; Moisan, N.; Toupet, L.; Guionneau, P.; Létard, J. F.; Freysz, E.; Cailleau, H.; Collet, E. Intermolecular control of thermoswitching and photoswitching phenomena in two spin-crossover polymorphs. *Phys. Rev. B.* 2012, 85, 064114.

- [9] Cobo, S.; Ostrovskii, D.; Bonhommeau, S.; Vendier, L.; Molnar, G.; Salmon, L.; Tanaka, K.; Bousseksou, A. Single-Laser-Shot-Induced Complete Bidirectional Spin Transition at Room Temperature in Single Crystals of $(\text{FeII}(\text{pyrazine})(\text{Pt}(\text{CN})_4))$. *J. Am. Chem. Soc.* 2008, 130, 9019.
- [10] Lorenc, M.; Hébert, J.; Moisan, N.; Trzop, E.; Servol, M.; Buron-Le Cointe, M.; Cailleau, H.; Boillot, M. L.; Pontecorvo, E.; Wulff, M.; Koshihara, S.; Collet, E. Successive Dynamical Steps of Photoinduced Switching of a Molecular Fe(III) Spin-Crossover Material by Time-Resolved X-Ray Diffraction. *Phys. Rev. Lett.* 2009, 103, 028301.
- [11] Bertoni, R.; Lorenc, M.; Tissot, A.; Boillot, M. L.; Collet, E. Femtosecond photoswitching dynamics and microsecond thermal conversion driven by laser heating in FeIII spin-crossover solids. *Coord. Chem. Rev.* 2015, 282-283, 66-76.
- [12] Smeigh, A. L.; Creelman, M.; Mathies, R. A.; McCusker, J. K. Femtosecond Time-Resolved Optical and Raman Spectroscopy of Photoinduced Spin Crossover: Temporal Resolution of Low-to-High Spin Optical Switching. *J. Am. Chem. Soc.* 2008, 130, 14105.
- [13] Cannizzo, A.; Milne, C. J.; Consani, C.; Gawelda, W.; Bressler, C.; van Mourik, F.; Chergui, M. Light-induced spin crossover in Fe(II)-based complexes: The full photocycle unraveled by ultrafast optical and X-ray spectroscopies. *Coord. Chem. Rev.* 2010, 254, 2677.
- [14] McGarvey, J. J.; Lawthers, I.; Heremans, K.; Toftlund, H. Spin-state relaxation dynamics in iron(II) complexes: solvent on the activation and reaction and volumes for the $^1\text{A} \rightarrow ^5\text{T}$ interconversion. *J. Chem. Soc., Chem. Commun.* 1984, 1575.
- [15] Khalil, M.; Marcus, M. M.; Smeigh, A. L.; McCusker, J. K.; Chong, H. H. W.; Schoenlein, R. W. Picosecond X-ray Absorption Spectroscopy of a Photoinduced Iron(II) Spin Crossover Reaction in Solution, *J. Phys. Chem. A.* 2006, 110, 38.
- [16] Wolf, M. M. N.; Groß, R.; Schumann, C.; Wolny, J. A.; Schünemann, V.; Døssing, A.; Paulsen, H.; McGarvey, J. J.; Diller, R. Sub-picosecond time resolved infrared spectroscopy of high-spin state formation in Fe(II) spin crossover complexes. *Phys. Chem. Chem. Phys.* 2008, 10, 4264.
- [17] Gawelda, W.; Cannizzo, A.; Pham, V. T.; van Mourik, F.; Bressler, C.; Chergui, M. Ultrafast Nonadiabatic Dynamics of $[\text{FeII}(\text{bpy})_3]^{2+}$ in Solution. *J. Am. Chem. Soc.* 2007, 129, 8199.
- [18] Brady, C.; Toftlund, H.; McGarvey, J. J.; McCusker, J. K.; Hendrickson, D. N. in: P. Gülich, H.A. Goodwin (Eds.), *Spin-crossover in Transition Metal Compounds*, vol. III, Springer, Berlin, 2004, p. 1, Top. Curr. Chem., 235.
- [19] Consani, C.; Prémont-Schwarz, M.; Elnahas, A.; Bressler, C.; van Mourik, F.; Cannizzo, A.; Chergui, M. Vibrational Coherences and Relaxation in the High-Spin State of Aqueous $[\text{Fe}^{\text{II}}(\text{bpy})_3]^{2+}$. *Angew. Chem.Int. Ed.* 2009, 48, 7184.
- [20] Huse, N.; Cho, H.; Hong, K.; Jamula, L.; de Groot, F. M. F.; Kim, T. K.; McCusker, J. K.; Schoenlein, R. W. Femtosecond Soft X-ray Spectroscopy of Solvated Transition-Metal Complexes: Deciphering the Interplay of Electronic and Structural Dynamics. *J. Phys. Chem. Lett.* 2011, 2, 880.
- [21] Lemke, H. T.; Bressler, C.; Chen, L. X.; Fritz, D. M.; Gaffney, K. J.; Galler, A.; Gawelda, W.; Haldrup, K.; Hartsock, R. W.; Ihee, H.; Kim, J.; Kim, K. H.; Lee, J. H.; Nielsen, M. M.; Stickrath, A. B.; Zhang, W.; Zhu, D.; Cammarata, M. Femtosecond X-ray Absorption Spectroscopy at a Hard X-ray Free Electron Laser: Application to Spin Crossover Dynamics. *J. Phys. Chem. A.* 2013, 117, 735.
- [22] Bressler, C.; Milne, C.; Pham, V. T.; El Nahhas, A.; van der Veen, R. M.; Gawelda, W.; Johnson, S.; Beaud, P.; Grolimund, D.; Kaiser, M.; Borca, C.; Ingold, G.; Abela, R.; Chergui, M. Femtosecond XANES Study of the Light-Induced Spin Crossover Dynamics in an Iron(II) Complex. *Science.* 2009, 323, 489.
- [23] Juban, E. A.; Smeigh, A. L.; Monat, J. E.; McCusker, J. K. Ultrafast dynamics of ligand-field excited states. *Coord. Chem. Rev.* 2006, 250, 1783.
- [24] Huse, N.; Kim, T. K.; Jamula, L.; McCusker, J. K.; de Groot, F. M. F.; Schoenlein, R. W. Photo-Induced Spin-State Conversion in Solvated Transition Metal Complexes Probed via Time-Resolved Soft X-ray Spectroscopy. *J. Am. Chem. Soc.* 2010, 132, 6809.

- [25] Chergui, M. in: M. A. Halcrow (Eds.), *Spin-crossover Materials*, Wiley, West Sussex, 2013, 405-489.
- [26] Bertoni, R.; Lorenc, M.; Tissot, A.; Servol, M.; Boillot, M. L.; Collet, E. Femtosecond Spin-State Photoswitching of Molecular Nanocrystals Evidenced by Optical Spectroscopy. *Angew. Chem. Int. Ed.* 2012, 51, 7485.
- [27] Lorenc, M.; Balde, C.; Kaszub, W.; Tissot, A.; Moisan, N.; Servol, M.; Buron-Le Cointe, M.; Cailleau, H.; Chasle, P.; Czarnecki, P.; Boillot, M. L.; Collet, E. Cascading photoinduced, elastic, and thermal switching of spin states triggered by a femtosecond laser pulse in an Fe(III) molecular crystal. *Phys. Rev. B.* 2012, 85, 054302.
- [28] Collet, E.; Lorenc, M.; Cammarata, M.; Guérin, L.; Servol, M.; Tissot, A.; Boillot, M. L.; Cailleau, H.; Buron, M. L. 100 Picosecond Diffraction Catches Structural Transients of Laser-Pulse Triggered Switching in a Spin-Crossover Crystal. *Chem. Eur. J.* 2012, 18, 2051.
- [29] Collet, E.; Moisan, N.; Baldé, C.; Bertoni, R.; Trzop, E.; Laulhé, C.; Lorenc, M.; Servol, M.; Cailleau, H.; Tissot, A.; Boillot, M. L.; Graber, T.; Henning, R.; Coppens, P.; Buron, M. Ultrafast spin-state photoswitching in a crystal and slower consecutive processes investigated by femtosecond optical spectroscopy and picosecond X-ray diffraction. *Phys. Chem. Chem. Phys.* 2012, 14, 6192.
- [30] Collet, E.; Boillot, M. L.; Hebert, J.; Moisan, N.; Servol, M.; Lorenc, M.; Toupet, L.; Buron-Le Cointe, M.; Tissot, A.; Sainton, J. Polymorphism in the spin-crossover ferric complexes $[(\text{TPA})\text{Fe}^{\text{III}}(\text{TCC})]\text{PF}_6$. *Acta Cryst. B.* 2009, 65, 474.
- [31] Marino, A.; Servol, M.; Bertoni, R.; Lorenc, M.; Mauriac, C.; Létard, J. F.; Collet, E. Femtosecond optical pump-probe reflectivity studies of spin-state photo-switching in the spin-crossover molecular crystals $[\text{Fe}(\text{PM-AzA})_2(\text{NCS})_2]$. *Polyhedron.* 2013, 66, 123.
- [32] Marino, A.; Chakraborty, P.; Servol, M.; Lorenc, M.; Collet, E.; Hauser, A. The Role of Ligand-Field States in the Ultrafast Photophysical Cycle of the Prototypical Iron(II) Spin-Crossover Compound $[\text{Fe}(\text{ptz})_6](\text{BF}_4)_2$. *Angew. Chem. Int. Ed.* 2014, 53, 3863-3867.
- [33] Cammarata, M.; Bertoni, R.; Lorenc, M.; Cailleau, H.; Di Matteo, S.; Mauriac, C.; Létard, J. F.; Matar, S.; Lemke, H.; Chollet, M.; Ravy, S.; Laulhé, C.; Collet, E. Sequential Activation of Molecular Breathing and Bending during Spin-Crossover Photoswitching Revealed by Femtosecond Optical and X-Ray Absorption Spectroscopy. *Phys. Rev. Lett.* 2014, 113, 227402.
- [34] König, E.; Madeja, K. $^5\text{T}_2$ $^1\text{A}_1$ Equilibria in Some Iron(II)-Bis(1,10-phenanthroline) Complexes. *Inorg. Chem.* 1967, 6, 48.
- [35] Müller, E. W.; Spiering, H.; Gülich, P. Spin transition in $[\text{Fe}(\text{phen})_2(\text{NCS})_2]$ and $[\text{Fe}(\text{bipy})_2(\text{NCS})_2]$: Hysteresis and effect of crystal quality. *Chem. Phys. Lett.* 1982, 93, 567.
- [36] Briois, V.; Cartier dit Moulin, Ch.; Saintavit, Ph.; Brouder, Ch.; Flank, A. M. Full Multiple Scattering and Crystal Field Multiplet Calculations Performed on the Spin Transition $\text{Fe}(\text{phen})_2(\text{NCS})_2$ Complex at the Iron K and L2,3 X-ray Absorption Edges. *J. Am. Chem. Soc.* 1995, 117, 1019–1026.
- [37] Baldé, C.; Desplanches, C.; Wattiaux, A.; Guionneau, P.; Gülich, P.; Létard, J. F. Effect of metal dilution on the light-induced spin transition in $[\text{Fe}_x\text{Zn}_{1-x}(\text{phen})_2(\text{NCS})_2]$ (phen = 1,10-phenanthroline). *Dalton Trans.* 2008, 2702–2707.
- [38] Létard, J. F.; Guionneau, P.; Nguyen, O.; Costa, J. S.; Marcen, S.; Chastanet, G.; Marchivie, M.; Goux-Capes, L. A Guideline to the design of molecular-based materials with long-lived photomagnetic lifetimes. *Chem. Eur. J.* 2005, 11, 4582-4589.
- [39] Hohenberg, P.; Kohn, W. Inhomogeneous Electron Gas. *Phys. Rev. B.* 1964, 136, 864.
- [40] Kohn, W.; Sham, L. J. Self-Consistent Equations Including Exchange and Correlation Effects. *Phys. Rev. A* 1965, 140, 1133.
- [47] Gaussian 09, Revision **D.01**, Frisch, M. J.; Trucks, G. W.; Schlegel, H. B.; Scuseria, G. E.; Robb, M. A.; Cheeseman, J. R.; Scalmani, G.; Barone, V.; Mennucci, B.; Petersson, G. A.; Nakatsuji, H.; Caricato, M.; Li, X.; Hratchian, H. P.; Izmaylov, A. F.; Bloino, J.; Zheng, G.; Sonnenberg, J. L.; Hada, M.; Ehara, M.; Toyota, K.; Fukuda, R.; Hasegawa, J.; Ishida, M.; Nakajima, T.; Honda, Y.; Kitao, O.; Nakai, H.; Vreven, T.; Montgomery,

- J. A., Jr.; Peralta, J. E.; Ogliaro, F.; Bearpark, M.; Heyd, J. J.; Brothers, E.; Kudin, K. N.; Staroverov, V. N.; Kobayashi, R.; Normand, J.; Raghavachari, K.; Rendell, A.; Burant, J. C.; Iyengar, S. S.; Tomasi, J.; Cossi, M.; Rega, N.; Millam, M. J.; Klene, M.; Knox, J. E.; Cross, J. B.; Bakken, V.; Adamo, C.; Jaramillo, J.; Gomperts, R.; Stratmann, R. E.; Yazyev, O.; Austin, A. J.; Cammi, R.; Pomelli, C.; Ochterski, J. W.; Martin, R. L.; Morokuma, K.; Zakrzewski, V. G.; Voth, G. A.; Salvador, P.; Dannenberg, J. J.; Dapprich, S.; Daniels, A. D.; Farkas, Ö.; Foresman, J. B.; Ortiz, J. V.; Cioslowski, J.; Fox, D. J. Gaussian, Inc., Wallingford CT, 2009.
- [42] Zhang, W. K.; Alonso-Mori, R.; Bergmann, U.; Bressler, C.; Chollet, M.; Galler, A.; Gawelda, W.; Hadt, R. G.; Hartsock, R. W.; Kroll, T.; Kjar, K.S.; Kubicek, K.; Lemke, H.T.; Liang, H.W.; Meyer, D.A.; Nielsen, M.M.; Purser, C.; Robinson, J.S.; Solomon, E.I.; Sun, Z.; Sokaras, D.; van Driel, T.B.; Vanko G.; Weng, T.C.; Zhu, D.; Gaffney, K.J. Tracking Excited-State Charge and Spin Dynamics in Iron Coordination Complexes. *Nature* 2014, 509, 345-348.
- [43] van Veenendaal, M.; Chang, J.; Fedro, A. J. Model of Ultrafast Intersystem Crossing in Photoexcited Transition-Metal Organic Compounds. *Phys. Rev. Lett.* 2010, 104, 067401.
- [44] Chuang, J.; Fedro, A. J.; van Veenendaal, M. Ultrafast cascading theory of intersystem crossings in transition-metal complexes. *Phys. Rev. B.* 2010, 82, 075124.
- [45] Baranovic, G.; Babic, D. Vibrational study of the Fe(phen)₂(NCS)₂ spin-crossover complex by density-functional calculations. *Spectrochem. Acta A* 2004, 60, 1013.
- [46] Ronayne, K. L.; Paulsen, H.; Höfer, A.; Dennis, A. C.; Wolny, J. A.; Chumakov, A. I.; Schünemann, V.; Winkler, H.; Spiering, H.; Bousseksou, A.; Gütlich, P.; Trautwein, A. X.; McGarvey, J. J. Vibrational spectrum of the spin crossover complex [Fe(phen)₂(NCS)₂] studied by IR and Raman spectroscopy, nuclear inelastic scattering and DFT calculations. *Phys. Chem. Chem. Phys.* 2006, 4685.
- [47] Martin, R. Natural transition orbitals. *J. Chem. Phys.* 2003, 118, 4775.

Eric Collet was born in 1972 in Brittany, France. He obtained a Ph. D. (1999) degrees from University of Rennes 1 and was Post-Doc at Laboratoire Léon Brillouin (CEA). In 2007 he became full professor at University Rennes 1. In 2008 he obtained a junior chair at the Institut Universitaire de France. His main topics of interest concern photoinduced phase transitions, their ultra-fast structural dynamics and out-of-equilibrium physics.

Roman Bertoni was born in 1987 in France. He received his master degree in Physics from University Rennes 1 in 2010. He obtained his PhD at the University of Rennes 1 in 2013. He is currently post-doc at the Fritz Haber Institute in Berlin.

Marco Cammarata was Born in Palermo, Italy in 1979. He obtained his Master (2002) and PhD at the Palermo University (2006). He was Post Doc at the Center for Molecular Movies (2006-

2009, University of Copenhagen) and Staff Scientist at SLAC National Laboratory on the X-FEL LCLS (2009-2011, Stanford). Since 2011 he is researcher at CNRS. His major research interests concern fast and ultrafast dynamics of molecules in solution (including biomolecules) and photo-active materials.

Maciej Lorenc was born in 1974 in Poznan, Poland. He obtained his PhD in 2001 from UAM, Poznan. In 2002 he joined Michael Wulff's group at ESRF in Grenoble and used picosecond X-ray diffraction to study molecular dynamics in solution. In 2005 he joined CNRS and since has held scientist position at the Institute of Physics of Rennes University. In 2013 he received habilitation degree from Rennes University. His main research interest now is focused on the photo-induced phase transitions.

Jean François Létard was born in 1967 in France and studied Chemistry and Photochemistry at the University of Bordeaux. He received his PhD in 1994 and then obtained an Alexander Von Humboldt fellowship at the University of Mainz (Germany) with the Pr. P. Gütllich. In 1995, he was appointed as CNRS researcher and joined the Molecular Sciences Group of Pr. O. Kahn at the Bordeaux Institute of Condensed Matter Chemistry (ICMCB). His main research interests focus on the elaboration of switchable molecular materials with particular emphasis on photomagnetism and on bistability in connection with industrial applications.

Samir F MATAR was born in 1953 in Beirut, Lebanon. He has a French (and Lebanese) citizenship. He obtained his degrees at University of Bordeaux, B.Sc., M.Sc., 2 Ph.D. He was Formerly Assistant Professor at Lebanese University, Professor at Holy Spirit University and Honorary Dean (Lebanon). Since 1985, he is full time researcher at French National Research

Center (CNRS) at ‘Institut de Chimie de la Matière Condensée de Bordeaux’ ICMCB, Bordeaux-France. Present title 1st class research director (DR1-CNRS). Scientific director of the Supercomputer Center of the University of Bordeaux.

Henrik T Lemke was born 1979 in Cologne, Germany. He obtained his Diploma in 2005 (Physics department, University of Kiel, Germany) and his PhD in 2009 (Niels Bohr Institute, University of Copenhagen, Denmark). He worked as a postoc for the EU project Organic Nanomaterials for Electronics and Photonics (ONE-P, 2009) before he started to work as an Instrument scientist at the X-FEL Linac Coherent Light Source (LCLS) since 2011 at the SLAC National Laboratory. His research interest deals with non-equilibrium processes in functional materials in liquid and solid state.