



**HAL**  
open science

## Investigation of nonlinear bulk viscoelasticity in complex media using dynamic acoustoelasticity

Chloé Trarieux, Samuel Callé, Hélène Moreschi, Marielle Defontaine

### ► To cite this version:

Chloé Trarieux, Samuel Callé, Hélène Moreschi, Marielle Defontaine. Investigation of nonlinear bulk viscoelasticity in complex media using dynamic acoustoelasticity. 10th Annual European Rheology Conference, Apr 2015, Nantes, France. hal-01157905

**HAL Id: hal-01157905**

**<https://hal.science/hal-01157905>**

Submitted on 28 May 2015

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

C. Trarieux<sup>1</sup>, S. Callé<sup>2</sup>, H. Moreschi<sup>1</sup>, M. Defontaine<sup>1</sup>

<sup>1</sup>Rheawave SAS, Bâtiment Vialle, 10 bd Tonnellé, 37032 Tours, France

<sup>2</sup> Université François-Rabelais, INSERM Imagerie et Cerveau UMR U930, 10 bd Tonnellé, 37032 Tours, France

E-mail : chloe.trarieux@rheawave.com

## Introduction

- ❖ Few tools have been developed for industrial quality control of textures. The use of non-contact techniques, based on acoustic waves, offers obvious advantages in food-processing or cosmetics industries : health & safety, non-destructive testing, continuous inline measurement.
- ❖ The Dynamic AcoustoElastic Testing (DAET) assesses the nonlinear viscoelastic properties of materials in response to a bulk compression/expansion stress. In this study, we present several applications of DAET method in complex media.


Keywords:

Non-contact  
Acoustic rheology  
Nonlinear viscoelasticity



## DAET method

- ❖ Interaction between two acoustic waves :

- Low-frequency sinusoidal wave (LF, 4kHz) to successively compress and expand the medium,
- Ultrasound longitudinal pulses (US, 1 MHz) to probe this medium at different pressure values imposed by the LF wave.

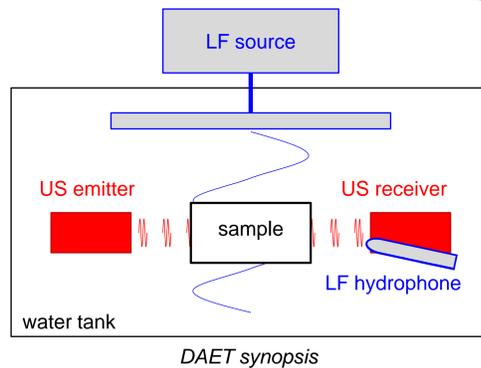

- ❖ Measurement of the Time of Flight Modulations (TOFM) of the US pulses, induced by the variations of the applied LF pressure:  $TOFM = TOF_{P_{LF}} - TOF_0$

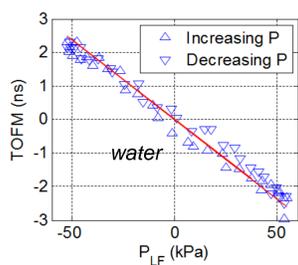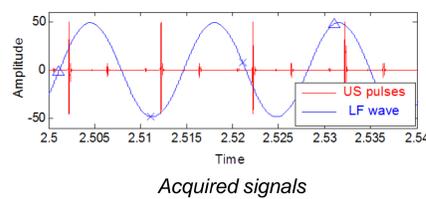

- ❖ DAET diagram: plot of TOFM as a function of LF pressure

$$\Rightarrow TOFM^* \approx -\frac{L}{c_0^2} \Delta c^* \approx -\frac{L}{2\rho_0 c_0^3} \Delta M^*$$

with  $c$  the celerity,  $L$  the length propagation,  $\rho$  the density and  $M^* = \rho c^2$  the complex longitudinal modulus

## Nonlinear viscoelastic parameters

$$M^* = A^* - B^* \varepsilon + C^* \frac{\varepsilon^2}{2} - \dots$$

$$\Rightarrow \Delta M^* = -B^* \varepsilon + C^* \frac{\varepsilon^2}{2} - \dots = -(B + j\omega\eta_B) \varepsilon + (C + j\omega\eta_C) \frac{\varepsilon^2}{2} - \dots$$

- ❖ From the measured TOFM, we identify nonlinear viscoelastic parameters:


$$TOFM = -\frac{L}{2\rho_0 c_0^3} \operatorname{Re} \left\{ \left( \frac{B}{A} + j \frac{\omega\eta_B}{A} \right) \Delta P + \left( \frac{C}{A} + j \frac{\omega\eta_C}{A} \right) \frac{\Delta P^2}{2A} \right\}$$

Elastic parameters ( $B/A$ ,  $C/A$ )

Viscous parameters ( $\omega\eta_B/A$ ,  $\omega\eta_C/A$ )

## Validation in Fluids

HOMOGENEOUS MEDIA

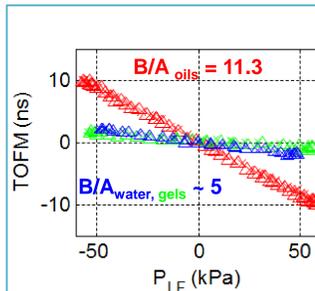

Water, Carbomer gels, Silicon oils :

- Low values of  $B^*$   $\Rightarrow$  homogeneous media


$$\frac{B}{A} < 15$$

$$\frac{\omega\eta_B}{A} < 1$$


- Governed by fluid nature

## Results in Complex media

POLYMERIZATION

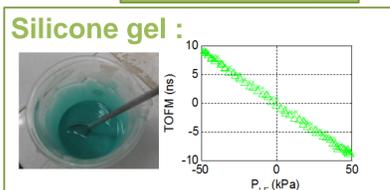


- ❖ Silicon hardening kinetics :  
 $\Rightarrow$  Gel time determination

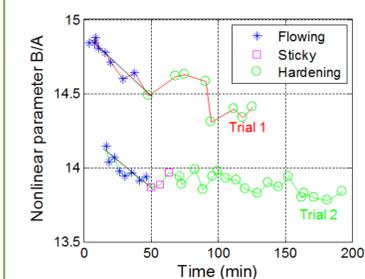


Governed by chemical bonds

GRANULAR MEDIA



250  $\mu$ m glass beads in gelatin :

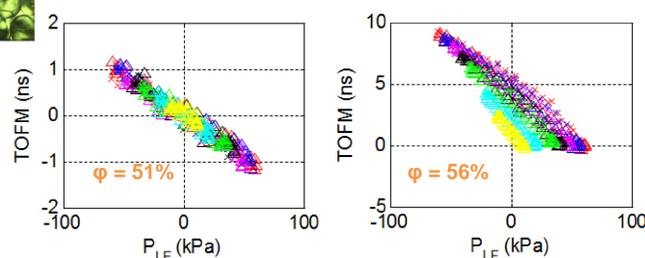

No beads contact ( $B^*$ )

Beads contact ( $B^*$ ,  $C^*$ )


$B/A$	$12,2 \pm 0,2$
$\omega\eta_B/A$	$-0,5 \pm 0,7$
Offset (ns)	$0,0 \pm 0,1$

$B/A$	$68 \pm 13$
$\omega\eta_B/A$	$14 \pm 3$
$C/A$ ( $\times 10^6$ )	$2 \pm 1$
Offset (ns)	$3,9 \pm 1,1$


- ❖ Sensitivity to a percolation threshold

Governed by beads contact

AIR-BASED MEDIA




Hollow glass beads in water :

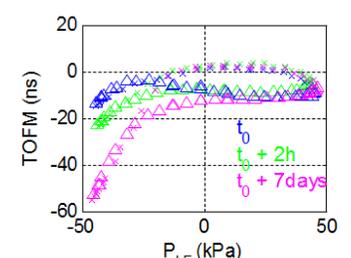

- ❖ High values of  $B^*$ ,  $C^*$  and  $D^*$   
 $\Rightarrow$  air presence

- ❖ Efficient creaming monitoring :

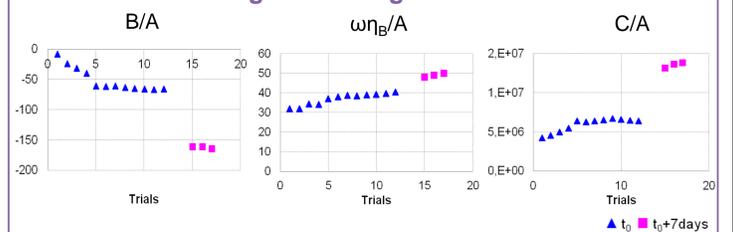

Governed by air and beads contact

## Conclusion and perspectives

- ❖ The DAET method measures with a good reproducibility the variations of the bulk viscoelastic modulus, through the quantification of nonlinear elastic and viscous parameters.
- ❖ Homogeneous fluids exhibit classical viscoelastic nonlinearities (1<sup>st</sup> order  $B^*$ ) and complex media nonclassical viscoelastic nonlinearities (until 3 orders  $B^*$ ,  $C^*$ ,  $D^*$ ).
- ❖ This method appears to be an interesting alternative to conventional rheometry, especially for the characterization of these complex fluids.
- ❖ A similar work has to be done on the RAM data related to an attenuation of US pulses (thanks to a nonlinear Kramers-Kronig relationship ?...)