



HAL
open science

Statistical Analysis of the Influence of Some Trace Elements on Chunky Graphite Formation in Heavy Section Nodular Iron Castings

Jon Sertucha, Jacques Lacaze, Susana Armendariz, Peio Larrañaga

► **To cite this version:**

Jon Sertucha, Jacques Lacaze, Susana Armendariz, Peio Larrañaga. Statistical Analysis of the Influence of Some Trace Elements on Chunky Graphite Formation in Heavy Section Nodular Iron Castings. Metallurgical and Materials Transactions A, 2013, vol. 44 (n° 3), pp. 1159-1162. 10.1007/s11661-012-1592-8 . hal-01170437

HAL Id: hal-01170437

<https://hal.science/hal-01170437>

Submitted on 1 Jul 2015

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Open Archive TOULOUSE Archive Ouverte (OATAO)

OATAO is an open access repository that collects the work of Toulouse researchers and makes it freely available over the web where possible.

This is an author-deposited version published in : <http://oatao.univ-toulouse.fr/>
Eprints ID : 14063

To link to this article : DOI:10.1007/s11661-012-1592-8

URL : <http://dx.doi.org/10.1007/s11661-012-1592-8>

To cite this version : Sertucha, Jon and Lacaze, Jacques and Armendariz, Susana and Larrañaga, Peio *Statistical Analysis of the Influence of Some Trace Elements on Chunky Graphite Formation in Heavy Section Nodular Iron Castings*. (2013) Metallurgical and Materials Transactions A, vol. 44 (n° 3). pp. 1159-1162. ISSN 1073-5623

Any correspondence concerning this service should be sent to the repository administrator: staff-oatao@listes-diff.inp-toulouse.fr

Communication

Statistical Analysis of the Influence of Some Trace Elements on Chunky Graphite Formation in Heavy Section Nodular Iron Castings

JON SERTUCHA, JACQUES LACAZE,
SUSANA ARMENDARIZ, and PEIO LARRAÑAGA

To study the formation of chunky graphite (CHG) in heavy section castings, 68 nodular cast irons of both pearlitic and ferritic grades were cast in cubic blocks 30 cm in edge. The volume fraction of the blocks affected by this degenerate graphite was quantified and related to the chemical analysis of the materials by means of a multivariate analysis. For the composition domain investigated, the effects of Ce, Cu, La, P, Sb, and Sn were statistically established with a high R^2 correlation coefficient.

Although the influence of graphite degeneration on mechanical properties of ductile irons has been the subject of several technical works in recent decades, the present knowledge about the mechanisms that cause it is still limited. One of the most important examples among these degenerations is chunky graphite (CHG), which was documented to have a detrimental effect on mechanical properties of nodular irons such as those used in the windmills industry.^[1-3] A noteworthy number of studies have focused on the influence of processing variables and of manufacturing conditions on CHG formation,^[2,4,5] while other works were aimed at determining the microscopic causes for the appearance of this defect.^[4, 6-9] Regarding the processing variables, it was found that both inoculation^[1,5,10] and low cooling rates^[4,11,12] promote CHG formation in nodular irons. The effect of inoculation, however, is controversial, as previously discussed.^[5] Furthermore, it has long been demonstrated that the chemical composition of melts has an important influence on this graphite degeneracy, which depends both on the main alloying elements such as C and Si through carbon equivalent^[9,13] and on trace elements such as As, Bi, Pb,

Sb, Te, or Ti.^[4,14] The interplay between these metallic trace elements and rare earth additions through spheroidization and inoculation treatments was demonstrated.^[4,15] The effect of Ce,^[16] Sb,^[16,17] Bi, and Sb^[18] was more particularly studied, and these elements were found to significantly affect this defect.

While it is recognized that very low levels of some elements may affect graphite degeneration in heavy-section nodular iron castings, very little quantitative information has been made available so far. The present work was designed to answer the need of quantitative prediction on the risk of CHG appearance in heavy-section castings. Chemical and metallographic data used in the present work were obtained from 68 cubic blocks 30 cm in side cast according to the experimental methodology previously described.^[5] The addition of specific alloying elements was performed in the ladle used to achieve the nodularizing treatment so as to have either pearlitic or ferritic grades. The chemical composition of the FeSiMg master alloy used for nodularizing was (wt pct) 42.2 to 45.0Si, 8.5 to 9.1Mg, 2.5 to 2.8Ca, 0.9 to 1.1Al, and 0.8 to 1.1 rare earths (RE). Postinoculation was carried out using a commercial inoculant (70 to 75Si, 3.2 to 4.5Al, 0.3 to 1.5Ca, and 0.4 to 0.6RE, wt pct). Chemical analysis of the cast materials was carried out on chips from the cast blocks by means of standard techniques. Table I gives the minimum and maximum values for all elements found to be significant in the present work. Among these casts, three of them were done for investigating the effect of nickel; they contained 0.03, 0.53, and 0.84 wt pct Ni. For these latter casts, the composition of the FeSiMg was (wt pct) 43.6Si, 6.3Mg, 1.1Ca, 0.6Al, and 0.9RE and that of the inoculant 74.4Si, 1.2Ca, 4.1Al, and 0.5RE. All alloys were nearly eutectic, the pearlitic grades having carbon content in the range of 3.69 to 3.87 wt pct and the ferritic ones in the range of 3.61 to 3.82 wt pct. The amount of CHG was quantified by the relative volume affected by this degeneration, V_V (pct), as estimated from an axial section of the blocks.^[5]

Using JMP software, multivariate analysis was performed to assess the effect of individual elements on V_V and for looking for the interaction between them. For this, the values of V_V and of the content in Sb that were null were set to 10^{-4} , so that the whole record of data could be processed. When performing the statistical analysis, only those parameters that were found to be statistically relevant for the available data set were selected. The shape of the residues *vs* V_V suggested looking for a relation involving $(V_V)^{0.5}$ instead of V_V . The final expression at which we arrived is given as

$$\begin{aligned} (V_V)^{0.5} = & -3.1 - 1214.0 \cdot (1 - 64.6 \cdot w_{Sb} - 0.37 \cdot w_{Cu}) \cdot w_{Sb} \\ & - 55.2 \cdot (1 - 4.8 \cdot w_{Sn} - 114.8 \cdot w_{Sb}) \cdot w_{Sn} \\ & + 924.2 \cdot (1 - 64.4 \cdot w_{Ce}) \cdot w_{Ce} \\ & + 605.0 \cdot (1 - 0.59 \cdot w_{Cu}) \cdot w_{La} + 133.3 \cdot w_P \quad (1) \end{aligned}$$

where w_i is the mass fraction of element i as obtained from chemical analysis.

This relation with 12 terms gives a fit to experimental data with a quite high R^2 coefficient of 0.94; this is illustrated in Figure 1.

JON SERTUCHA and PEIO LARRAÑAGA, Research Engineers, are with the Área de Ingeniería y Procesos de Fundición, AZTERLAN, 48200 Durango (Bizkaia), Spain. JACQUES LACAZE, Senior Scientist, is with CIRIMAT, Université de Toulouse, ENSIACET, BP 44362, 31030 Toulouse cedex 4, France. Contact e-mail: jacques.lacaze@ensiacet.fr SUSANA ARMENDARIZ, Engineer, is with TS Fundiciones, S.A. Pol. Sansinenea Erreka, 20749 Arroa-Zestoa (Gipuzkoa), Spain.

Table I. Composition Range of the Most Significant Elements in the Studied Alloys (Weight Percent)

Si	Mn	Cu	P	S	Mg	Sb	Sn	Ce	La
1.92 to 2.41	0.09 to 1.04	0.01 to 1.11	0.010 to 0.039	0.002 to 0.015	0.023 to 0.055	0.0 to 0.010	0.0 to 0.14	0.0005 to 0.0162	0.0005 to 0.0074

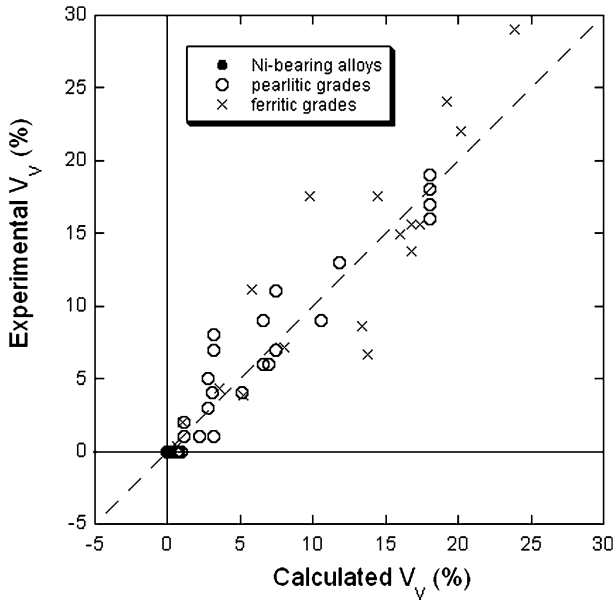


Fig. 1—Comparison of experimental and calculated values of V_v using Eq. [1].

When Sn and Sb are known to decrease the risk of CHG formation, as indicated by the negative sign in front of the related terms, the cross-term Sn-Sb is positive, indicating that these elements are counteracting each other at high enough level. As there is no stable compound between these elements at the temperature for processing and solidifying cast irons, this observation may be indicative of more complex interactions through other elements present in the melts or at the graphite liquid interface. As for Cu, this element was reported to decrease the risk of chunky appearance,^[19] but the present analysis shows this beneficial effect to be related to the presence of La while a negative cross-effect, *i.e.*, an increase of V_v , is associated with its association with Sb. Again, there is no compound stable at high enough temperature in the binary Cu-La and Cu-Sb systems that could help in understanding this result. These cross-effects are thus certainly worthy of further investigations.

The presence of a square term for Sb, Sn, and Ce in Eq. [1] suggests these elements could show an optimum value within the composition range investigated. The effect of each of these three elements on the predicted $(V_v)^{0.5}$ values is illustrated in Figure 2. The curves in this figure were obtained using Eq. [1] by varying the content of either Sb, Sn, or Ce with all other elements set at the minimum indicated in Table I (Figure 2(a)), at the mid of the composition range (Figure 2(b)) or at the maximum (Figure 2(c)). Note that a tenth of the Sn

content was used in plotting for easier reading of the figures.

Figure 2(a) shows that a cast iron with a composition at the minimum of the range in each element, and thus quite pure, would not present CHG, while an alloy with all elements at the mid (respectively, maximum) level in Table I would be slightly (respectively, significantly) affected.

It is seen in the graphs in Figure 2 that cerium addition has the same effect whatever the content in other elements. Cerium is detrimental for addition up to 0.008 wt pct and shows a healing effect above that percentage. The effect of cerium in increasing the amount of CHG when added at low and intermediate levels agrees with reports on heavy section castings. The present work suggests that, at higher level, cerium becomes beneficial, and this could possibly be related to the fact that it increases eutectic undercooling,^[16] thus favoring spheroidal growth.

Sb and Sn present the same behavior, decreasing CHG when added at low level in pure or slightly impure cast irons, but it is seen that they both would become detrimental in strongly contaminated alloys. The optimum addition of Sn is about 0.1 wt pct for a pure cast iron (Figure 2(a)) and about 0.05 for a slightly impure one (Figure 2(b)). These optimum values are similar to the maximum allowable Sn content at 0.13 wt pct reported in Lux's review.^[20] As for Sb, it should be noted that degenerate graphite due to Sb in usual castings has most often been reported as spiky graphite and not CHG. On the other hand, its beneficial effect in heavy-section castings was associated to Sb binding Ce in Ce-Sb compounds.^[4]

A close examination of Figure 1 shows that the investigated pearlitic grades present, on the whole, lower amounts of CHG than do ferritic grades. However, these pearlitic grades were obtained by adding one of either Cu, Mn, or Sn, but never both of them. Thus, Figure 2(c), where the predicted V_v values are higher than in Figures 2(a) and (b), is somehow an extrapolation of the present correlation in a composition range that has not been investigated.

Finally, the most striking observation made when looking at Eq. [1] concerns the role of P. As a matter of fact, it has never been reported explicitly as leading to CHG formation, as shown here, but is known to have a detrimental effect on graphite shape,^[20,21] much like Sb, as mentioned previously. However, a statistical analysis made by Javard and Loper^[4] showed the same trend as here, though the authors did not comment on this finding. Further, Reynaud and Parent-Simonin^[15] reported on a P spike around CHG cells, again without giving any hint about its meaning and consequences. This effect of P does not seem to relate directly to the fact that it may easily

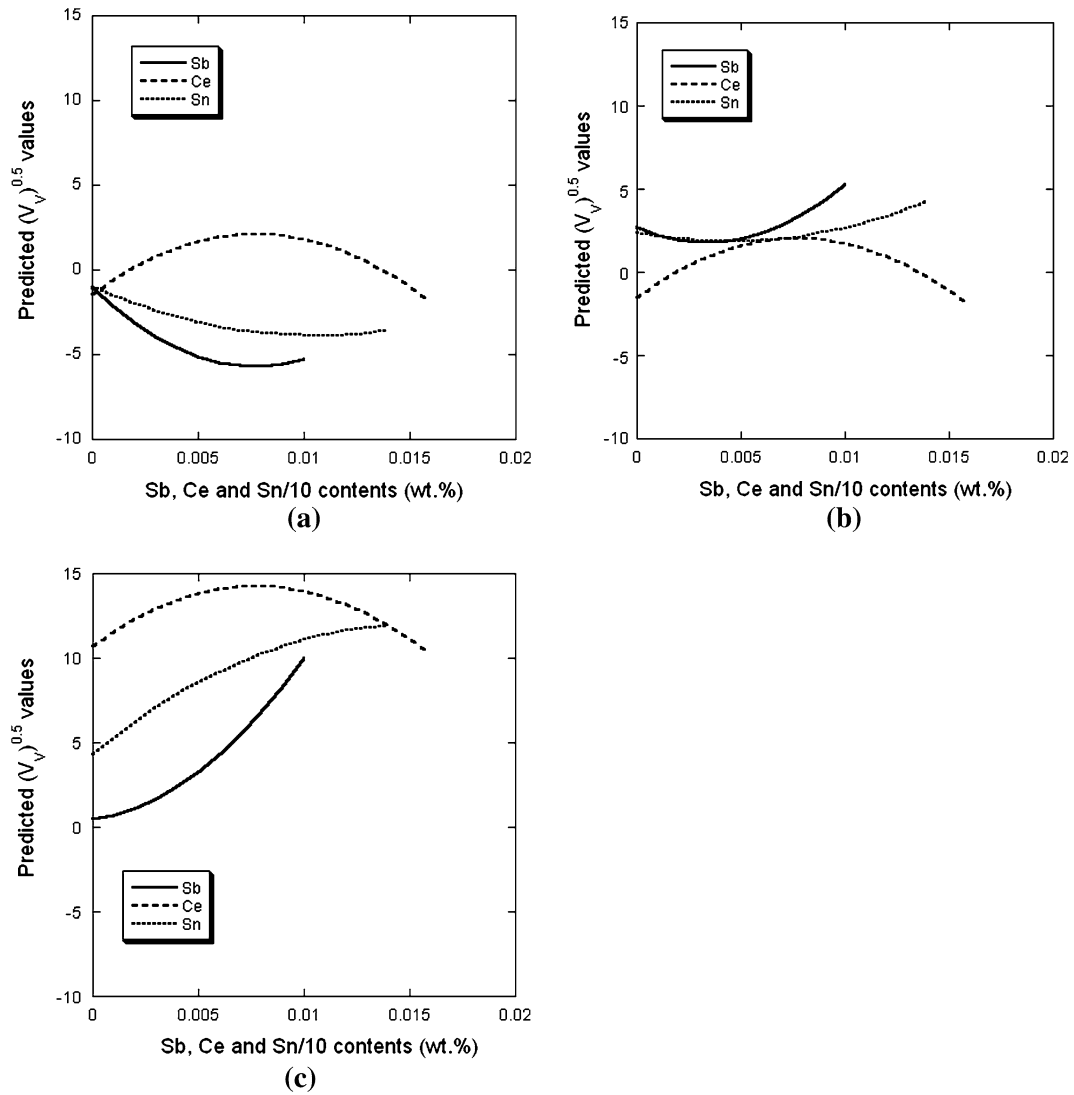


Fig. 2—Predicted change in CHG content $(V_V)^{0.5}$ with addition of Sb, Ce, and Sn. For easier reading, the tenth of the addition in Sn was used and the curves were limited to the investigated composition range for each of these three elements. (a) through (c) were obtained for, respectively, the minimum, the mid, and the maximum of the composition range of other elements.

combine with Ce to form CeP compound, which was observed.^[4,22] One possible explanation, which should be investigated further, is that the addition of P leads to the dissolution of some Ce-bearing compounds that are less stable than CeP and contain detrimental elements that can get dissolved again in the melt.

The present analysis offers a means to evaluate the risk for CHG formation in heavy-section castings on the basis of chemical contents in a limited number of elements. It is clear, however, that a more extensive study would be necessary to account for other low level elements that are known to modify graphite growth behavior.

REFERENCES

1. Z. Ignaszak: *Int. J. Cast Met. Res.*, 2003, vol. 16, pp. 93–97.
2. R. Källbom, K. Hamberg, and L.E. Björkegren: in *Proc. Gjuteknologin 2005 Final Seminar*, VTT Technical Research Centre of Finland, Espoo, 2005, pp. 1–25.
3. M. Gagné and C. Labrecque: *AFS Trans.*, 2009, vol. 117, pp. 561–71.
4. A. Javaid and C.R. Loper, Jr.: *AFS Trans.*, 1995, vol. 103, pp. 135–50.
5. I. Asenjo, P. Larrañaga, J. Sertucha, R. Suárez, J.M. Gómez, I. Ferrer, and J. Lacaze: *Int. J. Cast Met. Res.*, 2007, vol. 20, pp. 319–24.
6. E.N. Pan, C.N. Lin, and H.S. Chiou: *AFS Trans.*, 1995, vol. 103, pp. 265–73.
7. B.C. Liu, T.X. Li, Z.J. Rue, X.Y. Yang, E.Q. Huo, and C.R. Loper, Jr.: *AFS Trans.*, 1990, vol. 98, pp. 753–57.
8. E. Campomanes: *Giesserei*, 1978, vol. 65, pp. 535–40.
9. T.C. Xi, J. Fargues, M. Hecht, and J.C. Margerie: *Mater. Res. Soc. Symp. Proc.*, 1985, vol. 34, pp. 67–76.
10. S.I. Karsay and E. Campomanes: *AFS Trans.*, 1970, vol. 58, pp. 85–92.
11. R. Källbom, K. Hamberg, M. Wessen, and L.E. Björkegren: *Mater. Sci. Eng. A*, 2007, vols. 413–414, pp. 346–51.
12. H.W. Hoover, Jr.: *AFS Trans.*, 1986, vol. 102, pp. 601–08.
13. J. Lacaze, S. Armendariz, P. Larrañaga, I. Asenjo, J. Sertucha and R. Suárez: *Mater. Sci. Forum*, 2010, vols. 636–637, pp. 523–30.
14. H. Löblich: *Giesserei*, 2006, vol. 93, pp. 28–41.
15. A. Reynaud and S. Parent-Simonin: *Fonderie, Fondateur d'aujourd'hui*, 1990, vol. 91, pp. 17–25.
16. P. Larrañaga, I. Asenjo, J. Sertucha, R. Suarez, I. Ferrer, and J. Lacaze: *Metall. Mater. Trans. A*, 2009, vol. 40A, pp. 654–61.

17. P. Larrañaga, I. Asenjo, J. Sertucha, R. Suarez, I. Ferrer, and J. Lacaze: *Int. J. Cast Met. Res.*, 2009, vol. 22, pp. 192–95.
18. E.N. Pan and C.Y. Chen: *AFS Trans.*, 1996, vol. 104, pp. 845–58.
19. N. Carter and R. Barton: *BCIRA J.*, 1966, vol. 14, pp. 252–63.
20. B. Lux: *Giessereiforschung*, 1970, vol. 22, pp. 65–81.
21. *ASM Specialty Handbook*, ASM International, Materials Park, OH, 1996.
22. I. Asenjo, J. Lacaze, P. Larrañaga, S. Méndez, J. Sertucha and R. Suarez: *Key Eng. Mater.*, 2011, vol. 457, pp. 52–57.