



**HAL**  
open science

## Capacitance of Ti<sub>3</sub>C<sub>2</sub>T<sub>x</sub> MXene in ionic liquid electrolyte

Zifeng Lin, Daffos Barbara, Pierre-Louis Taberna, Katherine L. van Aken, Babak Anasori, Yury Gogotsi, Patrice Simon

► **To cite this version:**

Zifeng Lin, Daffos Barbara, Pierre-Louis Taberna, Katherine L. van Aken, Babak Anasori, et al.. Capacitance of Ti<sub>3</sub>C<sub>2</sub>T<sub>x</sub> MXene in ionic liquid electrolyte. *Journal of Power Sources*, 2016, 326, pp.575-579. 10.1016/j.jpowsour.2016.04.035 . hal-01466709

**HAL Id: hal-01466709**

**<https://hal.science/hal-01466709>**

Submitted on 13 Feb 2017

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



## Open Archive TOULOUSE Archive Ouverte (OATAO)

OATAO is an open access repository that collects the work of Toulouse researchers and makes it freely available over the web where possible.

This is an author-deposited version published in : <http://oatao.univ-toulouse.fr/>  
Eprints ID : 16655

**To link to this article** : DOI:10.1016/j.jpowsour.2016.04.035  
URL : <http://dx.doi.org/10.1016/j.jpowsour.2016.04.035>

**To cite this version** : Lin, Zifeng and Barbara, Daffos and Taberna, Pierre-Louis and Van Aken, Katherine L. and Anasori, Babak and Gogotsi, Yury and Simon, Patrice *Capacitance of Ti<sub>3</sub>C<sub>2</sub>T<sub>x</sub> MXene in ionic liquid electrolyte*. (2016) Journal of Power Sources, vol. 326. pp. 575-579. ISSN 0378-7753

Any correspondence concerning this service should be sent to the repository administrator: [staff-oatao@listes-diff.inp-toulouse.fr](mailto:staff-oatao@listes-diff.inp-toulouse.fr)

# Capacitance of $\text{Ti}_3\text{C}_2\text{T}_x$ MXene in ionic liquid electrolyte

Zifeng Lin <sup>a, b</sup>, Daffos Barbara <sup>a, b</sup>, Pierre-Louis Taberna <sup>a, b</sup>, Katherine L. Van Aken <sup>c</sup>,  
Babak Anasori <sup>c</sup>, Yury Gogotsi <sup>c</sup>, Patrice Simon <sup>a, b, \*</sup>

<sup>a</sup> CIRIMAT, Université de Toulouse, CNRS, INPT, UPS, 118, route de Narbonne, 31062 Toulouse cedex 9, France

<sup>b</sup> Réseau sur le Stockage Electrochimique de l'Energie (RS2E), FR CNRS 3459, France

<sup>c</sup> Department of Materials Science & Engineering, A.J. Drexel Nanomaterials Institute, Drexel University, Philadelphia, PA 19104, USA

## H I G H L I G H T S

- $\text{Ti}_3\text{C}_2\text{T}_x$ -ionogel film was prepared by vacuum filtration and ionic liquid immersion.
- Capacitance of  $70 \text{ F g}^{-1}$  in a voltage window of 3 V was achieved in EMI-TFSI.
- High power performance was obtained as shown by the rectangular CVs shape.

## A B S T R A C T

$\text{Ti}_3\text{C}_2\text{T}_x$  MXene, a two-dimensional (2D) early transition metal carbide, has shown an extremely high volumetric capacitance in aqueous electrolytes, but in a narrow voltage window (less than 1.23 V). The utilization of MXene materials in ionic liquid electrolytes with a large voltage window has never been addressed. Here, we report the preparation of the  $\text{Ti}_3\text{C}_2\text{T}_x$  MXene ionogel film by vacuum filtration for use as supercapacitor electrodes operating in 1-Ethyl-3-methylimidazolium bis(trifluoromethylsulfonyl) imide (EMI-TFSI) neat ionic liquid electrolyte. Due to the disordered structure of the  $\text{Ti}_3\text{C}_2\text{T}_x$  hydrogel film and a stable spacing after vacuum drying, achieved through ionic liquid electrolyte immersion of the  $\text{Ti}_3\text{C}_2\text{T}_x$  hydrogel film, the  $\text{Ti}_3\text{C}_2\text{T}_x$  surface became accessible to  $\text{EMI}^+$  and  $\text{TFSI}^-$  ions. A capacitance of  $70 \text{ F g}^{-1}$  together with a large voltage window of 3 V was obtained at a scan rate of  $20 \text{ mV s}^{-1}$  in neat EMI-TFSI electrolyte. The electrochemical signature indicates a capacitive behavior even at a high scan rate ( $500 \text{ mV s}^{-1}$ ) and a high power performance. This work opens up the possibilities of using MXene materials with various ionic liquid electrolytes.

### Keywords:

Supercapacitors  
MXene  
 $\text{Ti}_3\text{C}_2\text{T}_x$   
ionogel  
ionic liquid

## 1. Introduction

MXenes are a novel family of two-dimensional (2D) early transition metal carbides and carbonitrides which are produced by selective etching of the A element from MAX phases. MXenes are usually referred to as  $\text{M}_{n+1}\text{X}_n\text{T}_x$ , where M is an early transition metal, X is carbon and/or nitrogen, T represents surface terminations ( $=\text{O}$ ,  $-\text{OH}$ , and/or  $-\text{F}$ ),  $n = 1, 2$ , or 3, and  $x$  is the number of terminating groups per formula unit [1–4]. MXenes have shown great potential as electrode materials for both Li-ion batteries [5–10] and supercapacitors [1,11–13] where high volumetric capacitance up to  $900 \text{ F cm}^{-3}$  was reported in aqueous electrolyte

for the latter [1]. However, when a colloidal solution of MXene flakes is filtered for MXene paper electrode preparation, they restack and once the film was completely dried, the  $c$ -lattice parameter dropped dramatically. In other words, their interlayer spacing becomes smaller and this process was irreversible [14]. MXene flakes' restacking during filtration and their small interlayer spacing limit the accessibility to electrolyte ions, especially the large ions of ionic liquids, hindering the full utilization of the surface area thus leading to poor electrochemical behavior [15]. Improvement has been made by adding carbon nanotubes or graphene materials to MXene [15,16] and making composite materials, which also enhanced the capacitance of MXene-based supercapacitors in organic electrolytes [17]. However, the use of pure MXenes in ionic liquid electrolytes has not been reported yet. Ionic liquids (ILs) are solvent-free salts that are liquid at room temperature. They are promising for energy storage devices due to their

\* Corresponding author. CIRIMAT, Université de Toulouse, CNRS, INPT, UPS, 118, route de Narbonne, 31062 Toulouse cedex 9, France.

E-mail address: [simon@chimie.ups-tlse.fr](mailto:simon@chimie.ups-tlse.fr) (P. Simon).

low vapor pressure, electrochemical stability, and nonflammability. They can also operate at very high voltages compared to other electrolytes for energy storage devices ( $>4$  V in some cases) [18]. Nevertheless, one drawback is the low ion mobility and high viscosity, making such electrolytes less suitable for highly porous electrode materials or layered materials with a small interlayer distance.

In this paper, we propose a facile route for making a  $\text{Ti}_3\text{C}_2\text{T}_x$  hydrogel film by vacuum filtration, to prevent restacking of the flakes. The prepared  $\text{Ti}_3\text{C}_2\text{T}_x$  hydrogel film was further immersed in the ionic liquid electrolyte; after vacuum drying, ionic liquid (low vapor pressure and thermally stable) remained in the  $\text{Ti}_3\text{C}_2\text{T}_x$  film, which increased the MXene interflake spacing and prevented restacking. Hence, the surface of  $\text{Ti}_3\text{C}_2\text{T}_x$  flakes became accessible to the large size cations and anions of the ionic liquid electrolyte. Using this  $\text{Ti}_3\text{C}_2\text{T}_x$  ionogel film as electrode material for supercapacitors in EMI-TFSI electrolyte, a capacitance of  $70 \text{ F g}^{-1}$  within a large voltage window of 3 V is reported, as well as a high power performance.

## 2. Experimental

### 2.1. Material preparation

Multilayer  $\text{Ti}_3\text{C}_2\text{T}_x$  particles were prepared by selective etching of Al from  $\text{Ti}_3\text{AlC}_2$  by a mixture solution of hydrochloric acid (HCl) and lithium fluoride (LiF) [1]. Briefly, 2 g LiF was added to 40 mL 9 M HCl solution, followed by the slow addition of 2 g of  $\text{Ti}_3\text{AlC}_2$ . After etching for 24 h at  $35^\circ\text{C}$ , the obtained  $\text{Ti}_3\text{C}_2\text{T}_x$  flakes were washed until a pH value of  $\sim 6$  was achieved. The delaminated  $\text{Ti}_3\text{C}_2\text{T}_x$  colloidal solution was prepared by 1-h sonication, followed by 1-h centrifugation at 3500 rpm to eliminate the sediment.

### 2.2. Film preparation

$\text{Ti}_3\text{C}_2\text{T}_x$  dried film and hydrogel film were both prepared by vacuum filtration of delaminated  $\text{Ti}_3\text{C}_2\text{T}_x$  colloidal solution as shown in Fig. 1. The dried film was prepared by vacuum filtration to completely expel water from inside. To make the hydrogel film (Fig. 1), the vacuum was disconnected immediately once there were no free  $\text{Ti}_3\text{C}_2\text{T}_x$  colloidal flakes on the wet filtrate cake. After vacuum filtration, both films were immersed in acetone and carefully

peeled off from the filter membrane. Compared to dried  $\text{Ti}_3\text{C}_2\text{T}_x$  film, the hydrogel  $\text{Ti}_3\text{C}_2\text{T}_x$  film is assumed to contain huge amounts of water and acetone between  $\text{Ti}_3\text{C}_2\text{T}_x$  flakes. Afterward, the  $\text{Ti}_3\text{C}_2\text{T}_x$  dried film was transferred to a vacuum oven for drying at  $80^\circ\text{C}$  for 48 h and we henceforth will refer to it as dried film. The hydrogel film was immersed in EMI-TFSI electrolyte to exchange with water and acetone for more than 72 h, followed by 48 h of vacuum drying at  $80^\circ\text{C}$  to remove the residual water and acetone and will henceforth be referred to as ionogel film.

### 2.3. Electrochemical tests

$\text{Ti}_3\text{C}_2\text{T}_x$  disc films were punched (with a diameter of 10 mm) after vacuum drying from both samples and used as electrodes directly without any binders. 1-ethyl-3-methylimidazolium bis-(trifluoromethylsulfonyl)-imide (EMI-TFSI) neat ionic liquid was used as the electrolyte. Two layers of separator (Celgard<sup>®</sup> 3501) were used together with platinum discs as current collectors. Two-electrode Swagelok symmetric cells were assembled and tested at room temperature by using a VMP3 potentiostat (Biologic, USA.). All supercapacitors were assembled in a glove box under argon atmosphere with water and oxygen contents less than 1 ppm.

Electrochemical impedance spectroscopy (EIS) measurements were carried out at open circuit voltage (OCV) with an amplitude of 10 mV at the frequency range from 200 kHz to 0.01 Hz. Capacitances were calculated from cyclic voltammograms (CVs) by measuring the slope of the integrated discharge charge  $Q$  versus cell voltage (V) plot. Since all the tests were performed using a symmetric cell, the gravimetric electrode capacitance was calculated using Equation (1):

$$C = \frac{2\Delta Q}{\Delta V \cdot m} \quad (1)$$

where  $C$  is the specific capacitance ( $\text{F g}^{-1}$ );  $\Delta Q/\Delta V$  is the slope of the integrated discharge charge  $Q$  versus cell voltage plot;  $m$  is the mass of  $\text{Ti}_3\text{C}_2\text{T}_x$  of one electrode (g). 3-electrode experiments (not shown) have confirmed that both positive and negative electrode exhibit similar gravimetric capacitance.

### 2.4. Characterization

X-ray diffraction (XRD) patterns of  $\text{Ti}_3\text{C}_2\text{T}_x$  films were recorded


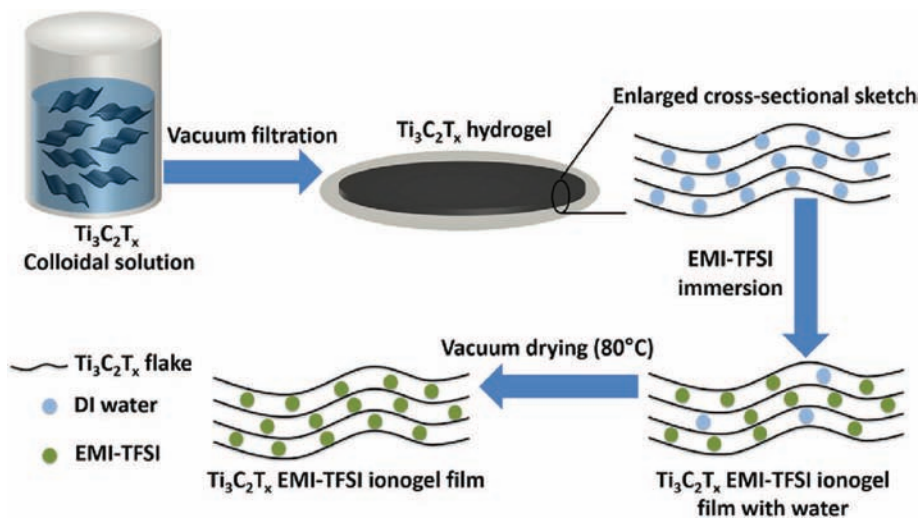


Fig. 1. Schematic of producing  $\text{Ti}_3\text{C}_2\text{T}_x$  EMI-TFSI ionogel film.

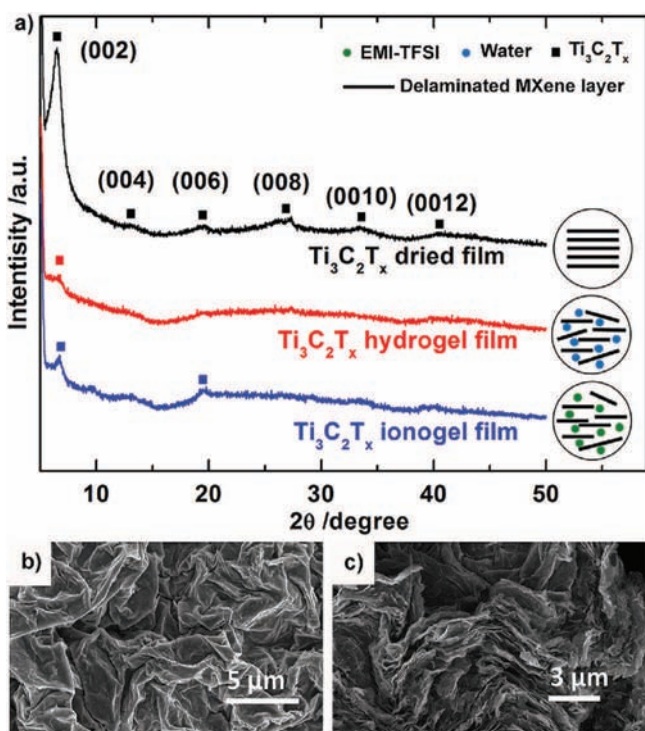

**Fig. 2.** a) XRD patterns of  $\text{Ti}_3\text{C}_2\text{T}_x$  dried film, hydrogel film and ionogel film; b, c) SEM images of  $\text{Ti}_3\text{C}_2\text{T}_x$  ionogel film: b) top view; c) cross-sectional view.

by a Bruker D4 (Bruker, Germany) diffractometer using a  $\text{Cu K}\alpha$  radiation ( $\lambda = 0.154 \text{ nm}$ ) in the range  $2\theta = 5\text{--}50^\circ$  at a step rate of

$0.06^\circ \text{ s}^{-1}$ .


Scanning electron microscope (SEM) observations of the  $\text{Ti}_3\text{C}_2\text{T}_x$  films were made using a FEG-SEM (EOL JSM 6700F, Japan).

### 3. Results and discussion

Fig. 2a presents the XRD diffraction patterns of the  $\text{Ti}_3\text{C}_2\text{T}_x$  dried, hydrogel and ionogel films. For comparison, all tested films were cut with the same size and the same weight of MXene material. The (002) peak around  $6.5^\circ$  (corresponding to a  $c$ -lattice parameter of  $\sim 27 \text{ \AA}$ ) in the dried film's XRD pattern evidences the existence of water between  $\text{Ti}_3\text{C}_2\text{T}_x$  flakes [1]. It has been shown previously that vacuum drying at above  $100^\circ \text{C}$  is needed to remove the water between MXene flakes [19]. The high intensity of the (002) peak and the presence of all (00 $l$ ) peaks in the dried film can be ascribed to restacking of  $\text{Ti}_3\text{C}_2\text{T}_x$  flakes. However, (00 $l$ ) peak intensities, especially (002), decrease in the hydrogel and ionogel XRD patterns, which is due to the interruption of  $\text{Ti}_3\text{C}_2\text{T}_x$  flakes restacking [20]. The nonperiodic (disordered) structure of the ionogel film vs. the dried film is believed to enhance the accessibility of cations and anions of ionic liquid electrolyte into the MXene layers.

SEM observations of the  $\text{Ti}_3\text{C}_2\text{T}_x$  ionogel film are shown in Fig. 2b and c. The top view, Fig. 2b, presents many wrinkles on the  $\text{Ti}_3\text{C}_2\text{T}_x$  flakes, which reveals a more disordered structure compared to the flat dried MXene paper shown in the previous studies [2,21]. From the cross-sectional view of the film in Fig. 2c, a less compact layered structure can be observed. The observed disordered structure is well consistent with the XRD results.

For comparison, the electrochemical performance of the dried  $\text{Ti}_3\text{C}_2\text{T}_x$  film was first explored. The Nyquist plot (Fig. 3a) reveals a low contact resistance at high frequencies due to the compact structure of the film, but the resistance drastically increases when

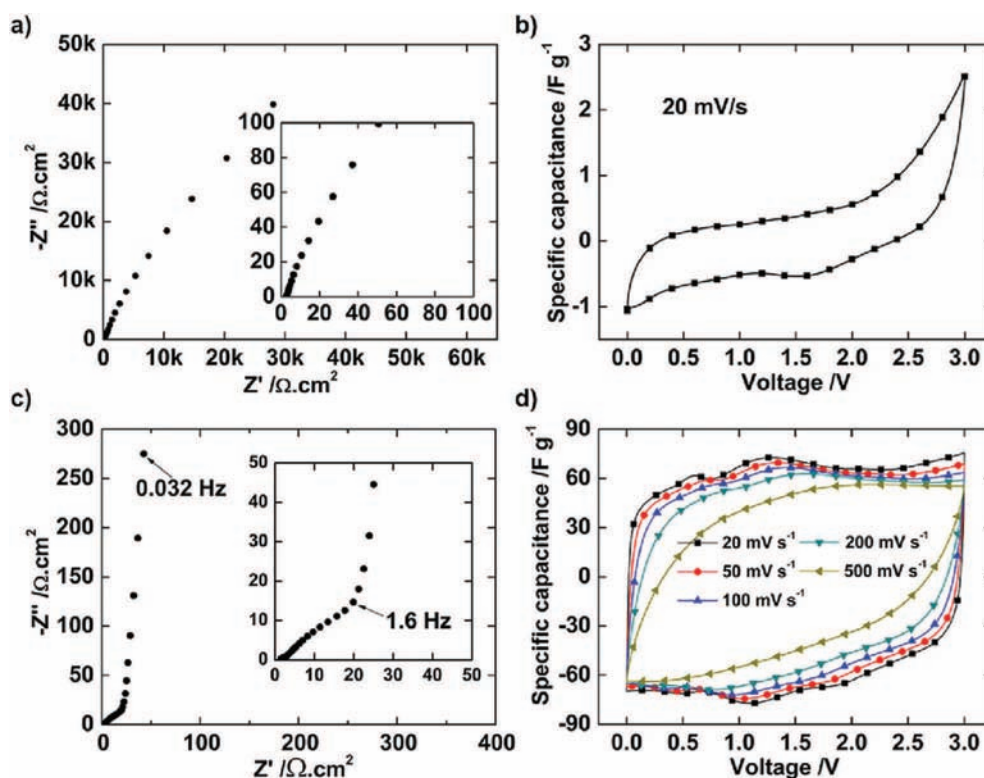

**Fig. 3.** a) Nyquist plot and b) CV of  $\text{Ti}_3\text{C}_2\text{T}_x$  dried film tested in EMI-TFSI ionic liquid electrolyte. Electrochemical characterizations of  $\text{Ti}_3\text{C}_2\text{T}_x$  ionogel film with mass loading of  $0.76 \text{ mg cm}^{-2}$  (mass of  $\text{Ti}_3\text{C}_2\text{T}_x$  only): c) Nyquist plot of a 2-electrode Swagelok cell; d), CVs of a 2-electrode Swagelok cell at scan rate from 20 to  $500 \text{ mV s}^{-1}$  within a voltage window of 3 V.

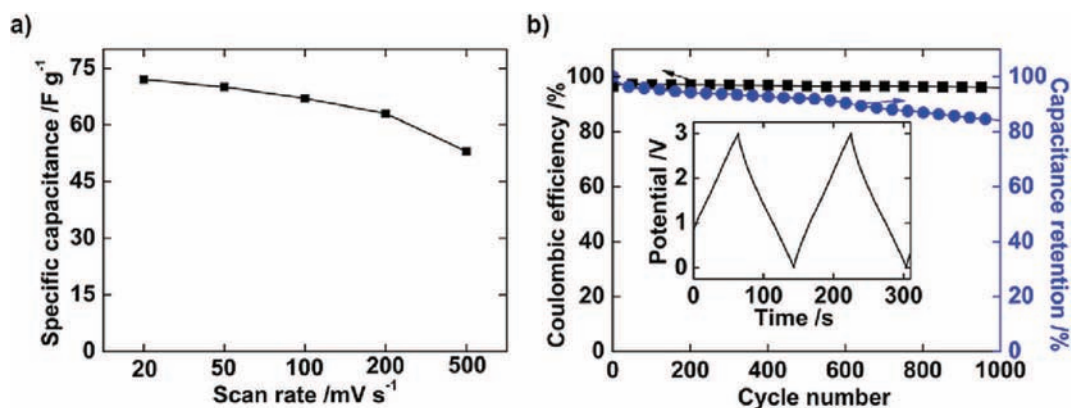


Fig. 4. a) Change of the specific capacitance with scan rate; b) Capacitance retention test of Ti<sub>3</sub>C<sub>2</sub>T<sub>x</sub> film at 1 A g<sup>-1</sup> and coulombic efficiency of 2-electrode Swagelok cell.

the frequency is decreased, evidencing a slow ion dynamics in the electrode (Warburg region). Cyclic voltammograms (CVs) in a 2-electrode cell assembled with two identical electrodes are presented in Fig. 3b. The narrow CVs suggest an extremely low capacitance of less than 1 F g<sup>-1</sup> at a scan rate of 20 mV s<sup>-1</sup>.

Electrochemical performance of the Ti<sub>3</sub>C<sub>2</sub>T<sub>x</sub> ionogel films is presented in Fig. 3c and d. The Nyquist plot (Fig. 3c), shows a low high-frequency series resistance of 1.3 Ω cm<sup>2</sup>; the resistance at the knee frequency is 20 Ω cm<sup>2</sup> corresponding to a resistance of the electrolyte in the MXene electrode of about 19 Ω cm<sup>2</sup> which is in the same range as that reported for graphene electrodes [22,23]. The fast increase of the imaginary part of the impedance at low frequency evidences a capacitive storage mechanism. Fig. 3d shows the CVs of a 2-electrode Swagelok cell assembled with two identical MXene electrodes, at scan rates from 20 mV s<sup>-1</sup> to 500 mV s<sup>-1</sup>. An average specific electrode capacitance of 70 F g<sup>-1</sup> was obtained at a scan rate of 20 mV s<sup>-1</sup> within a voltage window of 3 V. From our knowledge, this is the first report of MXene materials operating in an ionic liquid electrolyte with such a capacitance within a voltage window of 3 V. CVs of Fig. 3d show a set of peaks at about 0.5 V and 1.2 V. Differently from MXene in aqueous electrolytes, such features are not assumed to come from pseudocapacitive contributions of surface functional groups since O- or F- surface groups are not supposed to be electrochemically active in the aprotic ionic liquids [24]. The presence of these current peaks could be assigned to EMI<sup>+</sup> and/or TFSI<sup>-</sup> insertion between the Ti<sub>3</sub>C<sub>2</sub>T<sub>x</sub> layers such as those observed in layered MnO<sub>2</sub> [25,26] or for Ti<sub>3</sub>C<sub>2</sub>T<sub>x</sub> in organic

electrolyte [17]; further in-situ XRD studies (in progress) will be needed to get a better insight of the capacitive charge storage mechanism. The capacitance change with the scan rate is shown in Fig. 4a; 75% of the capacitance is preserved when the scan rate is increased from 20 mV s<sup>-1</sup> to 500 mV s<sup>-1</sup>, which demonstrates the high power capability of the electrodes [27]. Fig. 4b shows the cell voltage variation with time during galvanostatic charge/discharge cycling tests (inset) as well as the related coulombic efficiency and capacitance retention (in %). As observed, after 1000 cycles, capacitance retention is still more than 80% of the initial capacitance while coulombic efficiency remains above 95%.

In addition, a thicker Ti<sub>3</sub>C<sub>2</sub>T<sub>x</sub> ionogel film (400 μm), with a mass loading of 4 mg cm<sup>-2</sup> (mass of Ti<sub>3</sub>C<sub>2</sub>T<sub>x</sub> only) was investigated and found to perform similarly to the thin films. The Nyquist plot (Fig. 5a) shows the change of the imaginary vs. real part of the impedance. The high frequency series resistance is in the same range as that of thinner films (1.1 Ω cm<sup>2</sup>). As expected, the ionic resistance of the Ti<sub>3</sub>C<sub>2</sub>T<sub>x</sub> electrode, calculated from the difference between the knee frequency resistance and the high frequency series resistance, was found to be slightly larger than that of the thinner film (22 Ω cm<sup>2</sup>), which attributed to the larger thickness of the film [28]. A capacitive behavior can be observed from the CV plots in Fig. 5b. A capacitance of 70 F g<sup>-1</sup> was achieved at a scan rate of 1 mV s<sup>-1</sup> within a 3 V voltage window; the electrode was still delivering 90% (62 F g<sup>-1</sup>) of the initial capacitance at 20 mV s<sup>-1</sup>, thus showing decent power performance for this thick film in neat ionic liquid electrolyte.

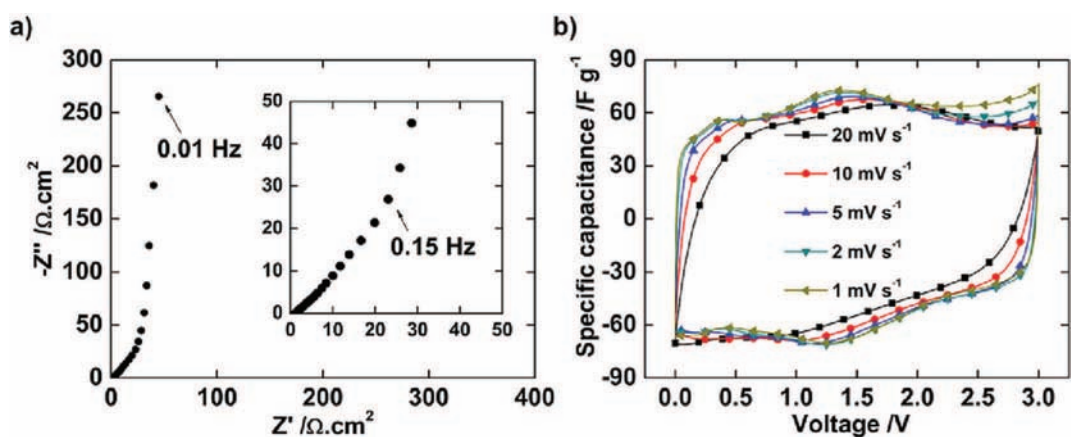


Fig. 5. Electrochemical characterization of thick Ti<sub>3</sub>C<sub>2</sub>T<sub>x</sub> ionogel film with mass loading of 4 mg cm<sup>-2</sup> (mass of Ti<sub>3</sub>C<sub>2</sub>T<sub>x</sub> only): a) Nyquist plot of 2-electrode Swagelok cell; b) CVs of 2-electrode Swagelok cell with voltage window of 3 V.

#### 4. Conclusions

A  $\text{Ti}_3\text{C}_2\text{T}_x$  MXene hydrogel was prepared by vacuum filtration. The hydrogel film was further immersed in EMI-TFSI ionic liquid electrolyte to prevent restacking of the MXene flakes after vacuum drying at 80 °C. Electrochemical performance of the  $\text{Ti}_3\text{C}_2\text{T}_x$  ionogel film in EMI-TFSI ionic liquid electrolyte was compared to a vacuum-dried  $\text{Ti}_3\text{C}_2\text{T}_x$  film. In contrast to the  $\text{Ti}_3\text{C}_2\text{T}_x$  dried film exhibiting an extremely low capacitance of  $1 \text{ F g}^{-1}$  and a highly resistive behavior, the  $\text{Ti}_3\text{C}_2\text{T}_x$  ionogel film shows a capacitance up to  $70 \text{ F g}^{-1}$  at a scan rate of  $20 \text{ mV s}^{-1}$  and a large voltage window of 3 V thanks to the disordered structure and larger  $\text{Ti}_3\text{C}_2\text{T}_x$  interflake spacing. The capacitive signature is preserved at high scan rates ( $500 \text{ mV s}^{-1}$ ), suggesting high power performance as well. A thick  $\text{Ti}_3\text{C}_2\text{T}_x$  ionogel film with high mass loading of  $4 \text{ mg cm}^{-2}$  shows a lower gravimetric capacitance of  $62 \text{ F g}^{-1}$  at a scan rate of  $20 \text{ mV s}^{-1}$ . To our knowledge, this is the first report on MXene hydrogel and also using MXene materials in an ionic liquid electrolyte, in which superior performance was achieved. Considering the rich chemistry of many other MXene materials, we can envisage further improvement by using MXenes in various ionic liquid electrolytes for supercapacitors.

#### Acknowledgements

Z. F. LIN was supported by China Scholarship Council (CSC). P. S. acknowledges the support from European Research Council (ERC, Advanced Grant, ERC-2011-AdG, Project no. 291543-IONACES). K. L. Van Aken and Y. Gogotsi were supported as part of the Fluid Interface Reactions, Structures and Transport (FIRST) Center, an Energy Frontier Research Center funded by the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences.

#### References

- [1] M. Ghidui, M.R. Lukatskaya, M.-Q. Zhao, Y. Gogotsi, M.W. Barsoum, *Nature* 516 (2014) 78–81.
- [2] B. Anasori, Y. Xie, M. Beidaghi, J. Lu, B.C. Hosler, L. Hultman, P.R.C. Kent, Y. Gogotsi, M.W. Barsoum, *ACS Nano* 9 (2015) 9507–9516.
- [3] M. Naguib, Y. Gogotsi, *Accounts Chem. Res.* 48 (2015) 128–135.
- [4] M. Naguib, V.N. Mochalin, M.W. Barsoum, Y. Gogotsi, *Adv. Mater.* 26 (2014) 992–1005.
- [5] M. Naguib, J. Come, B. Dyatkin, V. Presser, P.-L. Taberna, P. Simon, M.W. Barsoum, Y. Gogotsi, *Electrochem. Commun.* 16 (2012) 61–64.
- [6] M. Naguib, J. Halim, J. Lu, K.M. Cook, L. Hultman, Y. Gogotsi, M.W. Barsoum, *J. Am. Chem. Soc.* 135 (2013) 15966–15969.
- [7] O. Mashtalir, M.R. Lukatskaya, M.Q. Zhao, M.W. Barsoum, Y. Gogotsi, *Adv. Mater.* 27 (2015) 3501–3506.
- [8] Z.Y. Lin, D.F. Sun, Q. Huang, J. Yang, M.W. Barsoum, X.B. Yan, *J. Mater. Chem. A* 3 (2015) 14096–14100.
- [9] D.D. Sun, M.S. Wang, Z.Y. Li, G.X. Fan, L.Z. Fan, A.G. Zhou, *Electrochem. Commun.* 47 (2014) 80–83.
- [10] D. Er, J. Li, M. Naguib, Y. Gogotsi, V.B. Shenoy, *ACS Appl. Mater. Interfaces* 6 (2014) 11173–11179.
- [11] M.R. Lukatskaya, O. Mashtalir, C.E. Ren, Y. Dall'Agnese, P. Rozier, P.L. Taberna, M. Naguib, P. Simon, M.W. Barsoum, Y. Gogotsi, *Science* 341 (2013) 1502–1505.
- [12] M. Hu, Z. Li, H. Zhang, T. Hu, C. Zhang, Z. Wu, X. Wang, *Chem. Commun.* 51 (2015) 13531–13533.
- [13] X. Wang, S. Kajiyama, H. Iinuma, E. Hosono, S. Oro, I. Moriguchi, M. Okubo, A. Yamada, *Nat. Commun.* 6 (2015) 1–6.
- [14] H.-W. Wang, M. Naguib, K. Page, D.J. Wesolowski, Y. Gogotsi, *Chem. Mat.* (2015) 349–359.
- [15] M.-Q. Zhao, C.E. Ren, Z. Ling, M.R. Lukatskaya, C. Zhang, K.L. Van Aken, M.W. Barsoum, Y. Gogotsi, *Adv. Mater.* 27 (2015) 339–345.
- [16] P. Yan, R. Zhang, J. Jia, C. Wu, A. Zhou, J. Xu, X. Zhang, *J. Power Sources* 284 (2015) 38–43.
- [17] Y. Dall'Agnese, P. Rozier, P.-L. Taberna, Y. Gogotsi, P. Simon, *J. Power Sources* 306 (2016) 510–515.
- [18] M. Armand, F. Endres, D.R. MacFarlane, H. Ohno, B. Scrosati, *Nat. Mater.* 8 (2009) 621–629.
- [19] M.A. Hope, A.C. Forse, K.J. Griffith, M.R. Lukatskaya, M. Ghidui, Y. Gogotsi, C.P. Grey, *Phys. Chem. Chem. Phys.* 18 (2016) 5099–5102.
- [20] T.N. Blanton, D. Majumdar, *Powder Diffr.* 27 (2012) 104–107.
- [21] M. Naguib, O. Mashtalir, J. Carle, V. Presser, J. Lu, L. Hultman, Y. Gogotsi, M.W. Barsoum, *ACS Nano* 6 (2012) 1322–1331.
- [22] W.Y. Tsai, R.Y. Lin, S. Murali, L.L. Zhang, J.K. McDonough, R.S. Ruoff, P.L. Taberna, Y. Gogotsi, P. Simon, *Nano Energy* 2 (2013) 403–411.
- [23] Z. Lin, P.-L. Taberna, P. Simon, *Electrochim. Acta* (2015), <http://dx.doi.org/10.1016/j.electacta.2015.12.097> (in press).
- [24] E. Kowsari, High-performance supercapacitors based on ionic liquids and a graphene nanostructure, in: S. Handy (Ed.), *Ionic Liquids – Current State of the Art*, InTech, 2015, pp. 505–542.
- [25] J.-K. Chang, M.-T. Lee, W.-T. Tsai, M.-J. Deng, I.W. Sun, *Chem. Mat.* 21 (2009) 2688–2695.
- [26] T.M. Benedetti, F.F.C. Bazito, E.A. Ponzio, R.M. Torresi, *Langmuir* 24 (2008) 3602–3610.
- [27] D. Chunsheng, P. Ning, *Nanotechnology* 17 (2006) 5314.
- [28] P.L. Taberna, P. Simon, J.F. Fauvarque, *J. Electrochem. Soc.* 150 (2003) A292–A300.