

Metal provenance of Iron Age Hacksilber hoards in the southern Levant

Liesel Gentelli, Janne Blichert-Toft, Gillan Davis, Haim Gitler, Francis Albarède

▶ To cite this version:

Liesel Gentelli, Janne Blichert-Toft, Gillan Davis, Haim Gitler, Francis Albarède. Metal provenance of Iron Age Hacksilber hoards in the southern Levant. Journal of Archaeological Science, 2021, 10.1016/j.jas.2021.105472 . hal-03327707

HAL Id: hal-03327707

https://hal.science/hal-03327707

Submitted on 27 Aug 2021

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Metal provenance of Iron Age *Hacksilber* hoards in the southern

Levant 2 3 Liesel Gentelli^{1*}, Janne Blichert-Toft¹, Gillan Davis², Haim Gitler³, and Francis Albarède¹ 4 5 6 ¹ Ecole Normale Supérieure de Lyon, CNRS, and Université de Lyon, France ² Australian Catholic University, Sydney, Australia 7 8 ³ The Israel Museum, Jerusalem, Israel 9 10 * Corresponding author: Liesel Gentelli; liesel.gentelli@ens-lyon.fr lagentelli@gmail.com 11 12 **Abstract** Hacksilber facilitated trade and transactions from the beginning of the second millennium 13 14 BCE until the late fourth century BCE in the southern Levant. Here we demonstrate the use of 15 new, data-driven statistical approaches to interpret high-precision Pb isotope analysis of silver found in archaeological contexts for provenance determination. We sampled 46 pieces of 16 17 Hacksilber from five hoards (Megiddo Area H, Eshtemoa, Tel Dor, 'En Gedi, and Tel Migne-18 Ekron) and combined our data with recent literature data for the same hoards plus five more 19 (Beth Shean, Ashkelon, Tell Keisan, Tel 'Akko, and 'En Hofez) thus covering silver from the 20 Late Bronze Age III (c.1200 BCE) to the end of the Iron Age IIC (586 BCE). 21 22 Samples were taken by applying a new minimally destructive sampling technique. Lead was 23 extracted using anion-exchange chromatography and Pb isotopic compositions were measured 24 by MC-ICP-MS. Data were treated using a new clustering method to identify statistically 25 distinct groups of data, and a convex hull was applied to identify and constrain ore sources 26 consistent with the isotopic signature of each group. Samples were grouped by minimizing 27 variance within isotopic clusters and maximizing variance between isotopic clusters. 28 29 We found that exchanges between the Levant and the Aegean world continued at least 30 intermittently from the Late Bronze Age through to the Iron Age III, demonstrated by the 31 prevalence of Lavrion (Attica), Macedonia, Thrace (northern Greece), Southern Gaul 32 (southern France), and Sardinia as long-lived major silver sources. Occasional exchanges with 33 other west Mediterranean localities found in the isotopic record demonstrate that even though 34 the Aegean world dominated silver supply during the Iron Age, exchanges between the 35 eastern and the western Mediterranean did not altogether cease. The mixture of silver sources

within hoards and relatively low purity of silver intentionally mixed with copper and arsenic suggest long-term hoarding and irregular, limited supply during the Iron Age I.

1. Introduction

Hacksilber is irregularly cut silver bullion made from broken pieces of silver ingots, jewelry, and other pieces of scrap silver. It served as a store of wealth and means of payment in the Ancient Near East for thousands of years. Used in local and international transactions, the value of Hacksilber was determined by weighing it on scales against standardized weights presumably allowing for the purity of silver. Evidence exists of cupellation being used for silver extraction since the fourth millennium BCE at sites in Greater Mesopotamia (Helwing, 2014), and Hacksilber itself has been discovered in archaeological excavations in the region (for Middle Bronze Age II Hacksilber hoards see Kletter, 2003:148; Thompson, 2009 for Early Iron Age I hoards). In the southern Levant, Hacksilber facilitated trade and transactions from the beginning of the second millennium BCE (Kletter, 2003:148) until the late fourth century BCE (Farhi, 2014), with mixed hoards composed mainly of uncut coins supplemented by Hacksilber in equal or greater quantities (Gitler, 2006). A hoard allegedly found in the vicinity of Samaria illustrates that the practice of using cut coins alongside Hacksilber continued into the second half of the fourth century BCE (Gitler, 2006).

Hacksilber hoards have been found in excavations throughout the southern Levant in:

- Ceramic containers e.g. 'En Gedi (Kletter and De Groot, 2007), Eshtemoa (Kletter and Brand, 1998), 'En Ḥofez (Thompson and Skaggs, 2013), Tel 'Akko (Thompson and Skaggs, 2013), and Tel Miqne-Ekron (Golani and Sass, 1998).
- Bundles wrapped in linen bags and kept in ceramic containers e.g. Megiddo
 Area H (Arie et al., 2019), Tell Keisan (Thompson and Skaggs, 2013), and Tel
 Dor (Shalev et al., 2014).
- Bundles wrapped in linen bags e.g. Tel Beth-Shean (Thompson, 2009),
 Ashkelon (Thompson, 2020), and Tel Migne-Ekron (Golani and Sass, 1998).
- Assemblages where no remains of the container or the textile bag have been found – e.g. Tel Miqne-Ekron (Golani and Sass, 1998) and Beth Shean (Thompson, 2009).

67 Recent research into *Hacksilber* has mostly concentrated on two questions. First, the extent to 68 which *Hacksilber* filled the functions of money prior to the invention of coinage (Stos-Gale, 69 2001; Thompson, 2003; Eshel et al., 2018). Second, identifying its silver sources with a focus 70 on determining when and to what extent the Phoenicians were engaged in long-distance silver 71 trade prior to their colonisation of the western Mediterranean (Thompson, 2003; Thompson 72 and Skaggs, 2013; Murillo -Barroso et al., 2016; Eshel et al., 2019; Wood et al., 2019; Gitler 73 and Tal, 2020; Eshel et al., 2021). 74 Arguably, the Hebrew phrase bz 'ksp, meaning "intentionally cut pieces of silver", was the 75 76 biblical term for money itself (cf. Judges 5:19). The bundling of *Hacksilber* evoking the 77 biblical expression "pouch of silver" (zrwr ksp, Genesis 42:35) has led to the contention that it 78 functioned as money (Thompson (2003) or at least as pre-coinage (Gitin and Golani, 2001; 79 Silver, 2006; Kroll, 2008; Gestoso-Singer, 2013, 2015; Heymans, 2018a). Eshel et al. (2018; 80 2019) addressed this by investigating the context, chronology, weight, and typology of the 81 Hacksilber, and comparing this information with a subset of major and minor elemental 82 compositions. They found that neither the weight nor the fineness, that is the quality and the 83 quantity of *Hacksilber*, are sufficiently consistent to support the theory that *Hacksilber* was a 84 precursor to coinage. Rather, it would appear that the Phoenician perspective on silver before 85 the 5th century BCE was to treat it as a commodity, not a currency (Gitler and Tal, 2006; Elayi and Elayi, 2009; Van Alfen, 2002; Albarède et al., 2020). This is an important finding which 86 87 matches Davis' (2012) conclusions about contemporary Archaic Athenian Greek use of 88 Hacksilber and goes to the question of whether there was an adequate and reliable supply of 89 silver to make true monetary use viable. If there was, then the expectation would be mostly 90 homogeneous hoards especially within the bundles, a question tested in this research. 91 Albarède et al (2021) further investigate the apparent resistance to the adoption of money in 92 the Western Mediterranean, tracing silver refining techniques in the region using lead and 93 silver isotope analysis. 94 95 Eshel et al. (2021) raise the point of whether systematic debasement by copper and arsenic 96 during the period 1200-950 BCE in the southern Levant was intentional or just common 97 economic practice in a region that could only acquire silver from abroad. They argue that the 98 use of arsenic (up to 4.6 wt.% in Megiddo Area H) to maintain a silvery shine indicated 99 deliberate debasement. However, there is no evidence to support Eshel et al.'s statement that 100 "the local administrations initiated sophisticated devaluation methods to compensate for the

101 lack of silver", and full-scale tampering with all silver circulating in the southern Levant in its 102 various forms is unlikely. An equally reasonable assumption is that relatively low-quality 103 silver alloys were broadly accepted during the Late Bronze to Iron Age transition period. 104 Understanding silver sources and thus trade routes in use at the time will help in better 105 understanding this phenomenon. 106 107 The focus of the present research is on Iron Age *Hacksilber* hoards in the southern Levant 108 when the geopolitical circumstances were different from the preceding Late Bronze Age. 109 Material found in controlled archaeologically excavated hoards and single finds provides the 110 best evidence because it has secure contexts. Research questions for this study to be addressed 111 by Pb isotopic analysis are: 112 1. How many silver sources were there, and which ones can be identified? 113 2. Do the silver sources change with time? 114 3. To what extent is the silver in each hoard internally homogenous? 115 The hoards described in this work have been dated based on their archaeological context, and 116 a generally agreed ceramic pottery typology (Mazar, 2011). For a description of the 117 methodology behind the dating of each hoard see Eshel et al. (2018; 2021). For details of the 118 archaeological context and relative dating for individual sites see Rowe (1940) (Beth Shean), 119 Arie et al. (2019) (Megiddo Area H), Balmuth (2001 p.15) (Ashkelon), Nodet (1980 pp. 323-120 326) (Tell Keisan), Stern (1998) and Shalev et al. (2014) (Tel Dor), Thompson and Skaggs 121 (2013) (Tel 'Akko), Alexandre (1997 p. 53) ('En Hofez), Kletter and Brand (1998) 122 (Eshtemoa), Golani and Sass (1998) and Gitin and Golani (2001) (Tel Migne-Ekron), and 123 Kletter and De Groot (2007) ('En Gedi). For a broader understanding of the hoards in relation 124 to each other see Thompson (2003) and Eshel et al. (2018). The Bronze Age and Iron Age are 125 convenient constructs understood to start and end at different times in different places. In the 126 southern Levant, the Bronze Age is considered to end around 1200 BCE with the cultural 127 collapse of the dominant states, and the Iron Age ends in 586 BCE marked by the Babylonian 128 conquest and destruction of the temple in Jerusalem. Within these two periods are separations 129 into shorter time phases (e.g. Iron Age I, Iron Age II), which can be further divided (e.g. Iron 130 Age IIA, Iron Age IIB, Iron Age IIC). The dates associated with each division remain 131 intensely debated (e.g. Gilboa et al., 2008; Finkelstein and Piasetzky, 2011; Mazar, 2011), 132 with ranges for the transition between each period being accepted within 'low' and 'high'

chronologies. The time periods are being tightened as further data are gathered in

134 archaeological excavations, especially by radiometric dating (Webster, 2015), but the exact 135 dating does not affect the arguments presented in this paper. 136 Lead isotope analysis of *Hacksilber* hoards has been conducted before, most notably through 137 the 'Hacksilber Project' undertaken by Balmuth and Thompson with Stos-Gale (Stos-Gale, 138 2001; Stos-Gale and Gale, 2012). These data were produced by thermal-ionization mass 139 spectrometry (TIMS), which does not control analytical mass bias as efficiently as multiple-140 collector inductively-coupled plasma mass spectrometry (MC-ICP-MS). The 'Hacksilber 141 Project' publication included a chapter on lead isotope analysis of excavated *Hacksilber* at Tel 142 Migne-Ekron, Shechem, and Selinus (Stos-Gale, 2001). When interpreting results from lead 143 isotope analysis in these *Hacksilber* hoards, Stos-Gale observed that they are consistent with 144 lead isotope ratios of ores from the Aegean, Spain, and Iran. A further observation made by 145 Stos-Gale was that the data did not support a hypothesis of widespread mixing, positing that 146 melting and re-casting was done on individual objects on a small scale. Stos-Gale pointed out 147 that a silver object of unknown provenance can only be assigned an ore source if data from 148 that ore source exist and called for further lead isotope analyses of *Hacksilber*. 149 150 Stos-Gale's conclusions were re-examined by Thompson and Skaggs (2013) for hoards from 151 Tel 'Akko, Tel Dor, 'En Hofez, and Tell Keisan against geological data from the Forum of the 152 European Geological Surveys (FOREGS) Geochemical Baseline Mapping program. 153 Thompson and Skaggs concluded that at least one sample from each of the *Hacksilber* hoards 154 under consideration could have lead isotope ratios consistent with those of silver-bearing ores 155 from Sardinia and southern France and inconsistent with Aegean and Anatolian sources. 156 Apparent in this paper and elaborated on in Thompson's unpublished "A Brief History of 157 Hacksilber Project Research" (2017), is the criticism of previous assumptions that Hacksilber 158 was unlikely to originate in the western Mediterranean. Further, with regards to the problem 159 of mixing, Thompson (2017) asserted that even before 800 BCE silver sources were multiple 160 and bullion travelled long distances. 161 162 Eshel et al. (2019) analysed numerous pieces of *Hacksilber* from the same hoards analysed by 163 Stos-Gale (2001) for lead isotope composition, comparing their results to lead isotope 164 compositions of silver-bearing ores available in the Oxford Archaeological Lead Isotope 165 Database (OXALID). The study focused on the hoards from Tel Dor, Tel 'Akko, 'En Hofez, 166 and Eshtemoa. The authors were critical of Thompson and Skaggs (2013) for assuming that

Hacksilber hoards were not mixed. They suggested that Hacksilber from Tel Dor and Tel 'Akko originated from both Anatolia and Sardinia, while Hacksilber from 'En Ḥofez and Eshtemoa originated from Iberia (Spain). Based on the chronology of these hoards, they proposed that the Phoenicians brought knowledge of silver refining acquired in Anatolia to tribes in Iberia in the mid-10th century BCE, 150 to 200 years prior to Phoenician settlement in Iberia. However, while the data may be consistent with the conclusions, they do not necessarily go so far as to support them.

174175

176

177

178

179

180

181

182

183

184

185

186

187

188

189

190

191

192

193

194

195

196

197

198

199

200

167

168

169

170

171

172

173

Wood et al. (2019) used lead isotope analysis to further investigate whether *Hacksilber* silver sources were mixed. They re-examined the lead isotope ratios in *Hacksilber* produced by Stos-Gale (2001) against compositional data. Wood et al. (2019) proposed a comparison of the crustal age of the metal calculated from the lead isotope ratios against the compositional ratio of gold to silver. Where the gold to silver ratio did not match the crustal age, Wood et al. (2019) proposed that mixing of silver from different sources is evident. In this way, mixing lines were identified, and the authors proposed considerable mixing between several potential ore sources. The authors used the chronology of the hoards, identified via their archaeological contexts, to suggest where and when mixing of silver may have taken place. The study focused on the use of mixing lines to identify mixing events, with only some of the endmember clusters identified in terms of geological sources. Crucially, the authors noted that further work is needed to contextualize their findings, acknowledging that apart from the archaeological chronology, there is little evidence to support where or when potential mixing took place. The authors applied their proposed methodology in Wood et al. (2020) by reanalysing legacy lead isotope data from Stos-Gale (2001) in order to determine the source(s) of the Tel Dor Hacksilber hoard. The authors concluded that the Phoenicians learned silver refining in Cyprus, rather than Anatolia as Eshel et al. (2019) had suggested, and introduced the methodology to Iberia. The authors further suggested that silver objects which were previously identified as having originated from Thera, Kythnos, or Cyprus (Wood et al., 2019) are in fact silver mined at Kalavasos in Cyprus, or lead used for cupellation of silver from a different, so-far unidentified source. These conclusions are unsupported. The geochemistry of ores on the islands of Kythnos and Thera is inconsistent with significant silver production. As to the silver extraction from the ores in Kalavassos, one of the copper mines of Cyprus, this speculation is also unfounded. Even though intrusions of porphyries are ubiquitous from the Aegean to modern Afghanistan and contain substantial traces of silver (Zürcher et al., 2019), the historical context shows that silver from these ores could never

compete with peri-Aegean mines. A simple interpretation is technological: Cu and Ag form a eutectic barrier at 28% Cu (Baker, 1992) making silver purification by cupellation of Cu-rich alloys a major hurdle. This problem does not exist with Ag-Pb alloys. In a more geological context, finding Ag and Pb ores in Cyprus, a textbook example of an ophiolite, would be very unexpected.

Eshel et al. (2019; 2021) conducted further research on *Hacksilber* using lead isotope

analysis, with the premise that interpretations based on lead isotopes can be further refined using elemental compositions. The elements they considered diagnostic are Cu (<5.5%), Pb, Au, and Bi, which may be indicative of silver that has been cupelled, and Co, Ni, Zn, and Sn, the absence of which likewise is indicative of silver that has been cupelled but the presence of which is consistent with the addition of smelted copper. A caveat, however, is that some elements (Zn, Bi, As) (Honig, 1969) are more volatile than silver and, according to Henry's Law, should be at least partially lost during the metallurgical process. Arsenic and antimony were also considered carefully, as they may have been added intentionally to the alloy, and not introduced via the addition of copper. All compositional data were collected using quadrupole ICP-MS. Rather than using compositional information for provenance determination, this information was directed towards identifying mixing and alloying. When various mixes or alloys were identified, the results were placed within their specific archaeological context (particularly hoard location and approximate date of deposition) to draw conclusions about the broader political situation at the time. Their key claim was that high copper contents in *Hacksilber* date from around the Bronze Age collapse (c.1200 BCE) correlated with a purported end to ready access to Aegean silver in the Levant due to break down of trade connections. They proposed that a perceived influx of silver from Anatolia and the West Mediterranean (based on lead isotope results in Eshel et al., 2019) is reflected in considerably lower copper contents in *Hacksilber* deposited after approximately 950 BCE.

As discussed in the literature, a geological perspective is crucial to understanding lead isotope analysis of archaeological objects (Albarède et al., 2012; Blichert-Toft et al., 2016; Albarède et al., 2020). The advantage of using the geological perspective approach, which involves calculating Pb model ages and time-integrated parent-daughter (U/Pb) and parent-parent (Th/U) ratios from measured Pb isotope data, is that it is data driven and is performed independently of any archaeological or numismatic conclusions drawn about the samples. The former set of evidence thereby complements the latter two in an objective manner. As a

caveat, mixing trends are linear only if the x and y axis denominators are identical, as in Pb-Pb isotopic plots. Lead model ages are, to a first approximation, proportional to 207 Pb/ 206 Pb (Albarède et al., 2021) and mixing lines using Pb model ages vs elemental ratios such as Au/Ag (e.g. Figs. 4 and 6 in Wood et al., 2019) are strongly curved as a function of the Pb contents of the coins. Mixing patterns, therefore, should be interpreted with the utmost caution.

Prior attempts of provenance calculations have relied on one-to-one comparisons between individual ores and *Hacksilber* fragments (Thompson and Skaggs, 2013; Delile et al., 2014; Westner et al., 2020). Our approach is different. We provide 46 new high-precision Pb isotope compositions of *Hacksilber* fragments from seven southern Levantine hoards and combine them with Eshel et al.'s (2019; 2021) data. Eshel et al.'s data were all obtained by MC-ICP-MS, as were the new data of this study, hence justifying the merging of the two data sets. We further apply a new, more encompassing approach to statistically interpret the data, based on 'convex hulls' of the 3-dimensional Pb isotope data of each hoard (i.e., the smallest convex volume that contains the data). By using a data-driven approach to the statistical interpretation of lead isotope data, combined with lead isotope data for likely ore sources, we identify which ore sources could have contributed to the *Hacksilber* hoards and determine the homogeneity of silver sources for each hoard. By then combining these data with the archaeological chronology of the hoards in question, we identify changes in silver sources over time.

2. Materials

Thirty-four *Hacksilber* hoards dating to the Iron Age (c.1200-600 BCE) from 15 different sites in Israel and under the control of the Palestinian Authority were identified by Thompson as part of her '*Hacksilber* Project' (2017). The 13 sites listed in Table 1 were selected for the present research project to provide representative samples from the end of the Late Bronze Age through the Iron Age, from different find-spots in the southern Levant, which can best answer the research questions identified in this paper. There is a strong focus on the rich material from the seventh century sites of Tel Miqne-Ekron, with its multiple hoards, and 'En Gedi, as this was the century when coined money was invented and monetary use of *Hacksilber* might be expected.

 $Table\ 1-Hoards\ selected\ for\ analysis\ (for\ the\ description\ and\ dating\ of\ these\ hoards\ see$ $Heymans\ ,\ 2018b,\ pp.\ 256\text{-}269)$

Hoard	Period	Approximate date (BCE)	Contents	Sampled for new lead isotope analysis	Previous lead isotope analysis available in the literature
Beth Shean 10704 (L.88866)	Late Bronze Age III	1200-1150	Cut ingots, wires, broken jewellery stored in a bundle	0	13 (Eshel <i>et al.</i> 2021)
Megiddo Area H	Iron Age I	1070	3 linen-wrapped bundles of <i>Hacksilber</i> - cut ingots, jewellery	5	13 (Eshel <i>et al</i> . 2021)
Beth Shean 1095	Iron Age I	1150-950	Ingots, wires and jewellery stored in a bundle	0	5 (Eshel <i>et al</i> . 2021)
Megiddo 2012	Iron Age I	1050-950	Cut ingots, sheet fragments, and jewelry stored in three bundles	0	11 (Eshel <i>et al</i> . 2021)
Ashkelon	Iron Age I	1050-950	2 linen-wrapped bundles of <i>Hacksilber</i>	0	12 (Eshel et al. 2021)
Tell Keisan	Iron Age I	1050-950	Silver fragments including sheet silver + jewellery stored in a single jar	0	20 (Eshel <i>et al</i> . 2021)
Tel Dor	Iron Age IIA	2nd half of 10 th century	17 linen-wrapped bundles of <i>Hacksilber</i> stored in a single jar + ingots	14	34 (Eshel <i>et al.</i> 2019)
Tel `Akko	Iron Age IIA	10 th -9 th centuries	Cut ingots, tokens, wires, sheets stored in a juglet	0	12 (Eshel <i>et al.</i> 2019)
Beth Shean 1029a and b	Iron Age IIA	950-800	Jewellery and ingots store in a ceramic vessel	0	15 (Eshel <i>et al</i> . 2021)
En Ḥofez	Iron Age IIA	9 th century	Hacksilber, ingots + some jewellery stored in 3 jugs	0	29 (Eshel <i>et al</i> . 2019)
1029a and ba and b					
Eshtemoa	Iron Age IIB	8 th century	Hacksilber, ingots + jewellery stored in five jugs	5	0
Tel Miqne-Ekron	Iron Age IIC	Late 7th-early 6th century	Hacksilber, ingots, jewellery + a foundation deposit. Hoards 1, 3 and 5 were stored in a jug, Hoard 2 shows traces of textile impressions, Hoard 4 was found as an assemblage and Hoard 6 was covered by an overturned bowl.	16	0
En Gedi	Iron Age IIC	Late 7th-early 6th century	62 pieces of silver, mostly ingots stored in a cooking pot	5	0
	<u> </u>		Total	45	164*

Pre-MC-ICP-MS legacy data is dominated by more 'noise', and therefore less precision, than data from the MC-ICP-MS era. Precision and accuracy of early (pre-2000) TIMS and modern MC-ICP-MS Pb isotopic data may differ by up to two orders of magnitude. Furthermore, the archaeological literature tends to reference the data relative to ²⁰⁴Pb (e.g. Eshel et al., 2018; 2019; 2021), which is the least abundant isotope rather than, for example, ²⁰⁶Pb or ²⁰⁸Pb (Albarède et al., 2012; 2020). When lead isotope data are examined using ²⁰⁴Pb as the denominator on both the x and y axes, 'noise' is greater and, hence, precision is poorer. Interpreting geological provenance from data represented in this way, therefore, is not ideal. In order to avoid merging data of heterogeneous quality in the same database, ²⁰⁴Pb-referenced legacy data as well as Pb isotope data measured by TIMS, mostly from the OXALID database (which includes *Hacksilber* data published in Stos-Gale, 2001), have not been included in this study. This choice does not imply that the inclusion of these data would have modified the conclusions reached here but was made to limit the present assessment to high-precision data only. The merging of our data with those of Eshel et al. (2019; 2021) is justified by their similar level of precision acquired via solution purification chemistry and

3. Methods

3.1. Artefact sampling

MC-ICP-MS measurement.

All samples were etched on their edges using a novel technique (Milot et al., 2021) which removes only a few micrograms of material, less than one-millionth the total weight of the object (or less depending on the size of the object in question). To briefly summarize the technique, the artefact is rolled for about 90 seconds onto a strip of chromatographic paper impregnated with a solution of H₂O₂, NH₄OH, and H₂O in the proportions of 1:1:1 using a custom-made set of felt-covered pliers (Milot et al., 2021). In cases where the shape of the object does not permit rolling, such as is often the case with unevenly shaped *Hacksilber*, a cotton bud is used instead of the pliers and chromatographic paper. The strips and cotton buds were air-dried under an IR lamp and placed into clean 10 mL centrifuge tubes, which were closed tightly with screw lids and wrapped in multiple layers of film for transportation back to the Lyon clean laboratory for Pb separation and isotopic analysis (as artefacts were usually sampled on-site in a distant museum). There, 10 mL double-distilled 1M HBr, for which Pb has strong affinity, were added to the tubes, thereby submerging the strips (or cotton buds) which were subsequently left to leach at ambient temperature for 24 hours. The HBr

303	containing the Pb leached from the strips (or cotton buds) was then transferred to a clean
304	Savillex (PFA) beaker and evaporated to dryness on a hotplate at approximately 130°C.
305	Meanwhile, the HBr-leached strips (or cotton buds) were submerged in 10 mL distilled 0.5M
306	HNO ₃ and left to leach further at ambient temperature for another 24 hours. The HNO ₃ was
307	transferred to the same beakers containing the now dried-down HBr solutions and evaporated
308	to dryness under the same conditions.
309	3.2 Lead purification
310	Lead was eluted from the samples following a one-step anion-exchange (AG1-X8, 100-200
311	mesh) column chromatography protocol. The dry residues from the leaching procedure were
312	dissolved in 1 mL double-distilled 1M HBr, and alternately heated at 110°C on a hotplate and
313	placed in an ultrasonic bath to ensure total dissolution. The cooled-down samples were loaded
314	onto the anion-exchange columns, the sample matrix eluted with 1M double-distilled HBr,
315	and Pb subsequently collected with 6M distilled HCl. The Pb fractions were evaporated to
316	dryness at approximately 110°C, redissolved with a few drops of concentrated distilled HNO ₃
317	to remove any traces of HBr and organic material, dried down again and finally dissolved in 1
318	mL distilled 0.05M HNO ₃ with 5 ppb Tl prior to Pb isotope analysis.
319	3.3 Lead isotope analysis
320	Lead isotope analysis was done using a Nu Plasma 500 HR MC-ICP-MS at the Ecole
321	Normale Supérieure de Lyon. Blichert-Toft et al. (2003) and White et al. (2000) describe the
322	analytical method of Pb isotope analysis by MC-ICP-MS in detail. Instrumental mass bias was
323	corrected with added Tl using the reference values for Tl and Pb of Eisele et al. (2003).
324	Sample-standard bracketing relative to the NIST 981 Pb standard, which was run
325	systematically every two samples throughout each analytical session, further ensured the
326	accuracy of the measured Pb isotope compositions of the unknowns. The repeated
327	measurements of NIST 981 yielded an external reproducibility of 30-100 ppm (0.003-0.01%)
328	for 204 Pb-normalized ratios and of 6 ppm (0.0006%) for 207 Pb/ 206 Pb and 208 Pb/ 206 Pb.
329	Estimation of internal analytical uncertainties was based on the measurement of 60 isotope
330	ratios with 10 seconds integration time for each sample and standard expressed as twice the
331	standard deviation (2SD). The Pb isotope data of the 46 Hacksilber samples analyzed in this
332	study are listed in Supplementary Table S1.
333	3.4. Parameter calculation and statistical analysis
334	Traditionally in archaeometric research, lead isotopes are used for provenance determination
335	

the geologically-informed approach proposed by Albarède et al. (2012) and further developed in Albarède et al. (2020) to explore Pb model ages $T_{\rm mod}$ and the $^{238}{\rm U}/^{204}{\rm Pb}$ (μ) and $^{232}{\rm Th}/^{238}{\rm U}$ (κ) parameters of each sample.

336

337

338

339

340

341

342

343

344

345

346

347

348

349

350

351

352

353

354

355

356

357

358

359

360

361

362

363

364

365

366

367

368


369

3.5. Provenance assessment In previous studies (e.g. Delile et al., 2014; Westner et al., 2020), the 'consistencies' (Thompson and Skaggs, 2013) are established by testing the error-weighted or unweighted distance between a particular ore and a particular archaeological sample in one of the 3dimensional spaces of Pb isotopes (with isotopic ratios preferentially normalized to ²⁰⁶Pb to avoid the strong correlations arising from ²⁰⁴Pb-normalized ratios; see Albarède et al., 2020). The pair-wise approach ignores the fact that ore data tend to form regionally coherent populations, which the geologically-informed parameters (model age T_{mod} , μ , and κ) clearly confirm (Blichert-Toft et al., 2016; Milot et al., in press). These groups must, in one way or another, manifest themselves in the *Hacksilber* Pb isotope record. Here we adopted the alternative strategy of detecting the ores that are consistent with the range of Pb isotopic ratios defined by the samples. This led us to introduce the concept of the 'sample convex hull', which is the smallest volume in the 3-dimensional space of isotopic ratios which contains all the sample values. As a preliminary step, we used the standard clustering technique applied to Iberian galenas by Albarède et al. (2020) with the expectation that distinct isotopic groups would be found. The next step consisted in separating the data within each hoard into distinct groups, typically one to three as a function of the number of samples. At that point, a convex volume circumscribing the points of the group, known as a convex hull and meshed with tetrahedra, is calculated by Delaunay triangulation (e.g. Aurenhammer et al., 2013) (Fig. 1). Convexity is required to ensure that points do not lie in gulfs or embayments. Finally, an algorithm was run for each datum of the ore database to determine if the corresponding point lay inside or outside the volume. Minor improvements were added: the hoard data were scaled to unit variance and zero mean, and some slack around the volume was allowed for. The successful data finally were plotted on a map of the circum-Mediterranean regions. The

The convexity of the hull guarantees that if extreme points lie in the hull, so will all the points that are lying on the mixing lines between the extremes. The problem is that if a single sample with a completely different isotopic composition (i.e., an outlier) is included in the sample set, the hull will include the empty volume between the outlier and the rest of the data. We found that a preliminary identification of distinct groups, as explained above, avoids including data-

necessary algorithms were all implemented with the MATLAB software.

intermediate free volumes in the search. As will be shown below, all the hoards include one or two groups. It must be remembered that the extreme points are still included and should show up in the search.

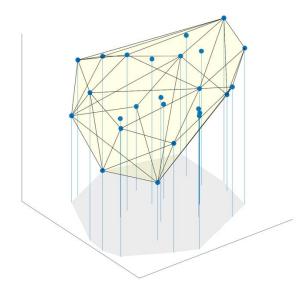

373

374

375

376

377

378

379

370

371

372

Figure 1. Sketch of a convex hull (in yellow) built by Delaunay triangulation. The original data (blue circles) were generated as a set of 25 random points in 3-dimensional space. In practice, the convex hull is the 3D convex volume that contains all the isotopic coordinates of the samples in each hoard. The Delaunay triangles have been made transparent to show the points inside the hull.

4. Results

- We first explored the space of the 209 Pb isotope data (including those produced by Eshel et
- al. (2019; 2021) and the 46 Pb isotope data produced in the present work), from the 13
- 382 different *Hacksilber* hoards listed in Table 1. We proceeded hoard by hoard by:
- 383 (1) identifying significantly different isotopic groups in each hoard,
- 384 (2) constructing the corresponding convex hulls for each of them by Delaunay triangulation,
- 385 (3) searching the ore database for the points lying within each hull, and
- 386 (4) identifying the location of potential sources.

- 388 4.1. Constructing the convex hulls
- Convex hulls were obtained for each hoard by Delaunay triangulation. By maximizing the
- smallest angle of all the triangles, Delaunay triangulation makes fewer elongated triangles. In
- order to avoid enclosing large unpopulated ('empty') volumes, a rough cluster analysis was

run for each hoard defining a maximum of three groups (in practice one or two) in the conventional space of ²⁰⁴Pb-normalized ratios. Choosing a different normalization isotope does not affect the definition of the clusters. Figure 2 shows how different the hulls are from hoard to hoard.

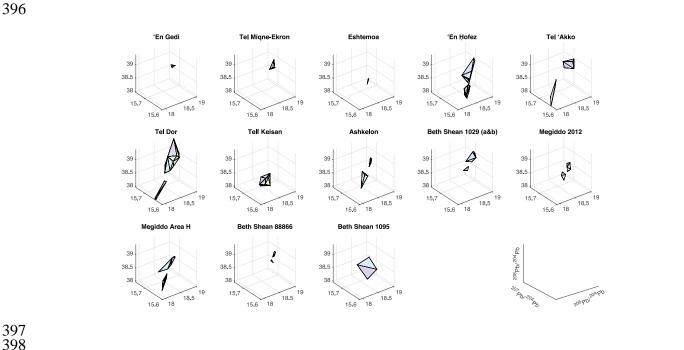




Figure 2. Scaled convex hulls obtained by Delaunay triangulation in the space of ²⁰⁴Pb-normalized ratios. The data were first standardized to zero mean and unit variance and cluster analysis allowing for up to three separate groups to help define tighter hulls.

A remarkable property of the technique is that, since the hull is convex, all the data corresponding to intermediate mixtures of different isotopic components plot within the hull defined by the data corresponding to the extreme mixtures. Let us assume a series of samples resulting from mixing components A and B, and label x_1 , x_2 , x_3 three of these mixtures with proportions of component B increasing in that order. If samples x_1 and x_3 plot in the convex hull, so will sample x_2 . A potential risk is that a mixture of components A and B may end up fortuitously producing a mix similar to an unrelated component C, thereby leading to an erroneous provenance assignment. Our experience with the available data is that if the risk of such a fortuitous coincidence in two-dimensional plots exists, it essentially disappears in three-dimensional space, or at the very least, concerns only isolated hits. We found that 'hot spots' with multiple hits are robust against such a fortuitous coincidence and that the robustness may be conveniently illustrated by frequency peaks of model ages.


4.2. Permissible silver sources


Once the hulls were defined, each sample from our ore database, which includes about 7000 samples of galena (Milot et al., in press), was tested for being inside or outside the hulls defined for each hoard. Although this database borrowed many references from the OXALID database, only Pb sulphides were retained and artefacts such as slags were carefully eliminated. A tolerance of 2% was allowed for on the standardized data, which is equivalent to considering the hull boundary as fuzzy. In-hull ores with isotope compositions falling in the hull of each hoard are considered 'hits.' The results are displayed for each hoard in Fig. 3. Each hit should not be considered as decisive, but only as a permissible source. Given the large number of ore samples in the database, a handful of geographically consistent hits may not be significant (e.g. Eshtemoa). Hits in unexpected localities, such as the modern United Kingdom or modern Tunisia may be disregarded on two different grounds: a very small number of hits or lack of archaeological evidence for mining. In contrast, ores that are no-hit can be excluded with a high degree of confidence.














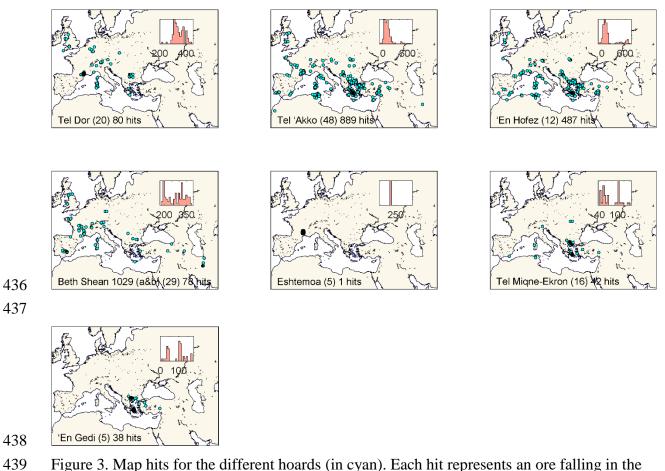


Figure 3. Map hits for the different hoards (in cyan). Each hit represents an ore falling in the sample convex hull of each hoard. The Pb isotope compositions of ~7000 ores were tested for inclusion in the convex hull of each hoard. Top panel: Bronze Age (yellow). Middle five panels: Iron Age I (blue). Bottom seven panels: Iron Age II (red). The black fields ('hot spots') include areas making up more than 10% of the hits (an equivalent of bi-dimensional histogram peaks). Upper right-hand corner insets are Pb model age histograms (Ma).

The most common hot spots are from Lavrion, Thrace, Macedonia, Sardinia, and the Cévennes (Southern Gaul) (Table 2). Fewer hits are found for some hoards in northern Sardinia, Illyria, the Betics, the Ossa-Morena Zone (southern Iberia), and Taurus. Only one hit was found for Eshtemoa, which we considered insufficient for source assignment.

Table 2. Approximate dates of deposition of the *Hacksilber* hoards analysed for Pb isotopes, number of hits, and probable origin of the metal.

Hoard	Period	Years (BCE)	Ref.	Hits	Probable silver source(s)
Beth Shean 88866	Late Bronze Age III	1200-1150	1	24	Unknown

Megiddo Area H	Iron Age I	1070	2	56	Lavrion	
Beth Shean 1095	Iron Age I	1150-950	3	57	Thrace, Sardinia	
	Iron Age I	1050-950	4	31	Cevennes	
	Iron Age I	1050-950	6	78	Lavrion	
Tell Keisan	Iron Age I	1050-950	7	86	Lavrion, Cevennes	
Tel Dor	Iron Age IIA	2 nd half 10 th century	8	786	Cevennes	
Tel ʿAkko	Iron Age IIA	10 th to 9 th centuries	9	422	Lavrion	
Beth Shean 1029a and b	Iron Age IIA	950-800	3	134	Sierra Morena, Eastern Persia	
En Ḥofez	Iron Age IIA	9 th century	9	78	Attica	
Eshtemoa	Iron Age IIB	8 th century	10	1	Unknown	
Tel Miqne-Ekron	Iron Age IIC	Late 7th early 6th century	11	35	Lavrion, Thrace	
'En Gedi	Iron Age IIC	Late 7th early 6th century	12	33	Lavrion, Macedonia	

References: 1 – Thompson, 2009; 2 – Arie, 2013; 3 – Rowe, 1940; 4 – Paice, 2004, Hall, 2016; 5 – Balmuth, 2001; 6 – Nodet, 1980; 7 – Stern, 1998; 2001; 8 - Thompson and Skaggs, 2013; 9 – Alexandre, 1997; 2013; 10 – Yeivin, 1990; Kletter and Brand, 1998; 11 - Golani and Sass, 1998; Gitin and Golani, 2001; 12 - Kletter and De Groot, 2007.

5. Discussion

Eshel et al. (2021) argue that the Pb isotope data of the Levant can be accounted for by mixing different end-members and we have tested this model here. We normalized the data to ²⁰⁶Pb (²⁰⁴Pb/²⁰⁶Pb, ²⁰⁷Pb/²⁰⁶Pb, and ²⁰⁸Pb/²⁰⁶Pb) to minimize error correlations and then ran a principal component analysis both globally and hoard by hoard. Table 3 shows that, with the exception of Tel Miqne-Ekron, the third principal component accounts for only a negligible fraction of the variance in each hoard. Two principal components (i.e., three end-members, but often only two) therefore adequately account for the observed isotopic variability, which in general is consistent with the number of modes in the histograms of Fig. 3, and agrees with Eshel et al.'s (2021) conclusions.

A concern raised by Eshel et al. (2021) is that Pb isotopes in *Hacksilber* may have been drastically altered by copper-based debasement. A puzzle in this context is the contrast between the well-defined mixing arrays observed by these authors for some hoards (Tell Keisan, Megiddo Area H) in Pb isotope diagrams and the lack of mixing hyperbolae observed

in the ²⁰⁶Pb/²⁰⁴Pb vs Cu diagram (Eshel et al., 2021, Fig. 8). The key to solving this puzzle is the limited solubility of Pb in Cu (a few hundred ppm, Vaajamo et al., 2013). In contrast, Pb solubility in Ag is substantial (up to a few percent, Karakaya and Thompson, 1987). It therefore takes up to several tens of percent of Cu addition to silver to alter the original Pb isotope composition. This is the case for the Tell Keisan and Megiddo Area H hoards. The mixing lines observed by Eshel et al. (2021) are therefore better interpreted as a mixture of silver components than as an effect of debasement by copper addition. The range of ²⁰⁶Pb/²⁰⁴Pb observed at nearly constant Cu concentration by Eshel et al. (2021, Fig. 8) for Beth Shean 1029a and b and 1095 and for Ashkelon confirms the lack of correlation between the two variables and cautions against overemphasizing the effect of debasement.

Table 3. Results of principal component analysis in the ²⁰⁴Pb/²⁰⁶Pb-²⁰⁷Pb/²⁰⁶Pb-²⁰⁸Pb/²⁰⁶Pb space for each hoard. PC1, PC2, and PC3 represent the percentage of variance accounted for by the corresponding component. One, two, and three significant percentages correspond to the presence of 2, 3, and 4 end-members, respectively.

Hoard	PC1	PC2	PC3	No of end-
				members
Beth Shean 88866	98.1	1.9	0.0	2-3
Megiddo Area H	99.8	0.1	0.1	2
Beth Shean 1095	77.8	21.4	0.8	3
Megiddo 2012	95.5	4.5	0.0	2-3
Ashkelon	99.3	0.7	0.0	2
Tell Keisan	96.0	4.0	0.1	2-3
Tel Dor	99.2	0.8	0.0	2
Tel 'Akko	98.8	1.2	0.0	2
'En Ḥofez	99.7	0.2	0.1	2
Beth Shean 1029a	99.4	0.5	0.1	2
and b				
Eshtemoa	97.9	2.1	0.0	2-3
Tel Miqne-Ekron	85.4	10.8	3.8	4
'En Gedi	98.5	1.5	0.0	2-3

We took advantage of Eshel et al.'s (2021) mixing model to calculate the hits for each of the convex hulls displayed in Fig. 2, with the expectation that potential end-members would be more frequent in the ore database if they could be safely considered as end-members.

Evidence obtained from these convex hull analyses is extremely rich and found to support or falsify previous theories as follows:

- The prevalence of Lavrion, Macedonia, Thrace, Sardinia, and southern Gaul (the
 Cévennes) as silver sources is particularly strong. Communication between these areas and
 the Levant, whether peacefully by trade or by way of war, never really stopped during the
 Late Bronze Age through the Iron Age IIC, and/or *Hacksilber* was recycled from earlier
 times.
- The prevalence of hits from southern Gaul is particularly interesting, as these mines have been known to be active since Roman times (Baron *et al.* 2005; Elbaz-Poulichet et al., 2017). The present study, however, indicates mining activity in the area centuries prior. We posit that this activity would conform to a broader pattern of silver exploitation and sale by dominant local tribes across Thrace and Iberia.
- The case of Sardinia is only strong for Beth Shean 1095. Iron Age Nuragic settlements are known from Sardinia and Corsica (Balmuth, 1992), but evidence of contemporaneous mining is missing. Taurus provided a few hits (Tel 'Akko, 'En Ḥofez), but the small number of ore samples does not make this area an incontrovertible source of silver.
 Modern Iran and Cyprus, with few hits and inadequate geology, are unlikely to have been significant silver providers.
 - Evidence of exploitation of silver ore sources in Iberia is surprisingly scant, with one exception being the Sierra Morena (Beth Shean 1029a and b). Hits in the Betics exist but are in general second to more productive areas in the Aegean domain. Possible hits near Huelva and in southern Portugal are uncommon, limited to Meggido Area H and Tel Dor. This area may be underrepresented because silver from southwest Iberia was mined from the mineral jarosite in the Lower Guadalquivir (Tartessos) to which extraneous Pb needed to be added for cupellation rather than from Pb-rich galena (Anguilano *et al.* 2010), which itself was obtained from the distant Betics and Ossa Morena Zone. This may be why the latter district is found only in the Tel 'Akko and 'En Hofez hoards.
 - The assignment of silver to other localities is more speculative, either because the number
 of hits is too small or because little evidence is known from archaeological and textual
 contexts. This is the case of the Eifel, Germany, the Palaeozoic basement of the southern
 Massif Central of France (the Cévennes), the Alps, and the Carpathians. Hits in Crete,

526 Peloponnese, Tunisia, and even the British Isles may at this point be considered 527 coincidental because they are unsupported by archaeological evidence. 528 One possible conclusion is that exchanges between the southern Levant and the Aegean world 529 never entirely came to a full stop during the Late Bronze and Iron Ages. What supported these 530 exchanges is not always clear; war, as attested to by the violent demise of large towns, and 531 trade, the only possible way to attract silver to the Levant, a territory where silver mines are 532 absent. In the context of the overall fineness of *Hacksilber* (Eshel et al., 2018; 2021), 533 occasional silver famines may be the reason for unusually high Cu contents in Beth Shean 534 88866 and Megiddo Area H (Eshel et al., 2021) rather than deliberate debasement but other 535 explanations are possible. 536 537 Alternatively, the prevalence of mixing in some hoards, the low percentage of silver, and the 538 relatively few hoards from over half a millennium suggest that bullion was hoarded over long periods of time. The scatter of isotopic values within some hoards can be taken as evidence of 539 such long-term hoarding, while the scatter in the plot of ²⁰⁶Pb/²⁰⁴Pb vs Cu in wt.% (Eshel et 540 al., 2021, Fig. 8) shows the lack of coherent mixing hyperbolae for hoards such as Tell 541 542 Keisan, Megiddo Area H, and Beth Shean 1095, and requires that the analysed samples were 543 produced from silver with widely different Pb contents and not from a single source. This 544 pattern may be usefully contrasted with early minting of silver coinage in the Late Archaic 545 period which overwhelmingly came from single ore sources refined to a very high percentage 546 of silver (Stos Gale and Davis, 2020; Birch et al., 2020). If mixing with recycling is the case, 547 we would in theory expect to see a linear array which tends to be parallel to the Pb evolution 548 curve (lines of constant μ and κ) (Albarède et al. 2020). Good examples of mixing are those of 549 Megiddo Area H and the Tell Keisan hoards (Eshel et al., 2021). However, mixing is by 550 definition between different end-members (A and B) which should manifest in ore 'hits' on the 551 end-members A and B, but not on the mixtures between A and B which have no natural 552 match. If the mixture is between different 'pure' issues (without remelting), it would show up, 553 not as alignments, but as separate groups of points corresponding to each issue. Although the 554 hoards seem to show both types of behavior, there are not enough samples at present to 555 conclusively separate the groups. Hence, until enough data points have become available to

conclusively demonstrate via statistical means long-term hoarding and mixing, trade

continuity is not contradicted by the present data and overall remains a valid working

556

557

558

hypothesis.

Exchanges between the eastern and western Mediterranean are more problematic. They may have been less active during the turmoil of the end of the Late Bronze Age but clearly were revived in the Early Iron Age I.

6. Conclusions

This study has demonstrated the applicability of a data-driven approach to lead isotope analysis. Principal component analysis of the most precise Pb isotope data (this work combined with Eshel et al., 2019; 2021) confirms that isotope compositions of each element in each hoard can be accounted for by a small number of end-members (2-3). The new 'convex hull' approach applied to the ore database of Pb isotopes identifies more previously unrecorded potential source end-members. The concepts of 'hits' and 'hot spots' turned out to be critical in assigning a provenance to individual isotopic data and data groups.

The prevalence of Aegean sources including Lavrion, Macedonia, Thrace, Sardinia, and southern Gaul as long-lived major sources of silver shows that exchanges between the southern Levant and the Aegean continued at least intermittently from the end of the Late Bronze Age through the Iron Age IIC. A caveat is that long-term hoarding suggested by isotopically heterogeneous hoards and use of low-purity silver may have blurred evidence of trade disruption. Southern Gaul is proposed as an Iron Age silver source. Occasional exchanges with Sardinia and southern Iberia in the Iron Age are confirmed. The Aegean world, including Thraco-Macedonian sources, dominated silver supply presumably because of its proximity, but exchanges between the eastern and western Mediterranean did not disappear from the isotopic record.

Acknowledgements

This research was funded by the European Research Council H2020 Advanced Grant 741454-SILVER-ERC-2016-ADG 'Silver Isotopes and the Rise of Money' awarded to Francis Albarède. Philippe Télouk is thanked for maintaining ICP-MS instrumentation in perfect conditions and Chloé Malod-Dognin and Florent Arnaud-Godet for maintaining a well-functioning and clean laboratory environment. François de Callataÿ's suggestions were as helpful as always. We are grateful to Eran Arie who enabled us to analyse the Hacksilber hoards kept at the Israel Museum and to Sharon Tager and Irit Lev-Beyth for providing the

- facilities to examine this material at the Israel Museum's Metals and Organic Object
- 592 Conservation laboratories. Insightful criticism of two anonymous reviewers greatly
- 593 contributed to the improvement of this manuscript.

Bibliography

594

605

606

607

608

609

610

612

613

617

618

619

620

621

622

624

625

- 595 ALBARÈDE, F., BLICHERT-TOFT, J., DE CALLATAŸ, F., DAVIS, G., DEBERNARDI, P., GENTELLI, L., GITLER, 596 H., KEMMERS, F., KLEIN, S., MALOD-DOGNIN, C., MILOT, J., TÉLOUK, P., VAXEVANOPOULOS, 597 M. & WESTNER, K. 2021. From commodity to money: The rise of silver coinage around the 598 Ancient Mediterranean (sixth–first centuries bce). *Archaeometry*, 63, 142-155.
- 599 ALBAREDE, F., BLICHERT-TOFT, J., GENTELLI, L., MILOT, J., VAXEVANOPOULOS, M., KLEIN, S.,
 600 WESTNER, K., BIRCH, T., DAVIS, G. & DE CALLATAŸ, F. 2020. A miner's perspective on Pb
 601 isotope provenances in the Western and Central Mediterranean. *Journal of Archaeological*602 *Science*, 121, 105194.
- ALBAREDE, F., DESAULTY, A-M., BLICHERT-TOFT, J. 2012. A geological perspective on the use of Pb isotopes in archaeometry. *Archaeometry*, 54, 853-867.
 - ANGUILANO, L., REHREN, T. H., MÜLLER, W. & ROTHENBERG, B. 2010. The importance of lead in the silver production at Riotinto (Spain). *Archéosciences*, 34, 269-276.
 - ARIE, E., BOARETTO, E., MARTIN, M., NAMDAR, D., SHAMIR, O., YAHALOM-MACK, N. 2019. A new jewelry hoard from eleventh-century BCE Megiddo. *Near Eastern Archaeology*, 82, 90-101.
 - AURENHAMMER, F., KLEIN, R. & LEE, D. 2013. *Voronoi Diagrams And Delaunay Triangulations*, World Scientific Publishing Company.
- BAKER, H. 1992. Alloy phase diagrams. *ASM Handbook*.
 - BALMUTH, M. S. 2001. *Hacksilber to Coinage: New Insights Into the Monetary History of the Near East and Greece*, New York, American Numismatic Society.
- 614 BARON, S., LAVOIE, M., PLOQUIN, A., CARIGNAN, J., PULIDO, M. & DE BEAULIEU, J. L. 2005. Record of Metal Workshops in Peat Deposits: History and Environmental Impact on the Mont Lozère Massif, France. *Environmental Science & Technology*, 39, 5131-5140.
 - BLICHERT-TOFT, J., DELILE, H., LEE, C-T., STOS-GALE, Z., BILLSTROM, K., ANDERSEN, T., HANNU, H., ALBAREDE, F. 2016. Large-scale tectonic cycles in Europe revealed by distinct Pb isotope provinces. *Geochemistry, Geophysics, Geosystems*, 17, 3854-3864.
 - BLICHERT-TOFT, J., WEIS, D., MAERSCHALK, C., AGRANIER, A. & ALBARÈDE, F. 2003. Hawaiian hot spot dynamics as inferred from the Hf and Pb isotope evolution of Mauna Kea volcano. *Geochemistry, Geophysics, Geosystems*, 4.
- DAVIS, G. 2012. Dating the drachmas in Solon's laws. *Historia*, 61, 127-158.
 - DELILE, H. 2014. Signatures des paléo-pollutions et des paléoenvironnements dans les archives sédimentaires des ports antiques de Rome et d'Éphèse. Doctor of Philosophy, Université Lumière Lyon 2.
- 627 EISELE, J., ABOUCHAMI, W., GALER, S. J. G. & HOFMANN, A. W. 2003. The 320 kyr Pb isotope 628 evolution of Mauna Kea lavas recorded in the HSDP-2 drill core. *Geochemistry, Geophysics,* 629 *Geosystems,* 4.
- 630 ELAYI, J. & ELAYI, A. G. 2009. The Coinage of the Phoenician City of Tyre in the Persian Period (5th-4th 631 Cent. BCE), Isd.
- 632 ELBAZ-POULICHET, F., RESONGLES, E., BANCON-MONTIGNY, C., DELPOUX, S., FREYDIER, R. & CASIOT, 633 C. 2017. The environmental legacy of historic Pb-Zn-Ag-Au mining in river basins of the 634 southern edge of the Massif Central (France). *Environmental Science and Pollution Research*, 635 24, 20725-20735.
- 636 ESHEL, T., EREL, Y., YAHALOM-MACK, N., TIROSH, O., GILBOA, A. 2019. Lead isotopes in silver reveal 637 earliest Phoenician quest for metals in the west Mediterranean. *Proceedings of the National* 638 *Academy of Sciences of the United States of America,* 116, 6007-6012.

- 639 ESHEL, T., GILBOA, A., YAHALOM-MACK, N., TIROSH, O. & EREL, Y. 2021. Debasement of silver 640 throughout the Late Bronze – Iron Age transition in the Southern Levant: Analytical and 641 cultural implications. *Journal of Archaeological Science*, 125, 105268.
- 642 ESHEL, T., YAHALOM-MACK, N., SHALEV, S., TIROSH, O., EREL, Y., GILBOA, A. 2018. Four Iron Age 643 silver hoards from southern Phoenicia: From bundles to hacksilber. *Bulletin of the American* 644 *Schools of Oriental Research*, 379, 197-228.
- FARHI, Y. 2014. A Preliminary Report on the Coins and Selected Small Finds. *In:* GARFINKEL, Y.,
 GANOR, S., HASEL, M. (ed.) *Khirbet Qeiyafa, Vol. 2: Excavation Report 2009–2013:* Stratigraphy and Architecture (Areas B, C, D, E). Israel: Institute of Archaeology, Southern
 Adventist University; Israel Exploration Society; Institute of Archaeology, Hebrew University
 of Jerusalem.
- FINKELSTEIN, I., PIASETZKY, E. 2011. The Iron Age chronology debate: Is the gap narrowing? *Near Eastern Archaeology*, 74.
- 652 GITLER, H. 2006. A *hacksilber* and cut Athenian Tetradrachm hoard from the environs of Samaria: 653 Late Fourth Century BCE. *Israel Numismatic Research*, 1, 5-14.

655

656

657

658

659

660

661

662

663

664

665

666

667

668

669

670

671

672

673

674

675

- GITLER, H. & TAL, O. 2006. The Coinage of Philistia of the Fifth and Fourth Centuries BC: A Study of the Earliest Coins of Palestine, Edizioni Ennerre.
- GITLER, H., TAL, O. 2020. A View from the Near East: The Transition from Metal to Coin Economy in the Southern Levant. *In:* VANALFEN, P., WARTENBERG, U. (ed.) *White Gold: Studies in Early Electrum Coinage*. New York, Jerusalem: The American Numismatic Society, The Israel Museum.
- GOLANI, A. & SASS, B. 1998. Three Seventh-Century B. C. E. Hoards of Silver Jewelry from Tel Migne-Ekron. *Bulletin of the American Schools of Oriental Research*, 57-81.
- HELWING, B. 2014. Silver in the early state societies of Greater Mesopotamia. *Metals of Power–Early Gold and Silver*, 411-421.
- HEYMANS, E. 2018a. Argonauts of the eastern Mediterranean: The early history of money in the eastern Mediterranean Iron Age. Doctor of Philosophy, Tel Aviv University.
- HEYMANS, E. 2018b. Heads or tails: metal hoards from the Iron Age southern Levant. *In:*BRANDHERM, D., HEYMANS, E., HOFMANN, D. (ed.) *Gifts, Goods and Money. Comparing currency and circulation systems in past societies.* Summertown: Archaeopress.
- HONIG, R. E. & KRAMER, D. A. 1969. *Vapor Pressure Data for the Solid and Liquid Elements*, RCA Laboratories, David Sarnoff Research Center.
- KARAKAYA, I. & THOMPSON, W. T. 1987. The Ag-Pb (Silver-Lead) system. *Bulletin of Alloy Phase Diagrams*, 8, 326-334.
- KLETTER, R. 2003. Iron Age hoards of precious metals in Palestine an "underground economy"? *Levant*, 35, 139-152.
- KLETTER, R. & BRAND, E. 1998. A New Look at the Iron Age Silver Hoard from Eshtemoa. *Zeitschrift des Deutschen Palästina-Vereins (1953-),* 114, 139-154.
- KLETTER, R., DEGROOT, A. 2007. The Iron Age hoard of "Hacksilber" from En-Gedi. *In:* STERN, E. (ed.)
 En-Gedi Excavations I: Conducted by B. Mazar and I. Dunayevsky; Final Report (1961–1965). Jerusalem: Israel Exploration Society; Institute of Archaeology, Hebrew University of
 Jerusalem.
- MAZAR, A. 2011. The Iron Age Chronology Debate: Is the Gap Narrowing? Another Viewpoint. *Near Eastern Archaeology*, 74, 105-111.
- 683 MILOT, J., BLICHERT-TOFT, J., AYARZAQUENA SANZ, M., FETTER, N., TELOUK, P, ALBAREDE, F. 2021.
 684 The significance of galena Pb model ages and the formation of large Pb-Zn sedimentary
 685 deposits. *Chemical Geology*, in press.
- 686 MILOT, J., MALOD-DOGNIN, C., BLICHERT-TOFT, J., TÉLOUK, P. & ALBARÈDE, F. 2021. Sampling and combined Pb and Ag isotopic analysis of ancient silver coins and ores. *Chemical Geology*, 564, 120028.

- 689 MURILLO-BARROSO, M., MONTERO- RUIZ, I., RAFEL, N., HUNT ORTIZ, M. A., & ARMADA, X. L. 2016. 690 The macro-regional scale of silver production in Iberia during the first millennium BC in the 691 context of Mediterranean contacts. *Oxford Journal of Archaeology*, 35, 75-100.
- 692 PEYRONEL, L. 2014. Between Archaic market and gift exchange: the role of silver in the embedded 693 economies of the ancient near east during the Bronze Age. *In:* CARLA-UHINK, F., GORI, M. 694 (ed.) *Gift giving and the "embedded" economy in the ancient world.* Heidelberg: 695 Universitatsverlag Winter.
- ROWE, A. 1940. *The Four Canaanite Temples of Beth-Shan, Part 1: The Temples and Cult Objects,*697 Philadelphia, University of Pennsylvania Press.
 - SHALEV, S., SHECHTMAN, D. & SHILSTEIN, S. 2013. A study of the composition and microstructure of silver hoards from Tel Beth-Shean, Tel Dor, and Tel Miqne, Israel. *Archaeological and Anthropological Sciences*, 6.
 - SHALEV, S., SHECHTMAN, D. & SHILSTEIN, S. 2014. A study of the composition and microstructure of silver hoards from Tel Beth-Shean, Tel Dor, and Tel Miqne, Israel. *Archaeological and Anthropological Sciences*, 6.
 - STOS-GALE, Z. 2001. The impact of natural sciences on studies of hacksilber and early silver coinage. In: BALMUTH, M. (ed.) Hacksilber to Coinage: New Insights into the Monetary History of the Near East and Greece. New York: American Numismatic Society.
 - STOS-GALE, Z., GALE, N. 2012. OXALID. https://oxalid.arch.ox.ac.uk/The%20Database/TheDatabase.htm.

699

700

701

702

703

704

705

706

707

708

709

710

711

712

713

715

716

717

718

719

720

721

722

723

724

725

726

727

728

729

730

731

732

733

734

735

- THOMPSON, C. 2003. Sealed silver in Iron Age Cisjordan and the 'invention' of coinage. *Oxford Journal of Archaeology*, 22, 67-107.
- THOMPSON, C. 2009. Three 20th Dynasty Silver Hoards from the Egyptian Garrison. *In:* PANITZ-COHEN, N., MAZAR, A. (ed.) *The Beth-Shean Valley Archaeological Project*. Jerusalem: The Israel Exploration Society.
- 714 THOMPSON, C. 2017. A Brief History of Hacksilber Project Research. *Hacksilber Project* [Online].
 - THOMPSON, C., SKAGGS, S. 2013. King Solomon's silver? Southern Phoenician hacksilber hoards and the location of Tarshish. *Internet Archaeology*, 35.
 - THOMPSON, C. M. 2020. Two Bundles of Hacksilber. *In:* STAGER, L. E., MASTER, D. M., AJA, A. J. (ed.) *Ashkelon.* University Park: Pennsylvania State University Press.
 - VAAJAMO, I., JOHTO, H. & TASKINEN, P. 2013. Solubility study of the copper-lead system. International Journal of Materials Research, 104, 372-376.
 - VANALFEN, P. 2002. *Commodities in Levantine-Aegean trade during the Persian period, 6-4th c. B.C.*Doctor of Philosophy, University of Texas at Austin.
 - WEBSTER, L. 2015. *Developing a Radiocarbon-Based Chronology for Tel Azekah: The First Stage.*Master of Research, Macquarie University.
 - WESTNER, K., BIRCH, T., KEMMERS, F., KLEIN, S., HÖFER, H. & SEITZ, H.-M. 2020. Rome's rise to power. Geochemical analysis of silver coinage from the western Mediterranean (4th to 2nd centuries BCE). *Archaeometry*, 62.
 - WHITE, W. M., ALBARÈDE, F. & TÉLOUK, P. 2000. High-precision analysis of Pb isotope ratios by multicollector ICP-MS. *Chemical Geology*, 167, 257-270.
 - WOOD, J., BELL, C., MONTERO-RUIZ, I. 2020. The origin of Tel Dor Hacksilber ad the westward expansion of the Phoenicians in the early Iron Age: The Cypriot connection. *Journal of Eastern Mediterranean Archaeology & Heritage Studies*, 8, 1-21.
 - WOOD, J., MONTERO-RUIZ, I., MARTINON-TORRES, M. 2019. From Iberia to the Southern Levant: The movement of silver across the Mediterranean in the early Iron Age. *Journal of World Prehistory*, 32, 1-31.
- ZÜRCHER, L., BOOKSTROM, A. A., HAMMARSTROM, J. M., MARS, J. C., LUDINGTON, S. D., ZIENTEK, M.
 L., DUNLAP, P. & WALLIS, J. C. 2019. Tectono-magmatic evolution of porphyry belts in the
 central Tethys region of Turkey, the Caucasus, Iran, western Pakistan, and southern
 Afghanistan. *Ore Geology Reviews*, 111, 102849.

Supplementary Material

Click here to access/download **Supplementary Material**Hacksilber data.xlsx