



HAL
open science

Antibacterial properties of glycosylated surfaces: variation of the glucosidal moiety and fatty acid conformation of grafted microbial glycolipids

Claire Valotteau, Sophie Roelants, Dasaiyan Prabhu, Susanne Zibek, Michael Günther, Wim Soetaert, Bernd Everaert, Claire-Marie Pradier, Florence Babonneau, Niki Baccile, et al.

► To cite this version:

Claire Valotteau, Sophie Roelants, Dasaiyan Prabhu, Susanne Zibek, Michael Günther, et al.. Antibacterial properties of glycosylated surfaces: variation of the glucosidal moiety and fatty acid conformation of grafted microbial glycolipids. *Molecular Systems Design & Engineering*, 2020, 5 (7), pp.1307 - 1316. hal-03414300

HAL Id: hal-03414300

<https://hal.science/hal-03414300>

Submitted on 4 Nov 2021

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Antibacterial properties of glycosylated surfaces: variation of the glucosidal moiety and fatty acid conformation of grafted microbial glycolipids

5 Claire Valotteau^{1,2}, Sophie Roelants^{3,4}, Prabhu Dasaiyan⁵, Susanne Zibek⁶, Michael Günther⁷,
Wim Soetaert^{3,4}, Bernd Everaert⁴, Claire-Marie Pradier¹, Florence Babonneau², Niki Baccile^{2,§},
Vincent Humblot^{1,8,§}.

¹ Sorbonne Université, Laboratoire de Réactivité de Surface (LRS), UMR CNRS 7197, 4 place Jussieu,
10 Paris, F-75005, France.

² Sorbonne Université, Laboratoire de Chimie de la Matière Condensée de Paris (LCMCP), UMR CNRS
7574, 4 place Jussieu, Paris, F-75005, France.

³ Ghent University, Centre for Industrial Biotechnology and Biocatalysis (InBio.be), Coupure Links
653, B-9000 Gent, Belgium

15 ⁴ Bio Base Europe Pilot Plant, Rodenhuzekaai 1, B-9000 Gent, Belgium

⁵ Physical and Materials Chemistry Division, CSIR - National Chemical Laboratory, Pune - 411 008,
India

⁶ Fraunhofer Institute for Interfacial Engineering and Biotechnology IGB, Nobelstraße 12, D-70569
Stuttgart, Germany

20 ⁷ Universität Stuttgart, Institut für Grenzflächenverfahrenstechnik, Nobelstraße 12, D-70569 Stuttgart,
Germany

⁸ FEMTO-ST Institute, Université Bourgogne Franche-Comté, UMR CNRS 6174, 15B avenue des
Montboucons, 25030 Besancon Cedex, France

[§]Corresponding authors: niki.baccile@sorbonne-universite.fr; vincent.humblot@femto-st.fr

25

ABSTRACT

Glycosylated surfaces can display antimicrobial properties. It has been shown that
30 sophorolipids can be used to develop biocidal coatings against Gram-positive and Gram-
negative bacteria, but with a limited efficiency so far. Therefore, it appears necessary to further
investigate the surface antibacterial activity of a broader set of structurally related glycolipids.
The present work explores the influence of the glucosidic moiety (gluco-, sophoro-, cellobio-)
and the fatty acid backbone (saturated, *cis* or *trans* monounsaturated). We show that the fatty
35 acid backbone plays an important role: *cis* derivative of sophorolipids (SL) grafted onto model
gold surfaces has better biocidal properties than saturated (SL₀) and *trans* monounsaturated
(SL_t) molecules, which appear to be inefficient. The number of glucose units is also a key factor:
a one-third decrease in antibacterial activity is observed when having one glucose unit (GL)
compared to two (SL). Sugar acetylation (SL_a) does not seem to have an impact on the biocidal
40 properties of surfaces. These results are not limited to sophorolipids, cellobioselipids (CL)
leading to similar antibacterial observations.

INTRODUCTION

Microbial attachment to surfaces and the subsequent biofilm development can lead to material deterioration¹ and health issues². Established biofilms are difficult to eradicate and their treatments are costly and ineffective. Therefore, many studies aimed at developing preventive antimicrobial coatings on surfaces. Antibiotics, chloride and quaternary ammonium compounds (CAQs), incorporated into or grafted onto (polymeric) matrices are commonly used.³⁻⁵ However, these strategies are nowadays criticized because of their ecotoxicity and the increased bacterial resistance to these chemicals, which highlights the need for alternative eco-responsible approaches^{6,7}, with for instance less toxic QACs as shown recently by Forman *et al.*⁸ Biosurfactants, such as free fatty acids, glycolipides or monoglycerides, are part of a class of molecules obtained from the fermentation of vegetable oils and sugar, appear to be promising ecofriendly and affordable candidates.⁹⁻¹²

Microbial biosurfactants are biobased compounds obtained by the fermentation process of sugars and lipids, and their antimicrobial properties have been long described.^{13, 14} Several reviews have been published on this topic since more than a decade,^{15,16} while a number of recent studies has shown additional interesting properties like adjuvant effects with other antimicrobial compounds¹⁷⁻¹⁹ or anti-biofilm properties.²⁰⁻²² On this basis, specific formulation in the field of, e.g., oral hygiene, were recently developed.^{17,23} The anti-adhesive properties of biosurfactants against pathogenic organisms like *E. faecalis*, *S. mutans* or *E. coli* are particularly interesting,¹⁶ although the general protocol to study anti-adhesion and anti-biofilm properties of biosurfactants only consider a surface dispersion of the compound, this making it particularly vulnerable to washing. To address this issue, sophorolipids were immobilized in surfaces and they have shown a short-term antiadhesive effect (within the first seconds of contact),²⁴ probably due to repulsive short-distance hydration forces, but also a long-term (> 1h) biocidal effect. These antimicrobial effects are characterized by lysis of both Gram-positive and Gram-negative bacterial cells and decreased bacterial growth capacities.²⁵ However, only up to 50% of bacterial cells are affected, whereas much higher efficiency is expected from antimicrobial surfaces. Therefore, it seems necessary to further investigate the potential of glycosylated surfaces to improve their antimicrobial activity and to understand the effect of carbohydrates.

It has already been demonstrated that no biocidal activity can be detected on surfaces grafted solely with the aliphatic backbone of sophorolipids, nor with sophorolipids having a fully saturated aliphatic chain.²⁶ Thus, the antimicrobial properties of surfaces functionalized

with sophorolipids are attributed to the presence of the carbohydrate moiety²⁶ and correlated to the configuration of the aliphatic chain²⁶, as well as to the surface density of sophorolipids²⁵. Besides, replacing the glucose by several sugars, such as fructose, xylose, ribose, lactose, mannose, arabinose, galactose, in the fermentation medium used for the production of the sophorolipids induces variations in the carbohydrate moieties that further influence the antimicrobial activities of the resulting compounds.²⁷ More generally, the properties of glycosylated surfaces, known as glycoarrays, developed to study carbohydrate-binding proteins and carbohydrate-processing enzymes,²⁸ are influenced by carbohydrates conformation²⁹ and the biochemical affinities of carbohydrates after immobilization on a surface can differ from those in solution³⁰. These observations encouraged us to explore a broader molecular portfolio and to seek a better understanding of the possible molecular parameters underlying the antimicrobial effect of glycosylated surfaces. Building on the methodology and protocols previously developed for a specific glycolipid²⁶, this work investigates rational variations in the glycosidic headgroup and chain configuration (Figure 1). The typical disaccharide sophorose is replaced by an acetylated sophorose (acetylated sophorolipid, SL_a, known to be more resistant to enzymatic degradation³¹ and more active in solution³²), or a monosaccharide (glucolipid, GL, that could be residue of the sophorolipids degradation by bacterial glycosidases^{33,34}). An alternative linkage of sophorose to the fatty acid chain is also being considered (branched sophorolipid, SL_b). The lipidic structure is varied from *cis* (oleic acid sophorolipid, SL) to *trans* (elaidic acid sophorolipid, SL_t) and saturated (stearic acid sophorolipid, SL₀) configurations. Cellobioselipid (CL), another microbial glycolipid with a cellobiose headgroup, produced by the fungus *Ustilago maydis* and also known to be a membrane disruptor,³⁵ is also tested for its structural proximity to sophorolipids. All compounds were immobilized on gold surfaces by grafting their free carboxylic acid moiety onto a self-assembled monolayer of short thiol amines, following the protocols developed in our previous works.^{25,26} The thickness, composition and homogeneity of these substrates were characterized by Polarization Modulation Reflection Absorption Infrared Spectroscopy (PM-RAIRS) and X-ray photoelectron spectroscopy (XPS), followed by evaluation of the adhesion, membrane integrity and cultivability of the non-pathogenic Gram-positive bacterium *Listeria ivanovii*. We found that the surface antimicrobial properties appear to be strongly affected by carbohydrate configuration and accessibility: for sophorolipid analogues with the same molecular surface density, it appears that the monounsaturated *cis* bond is necessary to enhance antibacterial activity. In addition, the nature of the sugar part, in particular the number and acetylation extent of glucose units, influences also the biocidal efficiency.

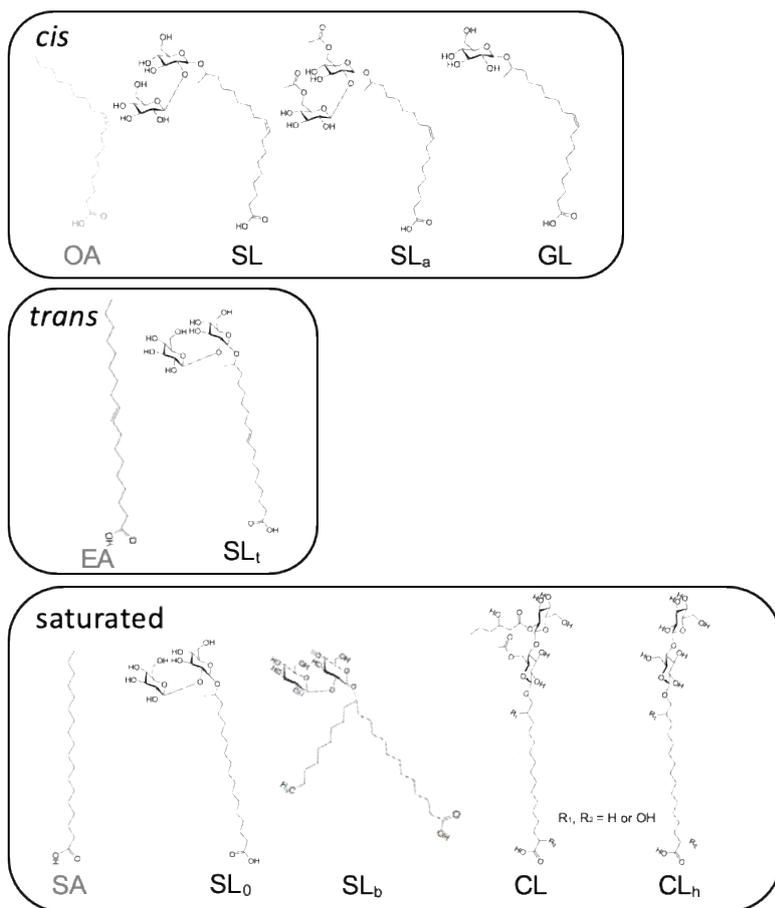


Figure 1. Set of microbial glycolipids presenting rational variation of the glycosidic headgroup (horizontally) and chain configuration (vertically).

The different acid chains are shown in grey as references.

115 3 glycolipids have a *cis* C18 oleic acid (OA) chain: the typical sophorolipid (SL), the acetylated sophorolipid (SL_a) and the glucolipid (GL).

The *trans* sophorolipid (SL_t) has a *trans* C18 elaidic acid (EA) chain.

The last glycolipids have a fully saturated chain: the saturated stearic acid (SA) sophorolipid (SL₀), the branched sophorolipid (SL_b), the cellobioselipid (CL) and the hydrolysed cellobioselipid (CL_h). For the latter, R₁=H or OH and R₂= H or OH, as described in the
120 materials and method section.

MATERIALS AND METHODS

125 Cysteamine (cys), N-hydroxysuccinimide (NHS), 1-(3-(dimethylamino)propyl)-N-ethylcarbodiimide hydrochloride (EDC), oleic acid (OA), stearic acid (SA) and elaidic acid (EA) were obtained from Sigma-Aldrich (Saint Quentin Fallavier, France). All solvents were

reagent-grade and were used without any further purification. Water was purified with a Milli-Q system (Millipore, resistivity $>18 \text{ M}\Omega \text{ cm}^{-1}$) from EMD Millipore Corp. (Billerica, MA).
130 Glass substrates, coated successively with a 50 \AA thick layer of chromium and a 200 nm thick layer of gold, were purchased from Arrandee (Werther, Germany).

All glycolipids (see Figure 1 for scheme and formula) used in this work have been used from previous studies, to which one should refer to for their characterization.

Deacetylated acidic *cis* C18 sophorolipids (SL) were obtained by a classical alkaline hydrolysis treatment of a commercial acidic and lactone mixture of sophorolipids purchased
135 from Soliance (France) (Sopholiance S; batch number, 11103A; dry content, $60 \pm 6\%$).^{26, 36}

The sophorolipid compound SL_0 constituted by a fully saturated C18 fatty acid (stearic acid, SA) was derived from the previous one using a Pd-catalyzed hydrogenation reaction described in ref ^{26, 37}

140 Acetylated acidic *cis* C18 sophorolipids (SL_a) have been produced using a *Starmerella bombicola* lactone esterase knock out strain ($\Delta sble$).³⁸ Their synthesis and composition has been described in detail in ref. ³⁹ and they were kindly provided by the Bio Base Europe Pilot Plant (Ghent, Belgium) and used as such.

Deacetylated acidic *cis* C18 glucolipids (GL) were produced by the *S. bombicola* strain
145 $\Delta ugtB1$ ⁴⁰ and provided by the Center for Industrial Biotechnology and Biocatalysis of Ghent University. Their synthesis and purification process has been described in ref. ⁴¹.

Acidic sophorolipids bearing a *trans* C18 fatty acid (elaidic acid, EA), SL_t , have also been employed. SL_t , produced at the National Chemical Laboratory at Pune (India), is obtained by the fermentation process by *S. bombicola* using elaidic acid as carbon support. Their
150 synthesis and purification procedure is given elsewhere.⁴²

The compound SL_b refers to a deacetylated acidic sophorolipid bearing a glycosidic bond with the C13 position of 13-hydroxydocosanoic acid. For its peculiar morphology, it is named “branched sophorolipid”. The compound used in this work was recently produced⁴³ according to a published procedure⁴⁴ by the yeast *Rhodotorula bogoriensis* MUCL 11796,
155 recently renamed *Pseudohyphozyma bogoriensis*.

Cellobioselipids (CL) were provided by the Industrial Biotechnology group of Fraunhofer Institute for Interfacial Engineering and Biotechnology (Stuttgart). They are produced by the fungus *Ustilago maydis*⁴⁵ as a mixture of hydroxylated and non-hydroxylated congeners. The hydrolyzed cellobioselipids (CL_h) were obtained by alkaline hydrolysis and
160 further acidification at neutral pH. Alkaline hydrolysis and characterization of both CL and CL_h are described in ref. ⁴¹. Both CL and CL_h are mixtures of structurally similar congeners where

both R1= H or OH and R2= H or OH and where the proportion of R1= H was evaluated to about 40% by ¹H NMR.⁴¹.

165 **Surface preparation and characterization.**

Glycosylated surfaces

All glycolipids were grafted onto flat gold substrates *via* a self-assembled monolayer of short aminothiols, as described previously.^{25,26} Briefly, the substrates were first annealed in a butane flame to ensure a good crystallinity of the uppermost layer and afterwards cleaned by
170 UV-ozone during 15 min. Substrates were then immersed in an ethanolic solution of cysteamine (cys) at 10 mM for 3 h, sonicated in ethanol for 5 min and then rinsed successively in ethanol and in ultrapure water before being dried under a flow of dried air. The samples were then immersed for 3 h into solutions of 8 mM glycolipids (equivalent to 50 mg/mL for SL)²⁵; the terminal carboxylic acid having been previously activated into a succinimide ester using a
175 mixture of EDC and NHS (molar ratio NHS:EDC=1:2). Finally, after incubation, sonication and successive rinsing in ultrapure water and ethanol were carried out to remove non-covalently grafted reactants before drying under a flow of dried air. All samples were characterized by Polarization Modulation Reflection Absorption Infrared Spectroscopy (PM-RAIRS) after each step of functionalization to guarantee the successful grafting of the different primers, fatty acids
180 and glycolipids.

X-ray Photoelectron Spectroscopy (XPS)

XPS analyses were performed using an Omicron Argus X-ray photoelectron spectrometer, equipped with a monochromated Al K_α radiation source ($h\nu = 1486.6$ eV) and a
185 300 W electron beam power. The emission of photoelectrons from the sample was analyzed at a take-off angle of 90° under ultra-high vacuum conditions ($\leq 10^{-10}$ Torr). Spectra were recorded with a 100 eV pass energy for the survey scan and 20 eV pass energy for the C1s, O1s, N1s, S2p regions. Binding energies were calibrated against the Au4f_{7/2} binding energy at 84.0 eV and element peak intensities were corrected by Scofield factors.⁴⁶ The peak areas were
190 determined after subtraction of a linear background. The spectra were fitted using Casa XPS v.2.3.15 software (Casa Software Ltd., U.K.) and applying a Gaussian/Lorentzian ratio G/L equal to 70/30.

Polarization Modulation Reflection Absorption Infrared Spectroscopy (PM-RAIRS)

195 Infrared (IR) analysis of the surfaces has been done using PM-RAIRS. A Nicolet Nexus
5700 FT-IR spectrometer equipped with a nitrogen-cooled HgCdTe wide band detector has
been employed. Infrared spectra were recorded at 8 cm^{-1} resolution, by coaddition of 128 scans.
A ZnSe grid polarizer and a ZnSe photoelastic modulator were placed prior to the sample in
200 order to modulate the incident beam between p and s polarizations (HINDS Instruments, PM90,
modulation frequency = 36 kHz). The sum and difference interferograms were processed and
underwent Fourier-transformation to yield the PM-RAIRS signal which is the differential
reflectivity $(\Delta R/R_0) = (R_p - R_s)/(R_p + R_s)$ where R_p and R_s are respectively the p- and s-
polarized components of radiation. All measurements (on control and functionalized surfaces)
were performed during the same experimental session, thus reducing at minimum intensity
205 variations of the background, beam intensity and alignment.

Antimicrobial activity.

Strain and culture conditions

The antibacterial properties of the glycosylated surfaces were tested against the non-
210 human pathogenic Gram-positive bacteria *Listeria ivanovii* Li4pVS2. Bacteria were cultivated
overnight in Brain Heart Infusion (BHI) broth (BD Difco, France) at 37°C under agitation
(250 rpm). The cells from stationary cultures were harvested by centrifugation at 10,000 g for
5 min and dispersed in an isotonic sterile solution (NaCl 0.9%) in order to obtain an optical
density at 620 nm of 0.05, which corresponds to approximately $5 \cdot 10^6$ colony forming units
215 per mL (cfu/mL).

Deposition of bacteria on samples

All samples were sterilized by immersion in a solution of 70 % ethanol (in water) and
dried in a sterile environment. They were then inoculated with a 100 μL drop of bacterial
220 suspension and incubated for 3 h at room temperature in a wet atmosphere. After this time,
surfaces were washed five times with 100 μL of isotonic sterile solution (NaCl 0.9%) to remove
all non-adhering bacteria.

Evaluation of bacteria adhesion by infrared spectroscopy

225 The relative amounts of bacteria adsorbed on each substrate were evaluated by
considering the IR signal collected by scanning each surface (after drying under sterile laminar
air-flow), as described in previous works.^{25, 26}

230 The attachment of bacteria onto the different surfaces is expressed as a percentage of amide I and II bands area (between 1700 cm^{-1} and 1500 cm^{-1}) compared to control gold substrates: Adhesion(%) = $100 \times (\text{area of amide bands on sample})/(\text{area of amide bands on gold})$. The uncertainty attached to this percentage comes from the propagation of the uncertainties attached to the measurement of amide bands area on both the considered surface and the gold substrate. These results were confirmed by repeating the same procedure on three different sets of samples prepared with independent bacterial cultures.

235

Evaluation of bacteria damaging by fluorescent staining

The proportion of damaged bacterial cells was evaluated by counting bacteria after staining with Live/Dead Bacterial Viability Kit (BacLight®). After rinsing of inoculated sample, the adhered bacteria were labeled with 10 μ L of a fluorochrome solution prepared by mixing 1.5 μ L of Syto9 stain and 1.5 μ L of propidium iodide (PI) with 1 mL of ultrapure water. Samples were then incubated in dark for 10 min prior to microscopic analysis. Surfaces were kept in a humid environment during the experiments to prevent drying. Samples were examined with an epifluorescence microscope (AXIO 100 Zeiss), images were acquired with a 10 \times or 40 \times objective lens and a CCD camera (AxioCamMRm Zeiss). Fluorochromes were respectively excited and detected at 455–495 nm and 505–555 nm for Syto9 and at 533–558 nm and 570–640 nm for PI. To obtain statistically relevant data; about 10 different locations of each surface were analyzed, at least a thousand bacteria were enumerated and experiments were repeated on three independent sets of samples. Bacterial counting (red, damaged membrane; green, intact membrane) was done using the software ImageJ and the viability calculated as follows: Viability (%) = $100 \times (\text{number of green bacteria}) / (\text{number of green bacteria} + \text{number of red bacteria})$.

Evaluation of bacteria damaging by scanning electronic microscopy

After deposition and incubation for 3 hours on the different surfaces, bacteria were fixed using formaldehyde at 37% to avoid collapsing of cells upon drying. After 15 min, samples were washed six times with ultrapure water to remove non-adhered bacteria, dehydrated in successive baths of increasing ethanoic concentration (25, 50, 75, 100%) and dried under a laminar air flow. SEM images were recorded with a Hitachi SU-70 field emission gun scanning electron microscope. The samples were fixed on an alumina SEM support with a carbon adhesive tape and were observed without metallization. An in-lens secondary electron detector (SEUpper) was used to characterize our samples. The accelerating voltage was 1 kV, and the working distance was around 5 mm. At least five different locations were analyzed on each surface, arising to the observation of a minimum of 100 single bacteria observed.

Cultivability (bacterial growth capacity)

In order to evaluate the bacterial growth capacity after being in contact with the glycosylated substrates, each inoculated sample was transferred into a sterile tube containing 2 mL of isotonic sterile solution (NaCl at 0.9%) and sonicated 5 min. The obtained bacterial

270 suspensions were diluted 10, 100 and 1000 times and a volume of 50 μL of each was deposited
in duplicate on Petri dishes filled with BHI + agar (37 g/L + 15g/L, respectively). These plates
were incubated at 37°C overnight before enumeration. Results are expressed in percentages of
the number of attached and cultivable bacterial cells onto the glycosylated surfaces as compared
to control gold substrates: $\text{Cultivability}(\%) = 100 \times (\text{number of colonies forming unity on}$
275 $\text{sample}) / (\text{number of colonies forming unity on control gold substrate})$. These tests were done in
triplicate and the cultivability value was averaged over the three samples. The uncertainty
attached to these results follows from the statistical analysis of these repeated experiments.


RESULTS

280 Glycolipids grafting on Au (111)

Glycosylation of gold surfaces was performed using the glycolipids shown in Figure 1.
This work explores the molecular variations of the oleic acid derivative of sophorolipids
(glucose $\beta 1,2$)²⁶ in terms of both the carbohydrate moiety and fatty acid: glucolipid (GL) and
acetylated sophorolipid (SL_a) consist of an oleic acid linked respectively to a single glucose
285 unit and an acetylated sophorose headgroup³⁹; branched sophorolipid (SL_b) carries a
deacetylated acidic sophorolipid linked by a glycosidic bond to the C13 position of 13-
hydroxydocosanoic acid. Elaidic derivatives of *trans* configuration sophorolipids (SL_t) have
also been used. The stearic acid derivatives of sophorolipids (referred as SL₀), as well as the
more classical oleic acid sophorolipids (SL), studied in our previous works, are also presented
290 for comparison.²⁶ Finally, cellobioselipid (CL) and its hydrolyzed variant (CL_h) have also been
used.⁴¹ These glycolipids are composed of a fully saturated C16 hydroxylated fatty acid and a
cellobiose moiety (glucose $\beta 1,4$).

All glycolipids have been individually grafted, via their carboxylic acid, onto a self-
assembled monolayer (SAM) of cysteamine (cys) formed on a flat gold substrate, according to
295 a previously described protocol.^{25, 26} The glycolipid-functionalized surfaces were characterized
by infrared spectroscopy (PM-RAIRS) and X-ray photoelectron spectroscopy (XPS). The
corresponding spectroscopic data are given in Figure S1 and Figure S2 where the attribution is
given in corresponding captions, on the basis of ref. ^{25,26}. Both techniques demonstrate the
anchoring of glycolipids by amide bonds⁴⁷. The presence of aliphatic chains and carbohydrates
is also attested by both vibrational bands ⁴⁸ and XPS spectra.⁴⁹⁻⁵² The elongation of the C=O
300 bonds at 1740 cm^{-1} on acetyl moieties produces an additional signal on the infrared spectra of
substrates prepared with acetylated SL_a and CL.

While both PM-RAIRS and XPS demonstrate the success of glycolipids grafting, XPS analyses can also be used to estimate the thickness of the cysteamine and glycolipid coatings, which are assumed to form a homogeneous layer on the gold. This structural parameter can be obtained by considering the signal of a component of the layer (e.g. C=O, N or S_{bound} signal for instance) and that of the substrate (Au), using the methodology outlined in ref. ²⁵. The thickness estimate for each glycolipid is summarized in Figure 2A. The thickness of the cys on gold is about 3 ± 1 Å, which corresponds to the formation of a short chain SAM⁴⁸, while fatty acid (oleic, stearic, elaidic) controls, grafted onto the cysteamine, provide a layer of about 17 Å, as expected for C18 molecules^{25,26}. Layer thicknesses of grafted glycolipids appear around 30 Å on average, which is consistent with the thickness measured by ellipsometry on monolayers of saccharide-functionalized alkanethiols.⁵⁰ Sophoro- and cellobioselipids layers containing disaccharides are thicker than 28 Å, whereas GL, which contains only a single glucose headgroup, forms a thinner layer of 22 ± 3 Å. Furthermore, the difference of about 6 Å observed in the thicknesses between a layer of GL (22 ± 3 Å) and SL (28 ± 2 Å) is intermediate between the length of a single glucose unit (about 10 Å^{53,54}) and the ellipsometric difference of 3 Å between monosaccharides and disaccharides adsorbed monolayers.⁵⁰ Differences among all glycolipids layers containing disaccharides (from 28 ± 2 Å for SL up to 37 ± 4 Å for CL) can be attributed to the variations in the carbohydrate headgroups, which may also contribute to changes in the configuration and density of the monolayers, although these are not obvious to determine here.^{48,55,56} A difference of a few Ångströms systematically characterizes the SL_a (33 ± 3 Å) and CL (37 ± 4 Å) layers, both containing either acetyl groups or short organic acid chain on the disaccharide, compared to the corresponding hydrolyzed compounds, SL (28 ± 2 Å) and CL_h (32 ± 2 Å) respectively. The wettability of all glycosylated surfaces was also examined and the water contact angle (WCA) was measured on each substrate (Figure 2B). Surfaces bearing only a fatty acid, or monosaccharide (GL), appear slightly less hydrophilic (with WCA between $65 \pm 2^\circ$ and $68 \pm 2^\circ$) than substrates functionalized with disaccharides ($WCA \leq 61 \pm 2^\circ$), regardless of their acetylation, their linkage to the unsaturated aliphatic chain or the isometry of the unsaturated aliphatic chain. On the contrary, the surfaces of saturated glycolipids (SL₀, CL, CL_h) have larger WCAs ($\geq 70 \pm 2^\circ$), as already observed before, and this may indicate a variation in the orientation of the sugars.²⁶

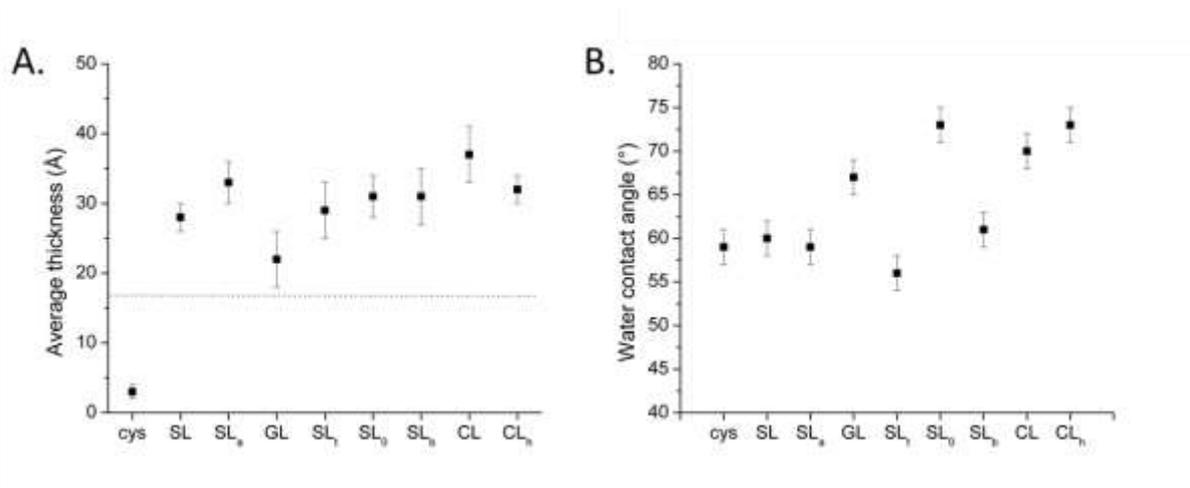

335

Figure 2. Physico-chemical properties of glycosylated surfaces.

(A) Thickness and (B) water contact angle measured on self-assembled monolayers of cysteamine (cys), deacetylated sophorolipid (SL), *cis* C18 sophorolipid (SL_a), glucolipid (GL), *trans* C18 sophorolipid (SL_t), branched sophorolipid (SL_b), cellobioselipid (CL), the saturated stearic acid sophorolipid (SL₀) and hydrolyzed cellobioselipid (CL_h). The dotted line indicates the average thickness of corresponding sugar-free lipids (oleic acid, stearic acid, elaidic acid) monolayers.

340

Antimicrobial activity

The biocidal effect of grafted oleic acid sophorolipids (SL) was tested against various Gram-positive and Gram-negative bacteria and it was shown that in the best case, depending on the type of microorganism, between 40% and 50% of the bacterial population was affected by the SL coating.^{25,26} Gram-positive bacteria appeared more susceptible and the non-pathogenic (to human) *Listeria ivanovii* strain was selected in this work as a standard. The protocol we developed to assess the biocidal activity of coated substrates involved the evaluation of bacterial adhesion to glycosylated surfaces and the resulting bacterial cultivability. Cultivability below adhesion indicates a biocidal effect against bacteria. These results were compared to the integrity of the bacterial membrane read using the Live/Dead fluorescent staining kit. All these data are normalized by the references obtained on biocompatible gold surfaces and are shown in Figure 3. The primer-modified gold substrate (cys) is a glycolipid-free control.

350

355

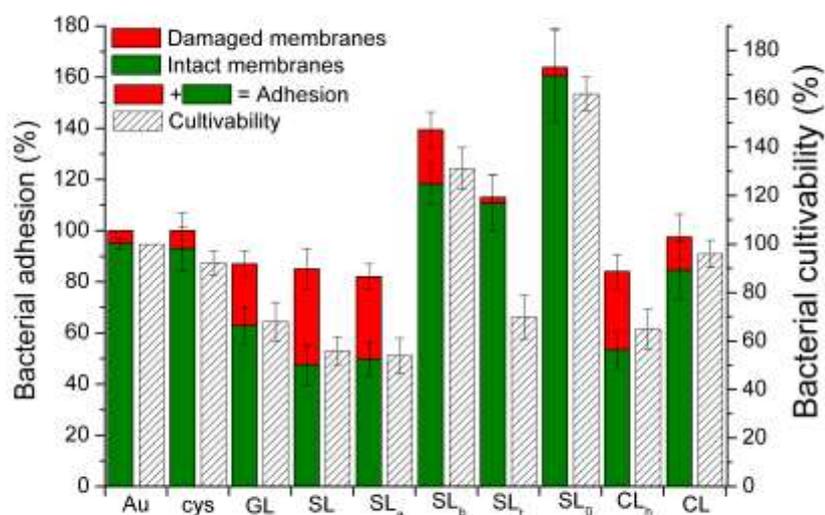


Figure 3. Antimicrobial properties of glycosylated surfaces.

360 Adhesion (bicolor bars, left axis) and cultivability (dashed bars, right axis) of *Listeria ivanovii* bacteria deposited on self-assembled monolayers of deacetylated sophorolipid (SL), *cis* C18 sophorolipid (SL_a), glucolipid (GL), *trans* C18 sophorolipid (SL_t), branched sophorolipid (SL_b), cellobioselipid (CL), the saturated stearic acid sophorolipid (SL₀) and hydrolyzed cellobioselipid (CL_h).

The results are relative to the same experiments performed on a bare gold substrate. The adhesive bars are colored according to the ratio of damaged (red) and intact (green) bacteria determined using the Live/Dead© kit.

Biocompatible gold (Au) surfaces and cysteamine (cys) monolayers constitute negative controls.

Biocidal properties of glycosylated surfaces

370 Bacterial adhesion is on average 15% lower on the glycosylated surfaces than on the negative control (Figure 3, red/green bars, left scale), confirming, for longer time scales (> 1 h), the antiadhesive effects attested at the nanoscale by single cell force microscopy.²⁴ Bacterial cultivability after contact with the substrates (Figure 3, dashed bars, right scale) matches bacterial adhesion for negative controls (Au, cys) and for SL₀ and CL samples, indicating that

375 no biocidal effect can be observed for the latter compounds. On the contrary, cultivability is systematically lower than adhesion for GL, SL, SL_a, SL_t and CL_h, suggesting a biocidal effect for these compounds. Furthermore, the decreases in cultivability are consistent with the fraction of the bacterial population with membrane damages (red portion of bicolor bars in Figure 3, left scale; an overview of images obtained using the Live/Dead staining kit is given in Figure S3),

380 suggesting that the biocidal effect of glycosylated surfaces is always due to membrane perturbations and alterations, which could be observed qualitatively by electron microscopy (Figure S4). It should be noted that grafted-glucose can damage some bacteria although they are capable of fermenting glucose units when they are free in solution⁵⁷. CL_h surfaces show a similar biocidal effect (35% reduction in bacterial cultivability correlated to 32% of
385 membranes-damaged cells). Thus, the antimicrobial properties of glycolipids surfaces are not directly correlated to sophorose itself, nor to the amount of glucose units, and they are not affected by the carbohydrate linkage in the glucidic moiety (sophorose being characterized by a β 1,2 glucose link, whereas CL_h has a deacetylated cellobiose (β 1,4 glucose) headgroup).

Effect of the carbohydrate valency on the biocidal properties

390 The number of glucose units appears as a key factor and grafted monosaccharides appear to be less active than disaccharides: the proportion of damaged bacteria is reduced by one third on GL coated substrates compared to the surfaces functionalized with the disaccharide-containing SL, of which the biocidal efficiency has previously been shown to be dependent to the surface density²⁵. These results are in line with various studies highlighting
395 the fact that the sugar density, as well as the sugar valency, are key parameters of carbohydrate properties and drive their interactions with the biomolecules^{58,59} and biomembranes⁶⁰. At low concentration, sugars may bind quite strongly to lipid bilayers and perturb their organization by their accumulation at the interface, while at high concentration sugars gradually become expelled from the membrane surface, and this repulsive mode of interaction counteracts
400 membrane disturbance⁶¹. Besides, the architecture of multivalent ligands is known to influence their affinities to receptors and to lead them to act either as effective inhibitors of protein binding, or as effectors of receptors clustering. For instance, high molecular weight polydisperse polyvalent mannose-bearing ligands inhibit the protein concanavalin A (Con A) binding, while linear oligomeric ligands favor clustering of this receptor.⁵⁸ Studies on
405 glycopolymers and glycodendrimers also demonstrate that not only the number of ligand groups matters, but also the spacer connecting the sugar to the scaffold.⁶¹ The effect of the carbohydrate valency observed here is also reminiscent to the charge-density threshold for optimal efficiency of biocide cationic surfaces.⁶²

Effect of the glycolipid conformation on the biocidal properties

Data in Figure 3 also provide some pieces of information on the conformational effects of carbohydrates after grafting on the surface. While SL, SL₀ and SL₁ coatings display the same

headgroup (deacetylated sophorose) and similar layer thickness strong differences are observed in their biocidal properties. These latter are then attributed to conformation changes expected among monounsaturated *cis* and *trans* isomers, and saturated chains. One can reasonably consider that the saturation/unsaturation features of the lipid backbone play an important role. The conformation of the SL aliphatic chain is known to be important: our previous study, confirmed here, demonstrates that saturated SL₀ coatings do not exhibit any antimicrobial properties²⁶ contrary to the monounsaturated SL coatings. The *trans* isomer SL_t exhibits intermediate properties between the *cis* isomer of SL and the saturated molecules: it seems to promote the microbial adhesion (increased up to 113%) but it is responsible for a decrease of their cultivability (of 30%).

Impact of the carbohydrate accessibility on the biocidal properties

Acetylation first does not seem to play an important role, since SL and SL_a have comparable biocidal effects, suggesting that the moieties on C6' and C6'' positions on sophorose do not have a critical role in biocidal activity. On the contrary, the acetyl moieties and fatty acid esters carried by cellobiose units in CL sample appear to interfere the biocidal activities of the anchored molecules when compared to hydrolyzed CL_h.

However, it should be kept in mind that SL_a carry only acetyl groups, while C6 fatty esters are covalently attached to CL, and may limit the carbohydrate accessibility. The difference in biocidal behavior between CL and SL_a could also result from the position of the acetyl groups and the linkage of the carbohydrate units to the aliphatic chain. Unfortunately, the microbial synthesis of CL and SL derivatives does not provide all the molecular intermediates necessary for a systematic study, and synthetic compounds would be needed to discriminate the influence of the mentioned parameters. Nevertheless, the accessibility of carbohydrates moieties is certainly a key parameter when examining antibacterial activity. In the case of SL_b, the relative position of the sophorose units seems identical to that of SL, but the presence of the saturated lateral chain, allowing the rotation of the sophorose unit, reduces the killing efficiency to only 16 % compare to 44 % for SL. However, if SL_b is compared to SL_t or SL₀, its activity is 5 time higher than that of the latter ones, probably due to a ratio of positioned as in SL layers.

DISCUSSION

It has been demonstrated that slight variations in the glycolipids structures lead to different behavior in solution, e.g. variations of alkyl chains or sugar acetylation of rhamnolipids affect not only their physical properties (cmc, surface tension, acyl chain fluidity,

structure of the aggregated state), but also the interactions of these compounds with living organisms (ability to insert into membranes)⁶³. Similarly, the present work shows that glycosylated substrates exhibit different antimicrobial properties depending on the carbohydrates and their anchoring to the surface. The molecular variations studied here allow the identification of certain key parameters.

The "cleavage" of sophorose into a simple glucose moiety (GL compound) decreases the killing efficiency of functionalized surfaces without affecting the mechanism of action (lysis of bacterial membranes and decrease in the cultivability of microorganisms). Thus, the number of sugars seems to be correlated with the interactions between bacteria and glycosylated surfaces. This is not surprising: the multivalence of glycoconjugate compounds (and their assemblages) is considered to be very important in developing effective interactions with other molecules:⁶⁴ the higher the sugar valency, the more effective the conjugate interactions with their molecular environment, sugars and proteins in particular (the individual interactions between these compounds being relatively weak)⁶⁵. Ligand-receptor recognition phenomena, in the manner of a molecular "Velcro"TM ⁶⁶ are then favored. A parallelism could be established between these works and the relative improvement in the membrane damage phenomena observed here when switching from a mono to a disaccharide. However, multivalency is probably not the only parameter to be taken into account, as the conformation of carbohydrates on the surface, the other molecular variations studied in this work, seems to be of the utmost importance.

The biocidal effect is minimized, or even disappears, when the geometry of the lipid chain is modified. Variation of the degree of saturation of the aliphatic chain (SL vs. SL₀) affects biocidal activity, surface wettability and appears to influence the orientation of the sophorose groups. Thus, the conformation of carbohydrate units emerges as a key parameter in the interactions between sophorolipids and microorganisms. This observation suggests that the phenomena observed are not specific to sophorose *per se* but rather induced by the molecular arrangement and orientation of certain hydroxyl groups. Similar observations have been reported recently in the field of glycobiology. The creation of glycosylated surfaces with azobenzene-containing ligands, whose orientation can be controlled by applying a light stimulus, has demonstrated the influence of sugar orientation on bacterial adhesion. Modification of the chirality of glycosylated dendrimers has also been shown to have an impact on the adhesion of *Escherichia coli*.⁶⁷ In these studies, variations in bacterial adhesion are interpreted as an alteration of specific recognition phenomena between dendrimers sugars and bacterial cell wall receptors. Comparison between the phenomena described in these studies

and this work could constitute an argument for a biochemical explanation of the biocidal action of glycolipids. However, the nature of the phenomena studied here is not strictly the same. In this work, bacterial adhesion is minimal on surfaces functionalized with monounsaturated fatty acids (OA derivatives), whereas samples functionalized with saturated fatty acid (SA derivatives) seem rather favorable to microbial adhesion (Figure 3). Thus, the behavior of bacteria seems to be affected by the saturation of the lipid chain, even in the absence of sugars, which is not the case in other studies.⁶⁷ The differences observed between surfaces functionalized with saturated and monounsaturated glycolipids may therefore not only be related to biochemical criteria. More generally, sugars are known to play a key role in the (de)stabilization of the biological system both in vivo and in vitro, either by influence the solvating shell of biomolecules or by specifically interacting with biological molecules (direct sugar-molecule binding at the interface)⁶⁸ and several studies on the antimicrobial activity of glycolipids in solution suggest biophysical, rather than biochemical, effects, as it has been discussed for cellobioselipids⁶⁹. However, grafting of these compounds onto a surface limits the antimicrobial activity unless cellobioselipids are hydrolyzed: our data show that CL_h has an impact on the membrane integrity of *L. ivanovii*. Interestingly, the hydroxylated form of CL is considered less bioactive against *fungus* and *bacteria* in solution.^{35,70} These experiments confirm that the phenomena observed are not specific to sophorolipid, as previously assumed,²⁶ but they can be reproduced on surfaces coated with other glycoconjugate molecules. The conformation of the sugars is an important parameter to consider. Specifically, the orientation and availability of specific C-OH groups appears to be critical. Indeed, acetylation of the C-OH groups in the 6' and 6'' positions does not affect the antimicrobial activity of grafted sophorolipids, suggesting that the C6' and C6'' carbons of sophorose do not play a determining role in biocidal activity, while esterification of the 2'' and 6' positions in cellobioselipid inactivates it.

505

CONCLUSION

In this work, we have shown that self-assembled monolayers of microbial-derived glycolipids can be chemically grafted onto a gold substrate using a cysteamine primer; the surfaces thus modified have antibacterial properties against Gram⁺ bacteria *Listeria ivanovii*, with an efficiency that depends on the chemical and structural composition of the SL derivative. Surfaces analyses estimate thicknesses to be very close for each SL derivative, ensuring an almost identical molecular surface density for all the different substrates. The bacterial killing efficiency (corrected by the bacterial adhesion) can be up to 44% at best and as low as 2 % at worst, which is close to the statistical bacterial death observed in standard controls (Au and

510

515 cysteamine primer). From a mechanistic point of view, our results show that several parameters influence the killing efficiency and bacterial adhesion, such as the saturation and conformation of the fatty acid backbone, the number of glucose units in the head group or the sugar lateral chains. Thus, our results highlight that for sophorolipids with the same sugar head groups, the unsaturation of the fatty acid backbone is required and the *cis* conformation (SL) will have a
520 higher antibacterial activity when compared to the *trans* conformation (SL_t; in addition, the number of glucose unit is also a key factor, a decrease of one third of the antibacterial activity is observed by omitting one glucose unit (GL) in relation to two (SL).

ACKNOWLEDGMENTS

525 This work was supported by French state funds managed by the ANR within the Investissements d'Avenir program under Reference ANR-11-IDEX-0004-02 and more specifically within the framework of the Cluster of Excellence MATISSE. The authors acknowledge IMPC (Institut des Matériaux de Paris Centre, FR CNRS 2482) and the C'Nano projects of the Region Ile-de-France, Omicron XPS apparatus funding. The authors would also
530 like to thank Dr P. L. V. Baghavatula from CSIR is acknowledged for providing the SL_t compound, Christophe Calers and Dr. Christophe Méthivier from LRS for their help with XPS analyses and Sandra Casale for her help in acquiring SEM-FEG data.

REFERENCES

535

1. L. H. G. Morton and S. B. Surman, *Int. Biodeterior. Biodegradation*, 1994, **34**, 203-221.
2. J. D. Bryers, *Biotechnol. Bioeng.*, 2008, **100**, 1-18.
3. N. R. B. Boase, M. D. T. Torres, N. L. Fletcher, C. d. I. Fuente-Nunez and K. E. Fairfull-Smith, *Polym. Chem.*, 2018, **9**, 5308-5318.
- 540 4. B. Meyer, *Int. Biodeterior. Biodegradation*, 2003, **51**, 249-253.
5. A. D. Verderosa, M. Totsika and K. E. Fairfull-Smith, *Front. Chem.*, 2019, **7**, 824.
6. J. Hasan, R. J. Crawford and E. P. Ivanova, *Trends Biotechnol.*, 2013, **31**, 295-304.
7. D. M. Yebra, S. Kiil and K. Dam-Johansen, *Prog. Org. Coat.*, 2004, **50**, 75-104.
8. M. E. Forman, M. C. Jennings, W. M. Wuest and K. P. Minbiole, *Chem. Med. Chem.*, 2016, **11**, 1401-1405.
- 545 9. I. M. Banat, A. Franzetti, I. Gandolfi, G. Bestetti, M. G. Martinotti, L. Fracchia, T. J. Smyth and R. Marchant, *Appl. Microbiol. Biotechnol.*, 2010, **87**, 427-444.
10. M. Sun, J. Dong, Y. Xia and R. Shu, *Microb. Pathog.*, 2017, **107**, 212-218.
11. M. Sun, Z. Zhou, J. Dong, J. Zhang, Y. Xia and R. Shu, *Microb. Pathog.*, 2016, **99**, 196-203.
- 550 12. B. K. Yoon, J. A. Jackman, E. R. Valle-González and N.-J. Cho, *Int. J. Mol. Sci.*, 2018, **19**, 1114.
13. D. Kitamoto, H. Yanagishita, T. Shinbo, T. Nakane, C. Kamisawa and T. Nakahara, *J. Biotechnol.*, 1993, **29**, 91-96.
14. S. Lang, E. Katsiwela and F. Wagner, *Fett. Wiss. Technol. Sci. Technol.*, 1989, **91**, 363-366.
15. A. L. S. Coelho, P. E. Feuser, B. A. M. Carciofi, C. J. de Andrade and D. de Oliveira, *Appl. Microbiol. Biotechnol.*, 2020, **104**, 2297-2318.
- 555 16. L. Rodrigues, I. M. Banat, J. Teixeira and R. Oliveira, *J. Antimicrob. Chemother.*, 2006, **104**, 2297-2318.
17. J. M. Farias, T. C. M. Stamford, A. H. M. Resende, J. S. Aguiar, R. D. Rufino, J. M. Luna and L. A. Sarubbo, *Int. J. Biol. Macromol.*, 2019, **129**, 853-860.
- 560 18. J. Hage-Hülsmann, A. Grünberger, S. Thies, B. Santiago-Schübel, A. S. Klein, J. Pietruszka, D. Binder, F. Hilgers, A. Domröse, T. Drepper, D. Kohlheyer, K.-E. Jaeger and A. Loeschcke, *PLoS One* 2018, **13**, e200940.
19. C. A. Marangon, V. C. A. Martins, M. H. Ling, C. C. Melo, A. M. G. Plepis, R. L. Meyer and M. Nitschke, *ACS Appl. Mater. Interfaces*, 2020, **12**, 5488-54989.
- 565 20. C. Ceresa, L. Fracchia, M. Williams, I. M. Banat and M. A. Díaz De Rienzo, *J. Biotechnol.*, 2020, **309**, 34-43.
21. M. Ohadi, H. Forootanfar, G. Dehghannoudeh, T. Eslaminejad, A. Ameri, M. Shakibaie and M. Adeli-Sardou, *Microb. Pathog.*, 2020, **138**, 103806.
22. Q. Shu, T. Wei, H. Lu, Y. Niu and Q. Chen, *Appl. Microbiol. Biotechnol.*, 2020, **104**, 5053-5064.
- 570 23. M. Elshikh, I. Moya-Ramírez, H. Moens, S. Roelants, W. Soetaert, R. Marchant and I. M. Banat, *J. Appl. Microbiol.*, 2017, **123**, 1111-1123.
24. C. Valotteau, N. Baccile, V. Humblot, S. Roelants, W. Soetaert, C. V. Stevens and Y. F. Dufrêne, *Nanoscale Horiz.*, 2019, **4**, 975-982.
25. C. Valotteau, I. Banat, C. Mitchell, H. Lydon, F. Babonneau, C.-M. Pradier, N. Baccile and V. Humblot, *Coll. Surf. B*, 2017, **157**, 325-334.
- 575 26. C. Valotteau, C. Calers, S. Casale, J. Berton, C. V. Stevens, F. Babonneau, C.-M. Pradier, V. Humblot and N. Baccile, *ACS Appl. Mater. Interfaces*, 2015, **7**, 18086-18095.
27. V. Shah, D. Badia and P. Ratsep, *Antimicrob. Agents Chemother.*, 2007, **51**, 397-400.
28. N. Laurent, J. Voglmeir and S. L. Flitsch, *Chem. Comm.*, 2008, **37**, 4400-4412.
- 580 29. K. Larsen, M. B. Thygesen, F. Guillaumie, W. G. T. Willats and K. J. Jensen, *Carbohydr. Res.*, 2006, **341**, 1209-1234.
30. R. Liang, J. Loebach, N. Horan, M. Ge, C. Thompson, L. Yan and D. Kahne, *Proc. Natl. Acad. Sci. USA*, 1997, **94**, 10554-10559.

- 585 31. R. T. Otto, H. J. Daniel, G. Pekin, K. Müller-Decker, G. Fürstenberger, M. Reuss and C. Syldatk, *Appl. Microbiol. Biotechnol.*, 1999, **52**, 495-501.
32. M. R. d. Oliveira, A. Magri, C. Baldo, D. Camilios-Neto, T. Minucelli and M. A. P. C. Celligoi, *Int. J. Adv. Biotechnol. Res.*, 2015, **6**, 161-174.
33. U. Rau, R. Heckmann, V. Wray and S. Lang, *Biotechnol. Lett.*, 1999, **21**, 973-977.
34. K. M. Saerens, L. Saey and W. Soetaert, *Biotechnol. Bioeng.*, 2011, **108**, 2923-2931.
- 590 35. E. Kulakovskaya, B. Baskunov and A. Zvonarev, *J. Oleo Sci.*, 2014, **63**, 701-707.
36. N. Baccile, A.-S. Cuvier, C. Valotteau and I. N. A. Van Bogaert, *Eur. J. Lipid. Sci. Technol.*, 2013, **115**, 1404-1412.
37. A.-S. Cuvier, J. Berton, C. V. Stevens, G. C. Fadda, F. Babonneau, I. N. Van Bogaert, W. Soetaert, G. Pehau-Arnaudet and N. Baccile, *Soft Matter*, 2014, **10**, 3950-3959.
- 595 38. K. Ciesielska, I. N. V. Bogaert, S. Chevineau, B. Li, S. Groeneboer, W. Soetaert, Y. V. d. Peer and B. Devreese, *J. Proteomics*, 2014, **98**, 159-174.
39. N. Baccile, F. Babonneau, I. M. Banat, K. Ciesielska, A.-S. Cuvier, B. Devreese, B. Everaert, H. Lydon, R. Marchant, C. A. Mitchell, S. Roelants, L. Six, E. Theeuwes, G. Tsatsos, G. E. Tsotsou, B. Vanlerberghe, I. N. A. V. Bogaert and W. Soetaert, *ACS Sustain. Chem. Eng.*, 2017, **5**, 1186-1198.
- 600 40. K. M. J. Saerens, J. Zhang, L. Saey, I. N. A. V. Bogaert and W. Soetaert, *Yeast*, 2011, **28**, 279-292.
41. N. Baccile, M. Selmane, P. L. Griel, S. Prévost, J. Perez, C. V. Stevens, E. Delbeke, S. Zibek, M. Guenther, W. Soetaert, I. N. A. V. Bogaert and S. Roelants, *Langmuir*, 2016, **32**, 6343-6359.
42. P. Dhasaiyan, S. Prévost, N. Baccile and B. L. V. Prasad, *Langmuir*, 2018, **34**, 2121-2131.
- 605 43. N. Baccile, P. L. Griel, S. Prévost, B. Everaert, I. N. A. V. Bogaert, S. Roelants and W. Soetaert, *ChemistryOpen*, 2017, **6**, 526-533.
44. A. P. Tulloch, A. Hill and J. F. T. Spencer, *Can. J. Chem.*, 1968, **46**, 3337-3351.
45. S. Spoekner, V. Wray, M. Nimtz and S. Lang, *Appl. Microbiol. Biotech.*, 1999, **51**, 33-39.
46. J. H. Scofield, *J. Electron. Spectrosc. Relat. Phenom.*, 1976, **8**, 129-137.
- 610 47. J. Yala, P. Thebault, A. Hequet, V. Humblot, C.-M. Pradier and J. Berjeaud, *Appl. Microbiol. Biotechnol.*, 2011, **89**, 623-634.
48. M. D. Porter, T. B. Bright, D. L. Allara and C. E. D. Chidsey, *J. Am. Chem. Soc.*, 1987, **109**, 3559-3568.
49. R. G. Nuzzo, L. H. Dubois and D. L. Allara, *J. Am. Chem. Soc.*, 1990, **112**, 558-569.
- 615 50. T. Fyrner, H.-H. Lee, A. Mangone, T. Ekblad, M. E. Pettitt, M. E. Callow, J. A. Callow, S. L. Conlan, R. Mutton, A. S. Clare, P. Konradsson, B. Liedberg and T. Ederth, *Langmuir*, 2011, **27**, 15034-15047.
51. M. Hederos, P. Konradsson and B. Liedberg, *Langmuir*, 2005, **21**, 2971-1980.
52. J. S. Stevens and S. L. M. Schroeder, *Surf. Inter. Anal.*, 2009, **41**, 453-462.
- 620 53. S. Abel, F.-Y. Dupradeau, E. P. Raman, A. D. MacKerell, Jr. and M. Marchi, *J. Phys. Chem. B*, 2011, **115**, 487-499.
54. L. R. Winther, J. Qvist and B. Halle, *J. Phys. Chem. B*, 2012, **116**, 9196-9207.
55. F. Tielens, D. Costa, V. Humblot and C. M. Pradier, *J. Phys. Chem. C*, 2008, **112**, 182-190.
56. F. Tielens, V. Humblot, C. M. Pradier, M. Calatayud and F. Illas, *Langmuir*, 2009, **25**, 9980-9985.
- 625 57. <https://www.vetbact.org/index.php?artid=168&vbsearchstring=Listeria%20ivanovii>.
58. C. W. Cairo, J. E. Gestwicki, M. Kanai and L. L. Kiessling, *J. Am. Chem. Soc.*, 2002, **124**, 1615-1619.
59. M. C. Galan, P. Dumy and O. Renaudet, *Chem. Soc. Rev.*, 2013, **42**, 4599-4612.
60. H. D. Andersen, C. Wang, L. Arleth, G. H. Peters and P. Westh, *Proc. Natl. Acad. Sci. USA*, 2011, **108**, 1874-1878.
- 630 61. T. R. Branson and W. B. Turnbull, *Chem. Soc. Rev.*, 2013, **42**, 4613-4622.
62. R. Kugler, O. Bouloussa and F. Rondelez, *Microbiology*, 2005, **151**, 1341-1348.
63. J. Howe, J. Bauer, J. Andrä, A. B. Schromm, M. Ernst, M. Rössle, U. Zähringer, J. Rademann and K. Brandenburg, *FEBS J.*, 2006, **273**, 5101-5112.

- 635 64. A. Bernardi, J. Jiménez-Barbero, A. Casnati, C. D. Castro, T. Darbre, F. Fieschi, J. Finne, H. Funken, K.-E. Jaeger, M. Lahmann, T. K. Lindhorst, M. Marradi, P. Messner, A. Molinaro, P. V. Murphy, C. Nativi, S. Oscarson, S. Penadés, F. Peri, R. J. Pieters, O. Renaudet, J.-L. Reymond, B. Richichi, J. Rojo, F. Sansone, C. Schäffer, W. B. Turnbull, T. Velasco-Torrijos, S. Vidal, S. Vincent, T. Wennekes, H. Zuilhof and A. Imberty, *Chem. Soc. Rev.*, 2013, **42**, 4709-4727.
- 640 65. A. Martinez, C. Ortiz Mellet and J. M. Garcia Fernandez, *Chem. Soc. Rev.*, 2013, **42**, 4746-4773.
66. R. J. Pieters, *Org. Biomol. Chem.*, 2009, **7**, 2013-2025.
67. E. M. V. Johansson, R. U. Kadam, G. Rispoli, S. A. Crusz, K.-M. Bartels, S. P. Diggle, M. Camara, P. Williams, K.-E. Jaeger, T. Darbre and J.-L. Reymond, *Med. Chem. Comm.*, 2011, **2**, 418-420.
68. K. B. Konov, D. V. Leonov, N. P. Isaev, K. Y. Fedotov, V. K. Voronkova and S. A. Dzuba, *J. Phys. Chem. B*, 2015, **119**, 10261-10266.
- 645 69. B. Mimee, R. Pelletier and R. R. Belanger, *J. Appl. Microbiol.*, 2009, **107**, 989-996.
70. T. Kulakovskaya, A. Shashkov, E. Kulakovskaya, W. Golubev, A. Zinin, Y. Tsvetkov, A. Grachev and N. Nifantiev, *J. Oleo Sci.*, 2009, **58**, 133-140.

650

FIGURE LEGENDS

Figure 1. Set of microbial glycolipids presenting rational variation of the glycosidic headgroup (horizontally) and chain configuration (vertically).

655 The different acid chains are shown in grey as references.
3 glycolipids have a *cis* C18 oleic acid (OA) chain: the typical sophorolipid (SL), the acetylated sophorolipid (SL_a) and the glucolipid (GL).
The *trans* sophorolipid (SL_t) has a *trans* C18 elaidic acid (EA) chain.
The last glycolipids have a fully saturated chain: the saturated stearic acid (SA) sophorolipid (SL₀), the branched sophorolipid (SL_b), the cellobioselipid (CL) and the hydrolysed cellobioselipid (CL_h). For the latter, R1=H or OH and R2= H or OH, as described in the materials and method section.

Figure 2. Physico-chemical properties of glycosylated surfaces.

665 (A) Thickness and (B) water contact angle measured on self-assembled monolayers of cysteamine (cys), deacetylated sophorolipid (SL), *cis* C18 sophorolipid (SL_a), glucolipid (GL), *trans* C18 sophorolipid (SL_t), branched sophorolipid (SL_b), cellobioselipid (CL), the saturated stearic acid sophorolipid (SL₀) and hydrolyzed cellobioselipid (CL_h). The dotted line indicates the average thickness of corresponding sugar-free lipids (oleic acid, stearic acid, elaidic acid) monolayers²⁵.

Figure 3. Antimicrobial properties of glycosylated surfaces.

675 Adhesion (bicolor bars, left axis) and cultivability (dashed bars, right axis) of *Listeria ivanovii* bacteria deposited on self-assembled monolayers of deacetylated sophorolipid (SL), *cis* C18 sophorolipid (SL_a), glucolipid (GL), *trans* C18 sophorolipid (SL_t), branched sophorolipid (SL_b), cellobioselipid (CL), the saturated stearic acid sophorolipid (SL₀) and hydrolyzed cellobioselipid (CL_h).

The results are relative to the same experiments performed on a bare gold substrate. The adhesive bars are colored according to the ratio of damaged (red) and intact (green) bacteria determined using the Live/Dead© kit.

Biocompatible gold (Au) surfaces and cysteamine (cys) monolayers constitute negative controls.

Figure S1. PM-RAIRS spectra of self-assembled monolayers of glucolipid (GL), *cis* C18 sophorolipid (SL_a), branched sophorolipid (SL_b), *trans* C18 sophorolipid (SL_t), cellobioselipid

685 (CL) and hydrolyzed cellobioselipid (CL_h). The resonance signal at 1648 cm⁻¹ (ν_{C=O} in amide) and 1562 cm⁻¹ (ν_{CN} and δ_{NH}) are characteristic of amide bonds. The presence of aliphatic chains is attested by vibrational bands at 3000-2800 cm⁻¹ (ν_S and ν_{AS} of CH₂ and ν_S of CH₃) and 1400 cm⁻¹ (ω_{CH2}). The signal of carbohydrates resonates at 1200-1000 cm⁻¹ (δ_{CO}), where a multitude of bands are partially overlapped and therefore difficult to interpret in detail. The elongation of
690 the C=O bonds on acetyl moieties produces an additional band at 1740 cm⁻¹ on spectra of substrates prepared with acetylated SL_a and CL

Figure S2. High resolution standardized XPS spectra of the C1s (left) and N1s (right) regions recorded on self-assembled monolayers of glucolipid (GL), *cis* C18 sphorolipid (SL_a),
695 branched sphorolipid (SL_b), *trans* C18 sphorolipid (SL_t), cellobioselipid (CL) and hydrolyzed cellobioselipid (CL_h). The peak at 284.8 ± 0.1 eV in the C1s region attests the presence of an aliphatic chains while the two contributions, at 286.4 ± 0.1eV (C-OH) and 287.7 ± 0.1eV (O-C-O) are the signature of the carbohydrate groups, also visible in the O1s. The shift of the nitrogen signal from 401.8 ± 0.1 eV (NH₃⁺) on cys primer layer towards 399.9 ± 0.1 eV
700 (NH₂ and NH in amide) after immersion on glycolipids solution demonstrate that the glycolipids are grafted via amide bonds.

Figure S3. Fluorescent staining evidences membrane damages of bacteria (*L. ivanovii*) deposited on self-assembled monolayers of glucolipid (GL), deacetylated sphorolipid (SL),
705 *cis* C18 sphorolipid (SL_a), *trans* C18 sphorolipid (SL_t), saturated sphorolipid (SL₀), hydrolyzed cellobioselipid (CL_h) and cellobioselipid (CL).

Biocompatible gold (Au) surfaces and cysteamine (cys) monolayers constitute negative controls. The chart above each image represents the proportion of adhering intact (percentage given) and damaged bacteria according to fluorescent staining.

710

Figure S4. Scanning electron microscopy reveals qualitative morphological alterations (highlighted by white arrows) of bacteria (*L. ivanovii*) deposited on self-assembled monolayers of glucolipid (GL), deacetylated sphorolipid (SL), *cis* C18 sphorolipid (SL_a), *trans* C18 sphorolipid (SL_t), saturated sphorolipid (SL₀), cellobioselipid (CL) and hydrolyzed
715 cellobioselipid (CL_h).Biocompatible gold (Au) surfaces and cysteamine (cys) monolayers constitute negative controls.

