



HAL
open science

Investigating the Perovskite $\text{Ag}_{1-3x}\text{La}_x\text{NbO}_3$ as a High-Rate Negative Electrode for Li-Ion Batteries

Etienne Le Calvez, Julio César Espinosa-Angeles, Grace Whang, Nicolas Dupré, Bruce Dunn, Olivier Crosnier, Thierry Brousse

► **To cite this version:**

Etienne Le Calvez, Julio César Espinosa-Angeles, Grace Whang, Nicolas Dupré, Bruce Dunn, et al.. Investigating the Perovskite $\text{Ag}_{1-3x}\text{La}_x\text{NbO}_3$ as a High-Rate Negative Electrode for Li-Ion Batteries. *Frontiers in Chemistry*, 2022, 10, pp.873783. 10.3389/fchem.2022.873783 . hal-03686557

HAL Id: hal-03686557

<https://hal.science/hal-03686557>

Submitted on 7 Jul 2022

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Investigating the Perovskite $\text{Ag}_{1-3x}\text{La}_x\text{NbO}_3$ as a High-Rate Negative Electrode for Li-Ion Batteries

Etienne Le Calvez^{1,2}, Julio César Espinosa-Angeles^{1,2}, Grace J. Whang³, Nicolas Dupré¹, Bruce S. Dunn³, Olivier Crosnier^{1,2} and Thierry Brousse^{1,2*}

¹Nantes Université, CNRS, Institut des Matériaux de Nantes Jean Rouxel, IMN, Nantes, France, ²Réseau sur le Stockage Electrochimique de l'Energie (RS2E), CNRS FR 3459, Amiens Cedex, France, ³Department of Materials Science and Engineering, University of California, Los Angeles, Los Angeles, CA, United States

The broader development of the electric car for tomorrow's mobility requires the emergence of new fast-charging negative electrode materials to replace graphite in Li-ion batteries. In this area, the design of new compounds using innovative approaches could be the key to discovering new negative electrode materials that allow for faster charging and discharging processes. Here, we present a partially substituted AgNbO_3 perovskite material by introducing lanthanum in the A-site. By creating two vacancies for every lanthanum introduced in the structure, the resulting general formula becomes $\text{Ag}_{1-3x}\text{La}_x\text{NbO}_{3-2x}$ (with $x \leq 0.20$ and where \square is a A-site vacancy), allowing the insertion of lithium ions. The highly substituted $\text{Ag}_{0.40}\text{La}_{0.20}\text{NbO}_{3-0.40}$ oxide shows a specific capacity of $40 \text{ mAh}\cdot\text{g}^{-1}$ at a low sweep rate (0.1 mV s^{-1}). Interestingly, $\text{Ag}_{0.70}\text{La}_{0.10}\text{NbO}_{3-0.20}$ retains 64% of its capacity at a very high sweep rate (50 mV s^{-1}) and about 95% after 800 cycles. *Ex situ* ⁷Li MAS NMR experiments confirmed the insertion of lithium ions in these materials. A kinetic analysis of $\text{Ag}_{1-3x}\text{La}_x\text{NbO}_{3-2x}$ underlines the ability to store charge without solid-state ion-diffusion limitations. Furthermore, *in situ* XRD indicates no structural modification of the compound when accommodating lithium ions, which can be considered as zero-strain material. This finding explains the interesting capacity retention observed after 800 cycles. This paper thus demonstrates an alternative approach to traditional insertion materials and identifies a different way to explore not-so common electrode materials for fast energy storage application.

Keywords: silver niobate, lithium-ion battery, high rate anode material, fast charging, innovative oxide

INTRODUCTION

To eliminate our dependence on carbon-based energy production, specifically in the field of mobility, it is essential to develop energy storage devices able to store the intermittent energy harvested by renewable energy sources (Armand and Tarascon 2008). A key to the deployment of electric vehicles is the ability of batteries to charge quickly while ensuring long cycle life, and optimized safety (Burnham et al., 2017; Li et al., 2020). The current use of graphite as a negative electrode only partially satisfies these needs (Choi et al., 2020). In fast-charging batteries, graphite enables the insertion of lithium at an average potential close to that of Li^+/Li ($0.1 \text{ V vs. Li}^+/\text{Li}$), which can lead to the formation of lithium plating followed by dendrite growth, resulting in possible short circuits and thermal runaway. Moreover, the specific capacity of graphite is drastically reduced at high current

OPEN ACCESS

Edited by:

Yohan Dall'Agnese,
University College London,
United Kingdom

Reviewed by:

Martin Wilkening,
Graz University of Technology, Austria
Xiao-Dong Zhu,
Qingdao University of Science and
Technology, China

*Correspondence:

Thierry Brousse
thierry.brousse@univ-nantes.fr

Specialty section:

This article was submitted to
Electrochemistry,
a section of the journal
Frontiers in Chemistry


Received: 11 February 2022

Accepted: 18 March 2022

Published: 13 April 2022

Citation:

Le Calvez E, Espinosa-Angeles JC,
Whang GJ, Dupré N, Dunn BS,
Crosnier O and Brousse T (2022)
Investigating the Perovskite $\text{Ag}_{1-3x}\text{La}_x\text{NbO}_3$ as a High-Rate Negative
Electrode for Li-Ion Batteries.
Front. Chem. 10:873783.
doi: 10.3389/fchem.2022.873783

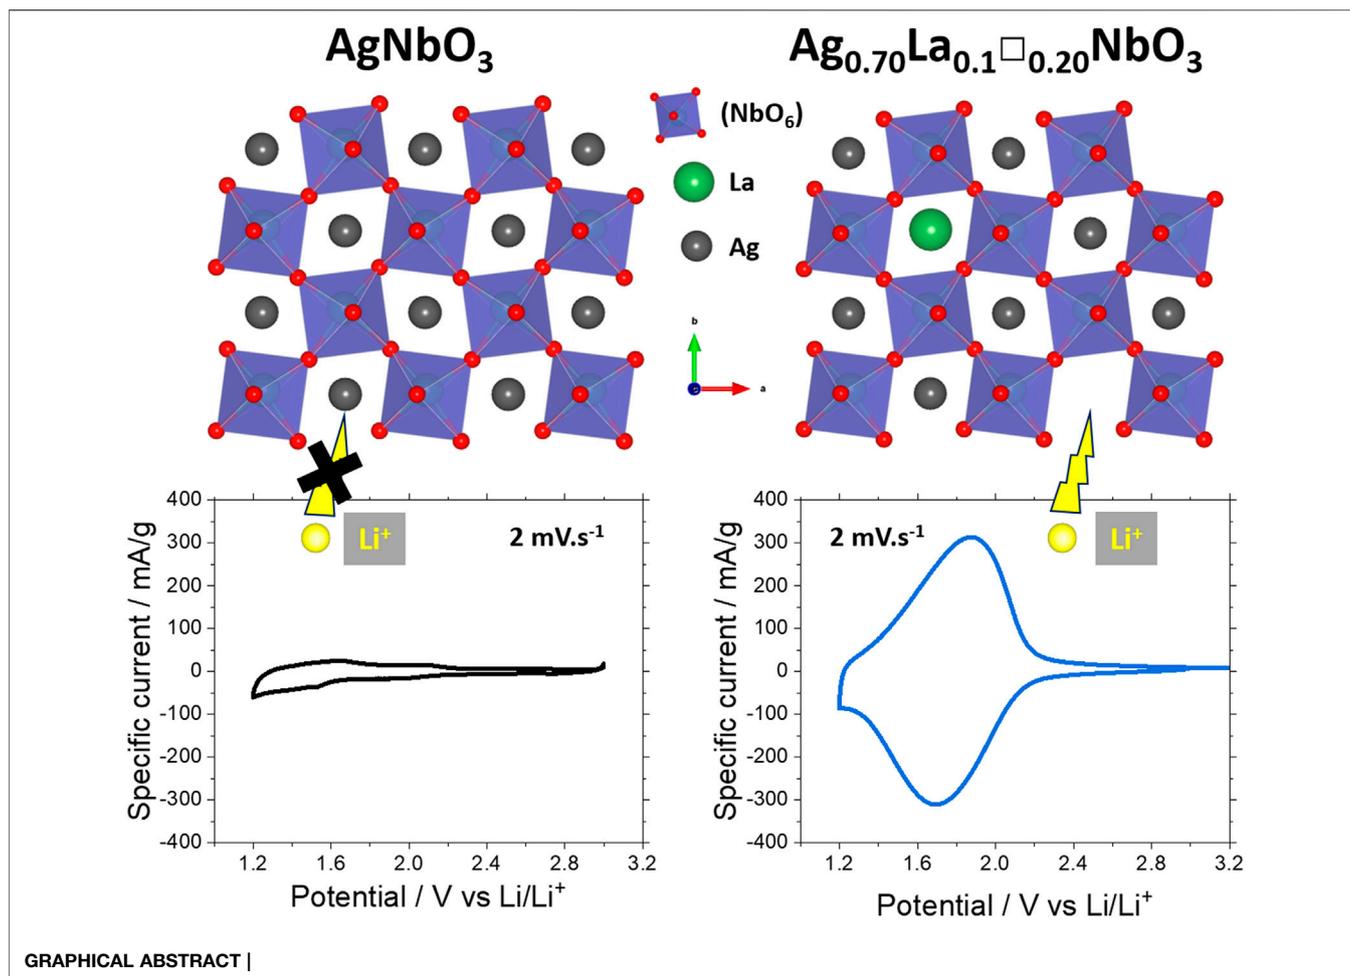

densities due to kinetic limitations on ion mobility between graphene layers (Sivakkumar et al., 2010).

For these reasons, alternative negative electrode materials have attracted increased attention over the past decade. One of the best known negative electrode materials for high-rate applications is Li₄Ti₅O₁₂ (LTO) (Prakash et al., 2010; Song et al., 2014; Thackeray and Amine 2021). Crystallizing in a spinel structure, this zero strain material offers an alternative route towards designing fast charging batteries with a relatively high specific capacity. Moreover, new approaches have been proposed to offer more options for the replacement of graphite electrode. Among others, shear-structure materials including TiNb₂O₇ (Griffith et al., 2019) or Nb₁₆W₁₈O₉₃ (Griffith et al., 2018) offer relatively large capacity values at high rate between 1V and 3V vs. Li⁺/Li. Low volume changes upon lithium insertion and an operating potential that avoids the formation of lithium-consuming solid electrolyte interphase (SEI) are the main advantages offered by these materials. In addition, a new approach has recently been proposed to transform a material traditionally used as an ionic conductor into a material for high-rate Na-ion batteries. Partial substitution of Al by Fe in β"-Al₂O₃ offers both ionic and electronic conduction, allowing fast and reversible Na⁺ intercalation (Butts et al., 2021). This material displays cyclic voltammogram with broad peaks attributed to a surface-controlled charge storage

mechanism. Similar approaches are needed to unravel different fast charging materials and their associated mechanisms.

In this work, we propose an alternative way to produce materials that can insert alkali cations with minor diffusion limitation, thus allowing high current density operation. More precisely, the A-site of AgNbO₃ perovskite synthesized by sol-gel process has been partially substituted by lanthanum (La³⁺), allowing the creation of vacancies in this crystallographic site. Insertion of Li ions is observed in every substituted Ag_{1-3x}La_x□_{2x}NbO₃ compound (with x > 0), thus leading to experimental specific capacities close to the theoretical values. Calculation of b-value shows a non-diffusion-controlled mechanism and *in situ* XRD shows negligible volume expansion (zero strain electrode) during the insertion/deinsertion mechanism for this new family of materials, therefore explaining the cycling stability of Ag_{1-3x}La_x□_{2x}NbO₃.

EXPERIMENTAL SECTION

Synthesis of Ag_{1-3x}La_x□_{2x}NbO₃

Ag_{1-3x}La_x□_{2x}NbO₃ powders were synthesized by a sol-gel route (SG) based on a previous report (Wu et al., 2013). Briefly, a

stoichiometric mixture of NbCl₅ (99%, Sigma Aldrich), La(NO₃)₃ (99.9%, Alfa Aesar), AgNO₃ (99.9%, Alfa Aesar), and citric acid in excess (99+%, Alfa Aesar) was dissolved in 30% (w/w) H₂O₂ in H₂O (Sigma Aldrich). Upon complete dissolution of the species, the solution turned to a dark yellow color. At this point, the solution was heated at 120°C until the formation of a dark brown gel. The latter was heated to 300°C overnight to remove organic moieties and dehydrate the gel. The resulting powder is ground in an agate mortar and then annealed at 650°C for 6 h in an alumina crucible to crystallize the material. Depending on the degree of substitution, the resulting powder ranges from dark grey for AgNbO₃ to whitish powder in the case of Ag_{0.40}La_{0.20}NbO₃.

Characterization

Powder X-Ray Diffraction

X-ray diffraction (XRD) patterns were collected using a PANalytical X'Pert Pro diffractometer (Malvern Panalytical, Almelo, Netherlands). An X'Celerator detector with Cu-Kα1-Kα2 ($\lambda = 1.54060, 1.54439 \text{ \AA}$) radiation was used with acceleration voltage and current of 40 kV and 40 mA, respectively. With a step scan of 0.0167°, diffraction patterns have been collected between 20° and 80° (2 θ). Using pseudo-Voigt functions, Le Bail refinement was performed using FullProf Suite. Preliminary lattice parameter values have been taken from the literature (Sciau et al., 2004). For *in situ* XRD measurements, patterns were collected using a homemade "Leriche-like" cell (Leriche et al., 2010). During charge-discharge experiment, a current of 0.005 A g⁻¹ was applied for 20 min and stopped during 30 min for XRD pattern acquisition.

Electron Microscopy and Energy Dispersive X-Ray Analyses


The morphology and particle size were studied with a transmission electron microscope ThermoFisher S/TEM Themis G3 at 300 kV (Breda) point to point resolution: 0.18 nm. SEM micrographs were obtained at 20 kV using a Zeiss MERLIN Instrument using in-Lens annular detector. Samples were prepared by dispersing a small fraction of the powder on a piece of conducting carbon tape. EDX was collected at 8.0 mm working distance using an X-Max 50 mm² OXFORD Instruments detector. The measurements were performed on at least two samples per synthesis and for each sample at least 10 acquisitions were performed. The atomic percentage of each cation was determined with an accuracy of $\pm 5\%$.

BET Measurement

The specific surface area of the powders was determined using the BET method (Brunauer-Emmett-Teller) from the 77 K nitrogen adsorption curves with a Quantachrome Nova 4200e equipment (Anton Paar).

Electrochemistry

Self-supported electrodes were fabricated by mixing, in a small amount of ethanol, 75% w/w Ag_{1-3x}La_xNbO₃, 15% w/w of conductive carbon (Carbon Black by Superior Graphite, Chicago, IL, United States) to increase electronic conductivity and 10% w/w poly (1,1,2,2-tetrafluoroethylene) dissolved in water (PTFE,

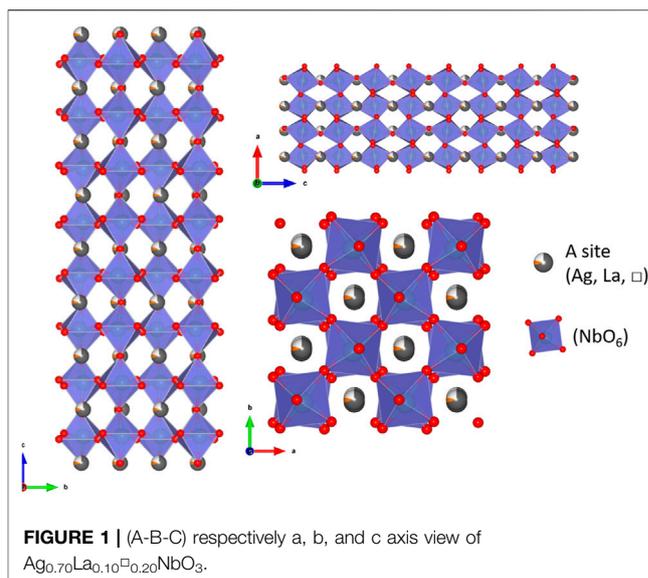

Sigma Aldrich) to form a homogeneous paste. This mixture was homogenized in a mortar and then cold-rolled until electrodes with a mass loading of about 5–10 mg cm⁻² were obtained. This level of loading enables reliable gravimetric values to be reported (Gogotsi and Simon 2011). Electrochemical measurements were performed using Swagelok cells. The positive electrode and metallic lithium (99.9%, Aldrich) were separated using a glass fiber membrane (70 mm, 10 mm diameter, GF/D Whatman) soaked with 1M LiPF₆ dissolved in 1:1 %wt. EC/DMC (Solvionic, France, battery grade purity). The Swageloks were assembled in a glove box containing less than 0.1 ppm of O₂ and H₂O. A VMP3 potentiostat (from Biologic run under ECLab software version V11.36, Seyssinet-Pariset, France) was used for electrochemical measurements.

Ex situ MAS NMR

For MAS NMR analysis, free-standing electrodes with about 5–10 mg cm⁻² were polarized for 10 h at different states of charge after performing a cyclic voltammogram (CV) at 0.1 mV s⁻¹. After disassembling the Swageloks in a glove box, electrodes were cleaned with a few drops of DMC and then dried overnight under *vacuum* in a Büchi oven at 60°C. Then, the electrolyte-free electrode was placed in a 2.5 mm-diameter zirconia rotor for MAS NMR experiments. ⁷Li MAS NMR spectra were acquired on a Bruker Avance 200 spectrometer (B₀ = 4.7 T, Larmor frequencies ν_0 (⁷Li = 77.78 MHz) at RT. A Bruker MAS probe with a cylindrical 2.5 mm (o.d) zirconia rotor spun at a frequency of 30 kHz was used. Spectra were obtained by applying a single pulse sequence, and a recycle delay (D1) of 3s ensured the acquisition of quantitative spectra. ⁷Li integrated intensities were determined by using spectral simulation (DMFit Software) (Massiot et al., 2002). The resulting integrated intensities were normalized with respect to the mass of the sample contained in the NMR rotor, the number of scans, and the receiver gain. Due to low amount of lithiated active material used for the analyses, it was not possible to rely on ⁶Li MAS NMR to characterize local structural features.

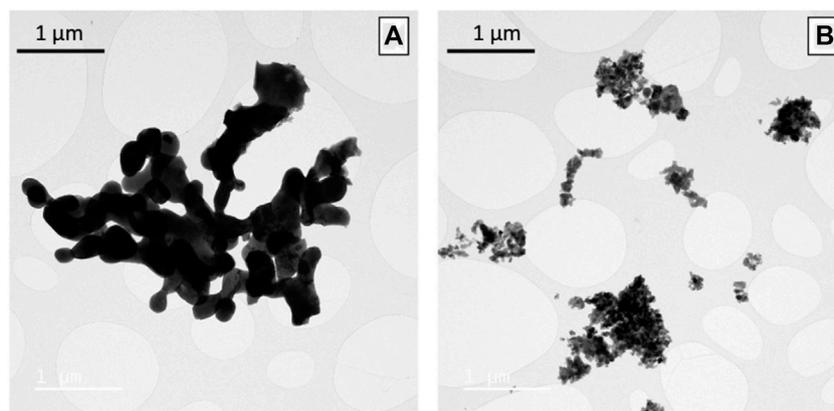


FIGURE 2 | TEM images of (A) AgNbO₃ and (B) Ag_{0.70}La_{0.10}NbO₃ after annealing at 650°C showing the difference in particles size between unsubstituted and substituted oxides.


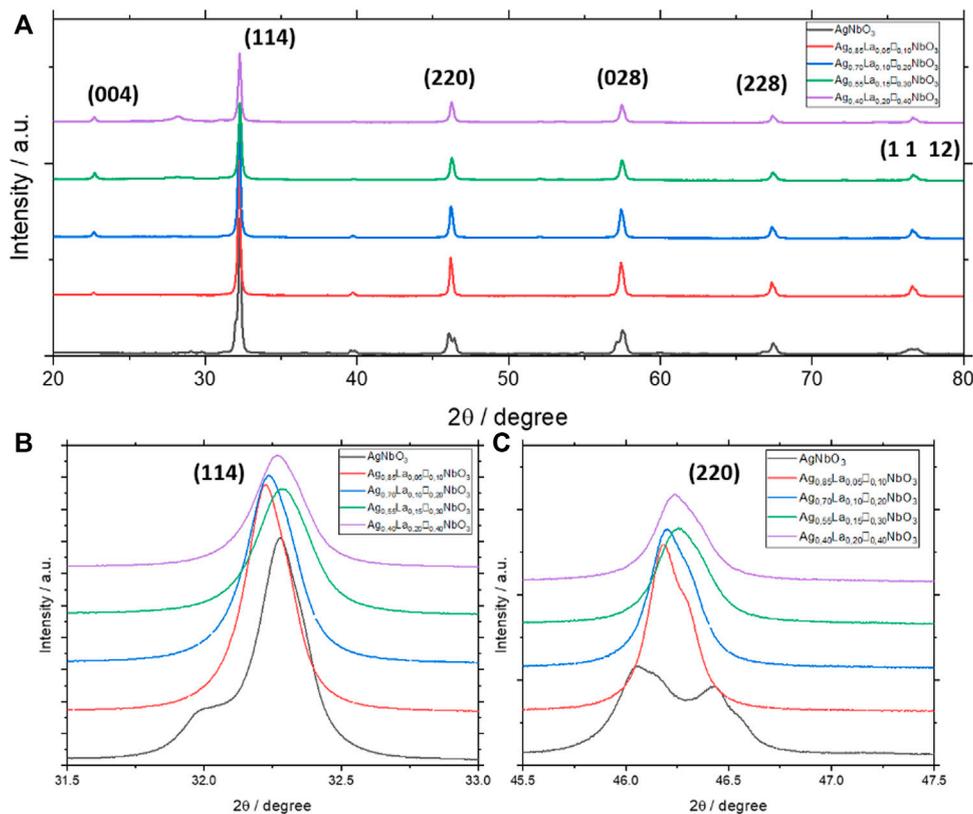


FIGURE 3 | (A–C) XRD patterns of Ag_{1-3x}La_xNbO₃ for different value of x.


RESULTS AND DISCUSSIONS

At room temperature, AgNbO₃ crystallizes in an orthorhombic perovskite structure (space group Pbcm) with distorted [BO₆] octahedra, similar to most perovskites (Sciau et al., 2004). Historically, AgNbO₃ has been studied in material science as antiferroelectric material for energy storage applications.

Substitutions in this lead-free material have been widely examined to stabilize the antiferroelectric phase and increase the power density. Various studies have explored the substitution of Ag⁺ in AgNbO₃ by Li⁺ (Farid et al., 2019), Na⁺ (Takeda et al., 2003), and multivalent cations (Li et al., 2009; Juang et al., 2016; Gao et al., 2020) (Sr²⁺, La³⁺, Sm³⁺, etc.) to create A-site vacancies. All the substitutions by multivalent cations show an increase in

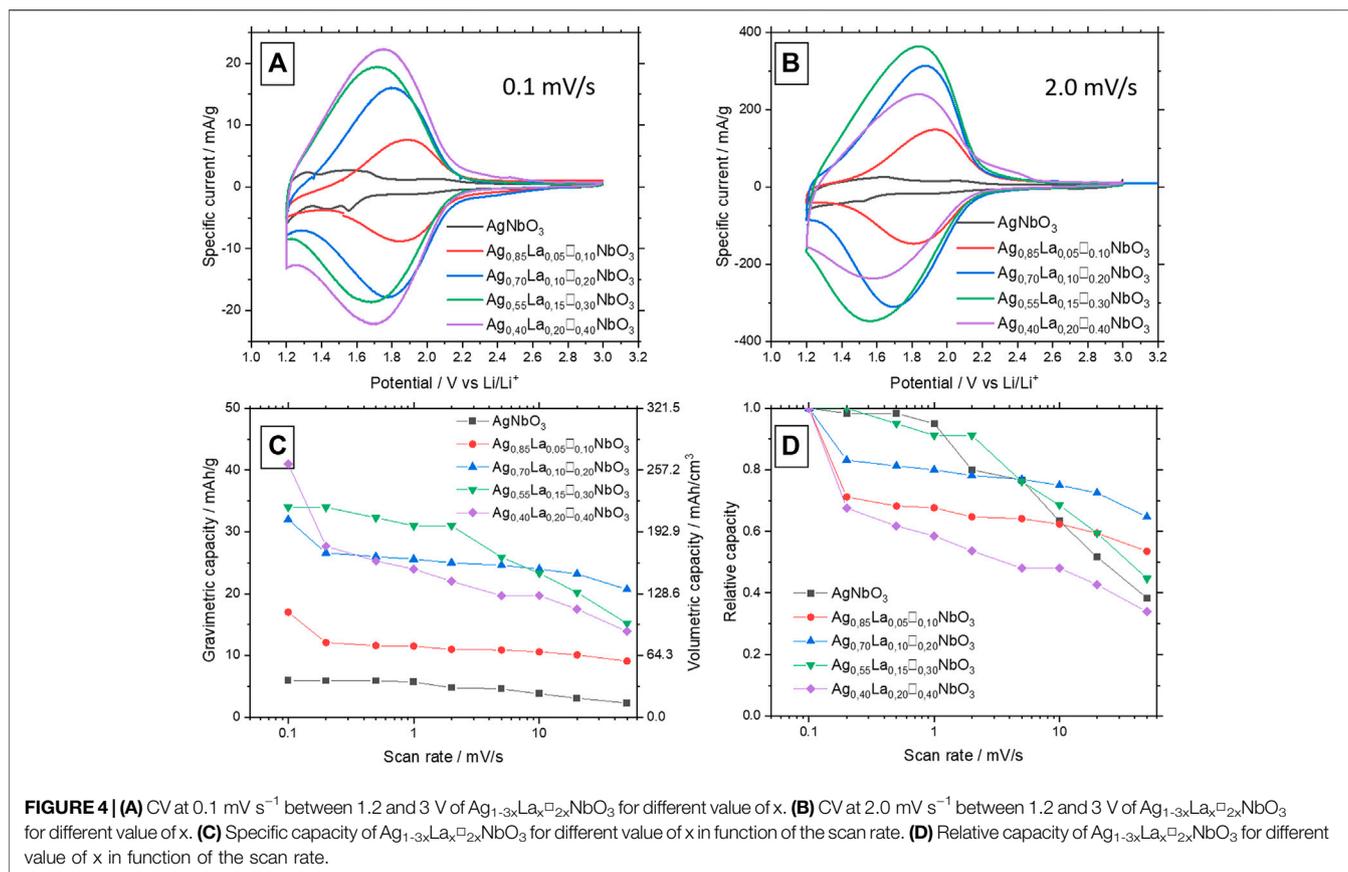

the symmetry of the material until the presence of impurities at a high degree of substitution (Juang et al., 2016; Gao et al., 2019; Gao et al., 2020). In order to investigate the possible Li-ion insertion into A site vacancies of this perovskite, we synthesized La-doped AgNbO₃ with different substitution ratios from x = 0 to x = 0.20. In a perovskite lattice, the coordination number of the A-site is 12, and 6 for the B-site. The ionic radius of silver is 1.54 Å, whereas that of niobium is 0.64 Å (Shannon and Prewitt 1969; Shannon 1976). Since the ionic radius of La for a coordination number of 12 is 1.36 Å, the silver-to-lanthanum substitution should be effective in the A site of the perovskite Ag_{1-3x}La_xNbO₃, where □ depicts a cation, vacancy in the A site of the perovskite, following reaction Eq. 1:



Here, we will name the samples Ag_{0.85}La_{0.05}□_{0.10}NbO₃, Ag_{0.70}La_{0.10}□_{0.20}NbO₃, Ag_{0.55}La_{0.15}□_{0.30}NbO₃ and Ag_{0.40}La_{0.20}□_{0.40}NbO₃, respectively for x = 0.05, x = 0.10, x = 0.15 and x = 0.20. Figure 1 represents the crystallographic arrangement of Ag_{0.70}La_{0.10}□_{0.20}NbO₃ which shows both distortion of [NbO₆] octahedra and the partial substitution of Ag by La in A-site with the corresponding vacancies.

The synthesis of Ag_{1-3x}La_x□_{2x}NbO₃ by a ceramic route was difficult to achieve. One reason is the reduction of Ag₂O to metallic Ag for a temperature higher than 150°C (Chun et al.,

2009; Shin et al., 2013). A second reason is the thermodynamic competition between AgNbO₃ and Ag₂Nb₄O₁₁ does not allow one to easily obtain a phase pure material, even by adding an excess of Ag₂O (Valant et al., 2007). For this reason, the different stoichiometries of AgNbO₃ were synthesized by a sol-gel (SG) process which has been demonstrated to be effective for the synthesis of perovskite materials (Huang et al., 1996; Y.; Li et al., 2010; Huizar-Félix et al., 2012). Moreover, the heat treatment at lower temperature (650°C) of the amorphous AgNbO₃ particles will avoid the reduction of silver. Figure 2A,B shows both AgNbO₃ and Ag_{0.70}La_{0.10}□_{0.20}NbO₃ agglomerated nanoparticles which are typical morphologies of sol-gel synthesis. AgNbO₃ particles are larger than those of Ag_{0.70}La_{0.10}□_{0.20}NbO₃, a feature confirmed by nitrogen adsorption measurements (BET method; Supplementary Table S1). These measurements revealed a specific surface area of 3 m² g⁻¹ for AgNbO₃ and 13 m² g⁻¹ for Ag_{0.70}La_{0.10}□_{0.20}NbO₃. In addition, as shown in Supplementary Table S2, EDX cationic ratio between Ag, La and Nb for every Ag_{1-3x}La_x□_{2x}NbO₃ confirms the presence of vacancies in all the powders of La-substituted AgNbO₃.

XRD was used to better understand the structural differences among all Ag_{1-3x}La_x□_{2x}NbO₃ powders. As shown in Figure 3A., AgNbO₃ has a perovskite structure with no secondary phase, although splitting of several peaks is observed. Ag_{0.85}La_{0.05}□_{0.10}NbO₃ (x = 0.05) and Ag_{0.70}La_{0.10}□_{0.20}NbO₃ (x

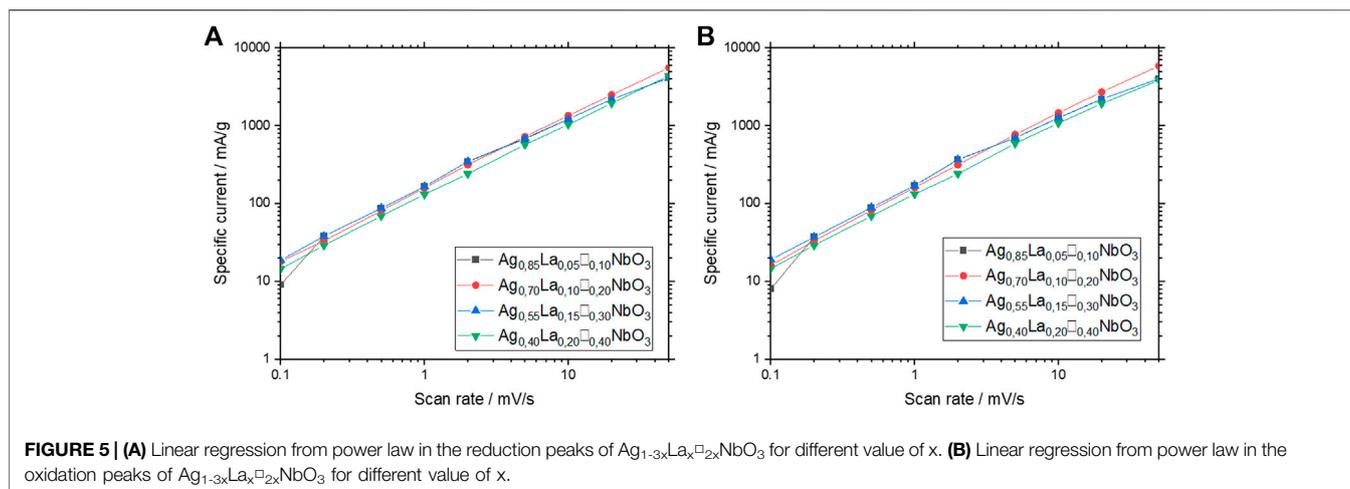



TABLE 1 | *b* value of Ag_{1-3x}La_xNbO₃ for different value of x for reduction and oxidation peaks.


	Reduction	Oxydation
Ag _{0.85} La _{0.05} NbO ₃	0.94	0.95
Ag _{0.70} La _{0.10} NbO ₃	0.92	0.95
Ag _{0.55} La _{0.15} NbO ₃	0.87	0.87
Ag _{0.40} La _{0.20} NbO ₃	0.9	0.91

= 0.10) also show the perovskite structure with no secondary phase visible in the diffractograms. However, starting from $x = 0.15$, impurity peaks appear, perhaps due to the lack of cations on the A-site, resulting in collapse of the structure. This is in agreement with previous reports on the A-site substitution in AgNbO₃ (Li et al., 2009; Juang et al., 2016). Depending on the size of the dopant cation, the perovskite structure can accept up to a certain amount of substitution, sometimes accompanied by the appearance of extra peaks which correspond to secondary phases. The decrease in peak intensity for Ag_{0.55}La_{0.15}NbO₃ and

Ag_{0.40}La_{0.20}NbO₃, compared to other samples, is an indicator of the stress caused by the high proportion of La in the perovskite. For the substituted oxides, a decrease in peak splitting was observed with increasing lanthanum substitution (Figures 3B–C). Further, the disappearance of peak splitting by $x = 0.15$ suggests a higher degree of symmetry in the substituted materials due to lower [NbO₆] octahedra distortion.


To get greater insight into the structure of the synthesized materials, Le Bail structural refinements were performed for each composition. First, as indicated in Supplementary Figure S1, the refinement of AgNbO₃ confirms that the Pbcm space group well represents the structure of AgNbO₃. Cell parameters of AgNbO₃ were extracted from the refinement as shown in Supplementary Figure S2 and Supplementary Table S3. We found that the cell parameters and the cell volume increase with increasing substitution of La for Ag_{1-3x}La_xNbO₃, which is in agreement with a previous report (Li et al., 2009). Moreover, this is consistent with a decrease of NbO₆ octahedra distortions previously described above. Refinements using a higher symmetry space group (Pm3m) have been performed to

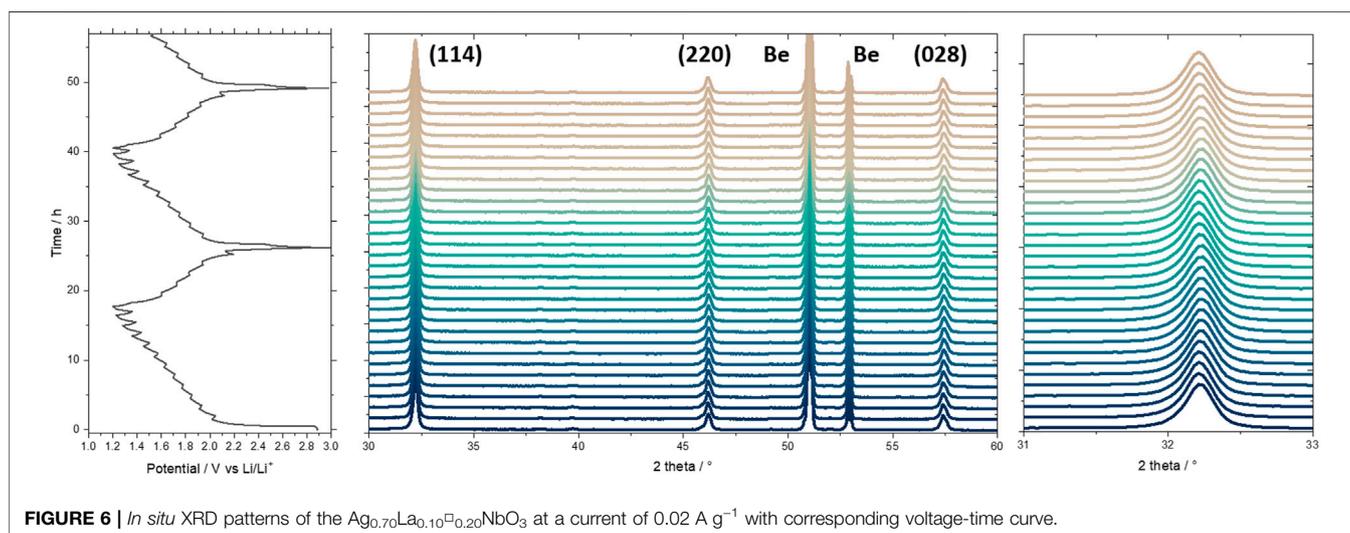

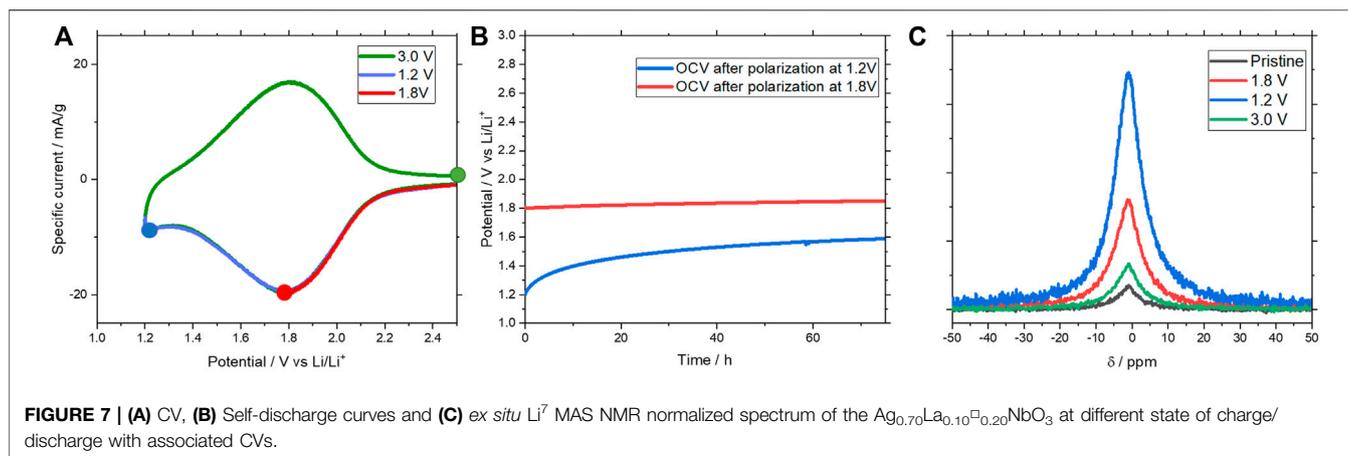

check that no phase transition appears with the substitution of silver by lanthanum. However, they did not lead to conclusive results. For this reason, we assume that the same space group (Pbcm) can be used to describe the crystallographic structure of all the Ag_{1-3x}La_x□_{2x}NbO₃ powders.

To characterize the ability of this family of materials to reversibly store lithium ions, cyclic voltammetry at 0.1 mV s⁻¹ was first performed. Note that this sweep rate should be considered as a low rate for power applications (around 5.5 h of charge). As depicted in **Figure 4A**, AgNbO₃ does not show any electrochemical activity between 1.2 and 3.0 V vs. Li⁺/Li at the selected scan rate. A negligible specific capacity of 6 mAh.g⁻¹ is reported. However, for each substituted material, broad and reversible peaks appear between 2.2 and 1.2 V vs. Li⁺/Li, characteristic of lithium insertion into the host structure. Considering no insertion is visible for the unsubstituted oxide, we propose the following reaction **Eq. 2** to describe the present electrochemical reaction.



At 0.1 mV s⁻¹, the specific capacity increases with the number of vacancies. During the first cycle at 0.1 mV s⁻¹, specific capacities are close to the theoretical capacity considering the insertion of one lithium ion per vacancy: 16 mAh g⁻¹, 35 mAh g⁻¹, 54 mAh g⁻¹, 76 mAh g⁻¹ for Ag_{0.85}La_{0.05}□_{0.10}NbO₃, Ag_{0.70}La_{0.10}□_{0.20}NbO₃, Ag_{0.55}La_{0.15}□_{0.30}NbO₃, Ag_{0.40}La_{0.20}□_{0.40}NbO₃, respectively. Considering only the mass of active materials the gravimetric capacity is found to be equal to 38 mAh cm⁻³, 109 mAh cm⁻³, 206 mAh cm⁻³, 219 mAh cm⁻³ and 264 mAh cm⁻³ for AgNbO₃, Ag_{0.85}La_{0.05}□_{0.10}NbO₃, Ag_{0.70}La_{0.10}□_{0.20}NbO₃, Ag_{0.55}La_{0.15}□_{0.30}NbO₃, Ag_{0.40}La_{0.20}□_{0.40}NbO₃, respectively. If the entire volume of the practical electrode is now considered (porosity volume ~70%), the gravimetric capacity is found to be equal to 12 mAh cm⁻³, 32 mAh cm⁻³, 62 mAh cm⁻³, 66 mAh cm⁻³ and 79 mAh cm⁻³ for AgNbO₃, Ag_{0.85}La_{0.05}□_{0.10}NbO₃, Ag_{0.70}La_{0.10}□_{0.20}NbO₃, Ag_{0.55}La_{0.15}□_{0.30}NbO₃, Ag_{0.40}La_{0.20}□_{0.40}NbO₃, respectively. Interestingly, no reduction of silver is observed in these materials indicating the strong interaction of silver cations within the perovskite

structure, contrary to most silver-based materials reported in the literature, i.e., silver vanadates (West and Crespi 1995; Marschilok et al., 2010; Sauvage et al., 2010).

Cyclic voltammetry was used to characterize the performance of the lanthanum-substituted oxides at a higher sweep rate of 2 mV s⁻¹ (**Figure 4B**). This sweep rate corresponds to 15 min of charge/discharge, which is consistent with the current goal for the development of electric vehicles (Colclasure et al., 2019). As was observed at 0.1 mV s⁻¹, the CVs shown at 2 mV s⁻¹ present very broad and reversible redox peaks.

As expected, the capacity of AgNbO₃ remains very low compared to the substituted oxides. Its capacity is 5 mA h.g⁻¹. Ag_{0.85}La_{0.05}□_{0.10}NbO₃ is the least substituted material and the one with the lower capacity at both 0.1 mV s⁻¹ and 2 mV s⁻¹ (32 mAh g⁻¹). Interestingly, at 2 mV s⁻¹, Ag_{0.40}La_{0.20}□_{0.40}NbO₃ has a lower capacity than Ag_{0.70}La_{0.10}□_{0.20}NbO₃ and Ag_{0.55}La_{0.15}□_{0.30}NbO₃, even though Ag_{0.40}La_{0.20}□_{0.40}NbO₃ shows the higher theoretical capacity most likely attributed to the higher amount of vacancies per unit cell. Such a decrease in capacity is explained by the lower degree of crystallinity which does not allow adequate diffusion of lithium ions in this substituted oxide. Moreover, the defects detected by the presence of peaks that did not belong to the orthorhombic lattice provides another possible explanation to the lower capacity of Ag_{0.40}La_{0.20}□_{0.40}NbO₃ at 2 mV s⁻¹. In addition, these CVs show the polarization between the oxidation and reduction peaks to be very small for each compound, even for CV at 2 mV s⁻¹. This result suggests that the intercalation process is not limited severely by low ionic diffusion, a consideration which will be discussed later.

CVs at different scan rates were performed to assess the capacity retention as a function of increasing scan rate. Scan rates from 0.1 mV s⁻¹ to 50 mV s⁻¹ were chosen, corresponding to 5.5h and 40s of charge, respectively. **Figures 4C,D** shows the specific capacity and relative capacity of every material at the mentioned scan rates. Ag_{0.40}La_{0.20}□_{0.40}NbO₃, the material with the highest number of vacancies, provides the highest capacity at a low sweep rate (**Figure 4C**). However, when the scan rate is increased, a rapid decrease in capacity is observed starting at 0.2 mV s⁻¹. As shown in **Figure 4D**, at 50 mV s⁻¹, Ag_{0.40}La_{0.20}□_{0.40}NbO₃ retains only 34% of the initial capacity

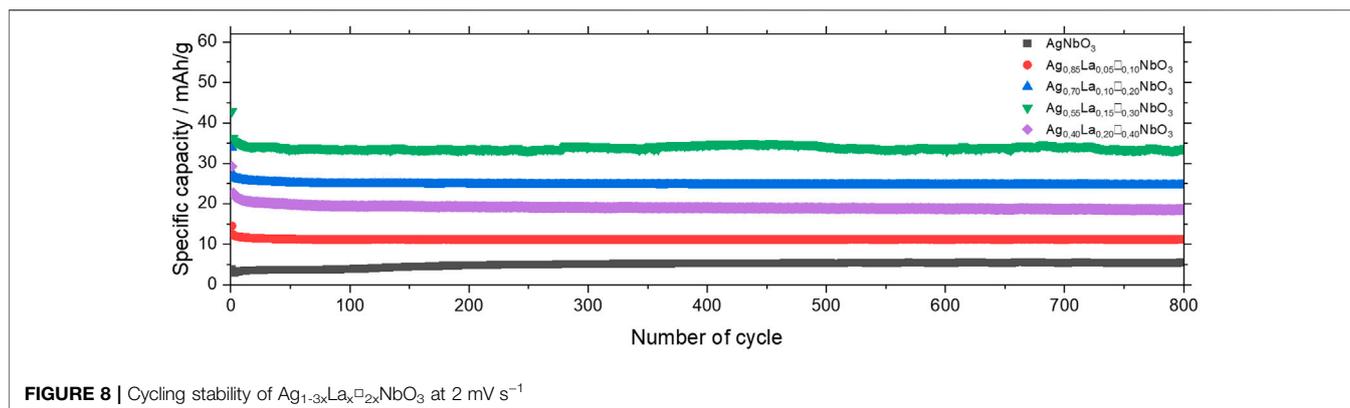


FIGURE 8 | Cycling stability of Ag_{1-3x}La_xNbO₃ at 2 mV s⁻¹

measured at 0.1 mV s⁻¹. Similarly, Ag_{0.55}La_{0.15}NbO₃ demonstrates a relatively high capacity at low scan rates but a rapid drop at higher rates. In contrast, while less substituted materials such as Ag_{0.85}La_{0.05}NbO₃ and Ag_{0.70}La_{0.10}NbO₃ exhibit lower capacities at 0.1 mV s⁻¹, they demonstrate better capacity retention. At 50 mV s⁻¹, Ag_{0.85}La_{0.05}NbO₃ and Ag_{0.70}La_{0.10}NbO₃ exhibit capacity retentions of 53 and 64%, respectively, for a 500 times faster rate of charge/discharge compared to their capacities measured at 0.1 mV s⁻¹. All the specific capacities are summarized in **Supplementary Table S4**.

In order to get a better understanding of the charge storage mechanism, *b*-values from the power law relationship in **Eq. 3** have been calculated,

$$i = a \cdot v^b \quad (3)$$

where *i* is the intensity of reduction/oxidation peak, *v* the corresponding scan rate, *a* and *b* are constant values. If *b* is close to 0.5, charge storage can be described as limited by ionic diffusion in the host material, as described in the Randles-Ševčík equation (Ševčík 1948; Randles 1948). When the value of *b* is equal or close to 1, charge storage occurs in agreement with non-diffusion limited mechanism, as in the case of pseudocapacitive materials (Choi et al., 2020). Regarding Ag_{1-3x}La_xNbO₃ compounds, as shown in **Figure 5A,B**, a linear relationship between specific current and scan rate (0.1 mV s⁻¹ and 50 mV s⁻¹) is observed, the *b*-values of which are listed in **Table 1**. The values of *b* vary between 0.87 and 0.95, which seems to indicate weak diffusion limitation during charge/discharge processes. Additionally, the smaller *b* values calculated for Ag_{0.55}La_{0.15}NbO₃ and Ag_{0.40}La_{0.20}NbO₃ support the difference in capacity retention observed previously, as compared to Ag_{0.85}La_{0.05}NbO₃ and Ag_{0.70}La_{0.10}NbO₃.

As displayed in **Figure 6**, the behavior of the different oxides during lithium insertion was investigated by *in situ* XRD, to better understand the filling of the vacant A-sites of the Ag_{1-3x}La_xNbO₃ perovskite. Ag_{0.70}La_{0.10}NbO₃ was used because no structural defects were observed in this phase compared to Ag_{0.55}La_{0.15}NbO₃ and Ag_{0.40}La_{0.20}NbO₃. First, no new peak appears (and/or disappears) on the XRD patterns during charge and discharge. This behavior indicates

that a solid solution type mechanism predominates upon charge storage, as previously reported for intercalation materials dedicated to power application with a *b* value close to 1 (Come et al., 2014). Moreover, it is observed that the peaks initially present do not move during lithiation. The three diffraction peaks observed in the studied 2θ range present the three crystallographic directions, implying that the perovskite structure does not modify its lattice parameters during lithium cation insertion in the vacant A sites. Thus, this material can be considered as a zero strain oxide during lithium insertion, similar to the well-known Li₄Ti₅O₁₂ (Thackeray and Amine 2021).

In another series of measurements, self-discharge and NMR experiments carried out on cycled Ag_{0.70}La_{0.10}NbO₃ electrodes provide further evidence of Li⁺ insertion in the material. For these experiments, electrodes were cycled to 1.8 and 1.2 V vs. Li⁺/Li at 0.1 mV s⁻¹ and subsequently polarized for 10 h to reach a thermodynamic equilibrium. As shown in **Figure 7A,B**, both electrodes (cycled at 1.2 and 1.8 V vs. Li⁺/Li) present relatively low self-discharge. The electrode polarized at 1.8 V shows a potential of 1.82 V vs. Li⁺/Li after almost 80 h of OCV. The electrode polarized at 1.2 V shows a potential of 1.59 V vs. Li⁺/Li in the same condition. These low self-discharge levels at 1.2 and 1.8 V are a strong indication that lithium cations are inserted in a stable way into the vacancies of the material. *Ex situ* ⁷Li MAS NMR measurements have been performed after these self-discharge experiments. ⁷Li MAS NMR spectra were also recorded for the pristine and the fully discharged electrode (3.0V) in addition to the charged samples at 1.2 V vs. Li⁺/Li, at a similar scan rate of 0.1 mV s⁻¹. As expected, the pristine electrode has a negligible quantity of Li detected. For the partially and fully charged samples, a peak is observed at around -1 ppm. The integrated intensity of the NMR peak, which is intrinsically proportional to the detected amount of lithium in the materials, is also found to be proportional to the specific capacity of the materials at 1.8 and 1.2 V (**Figure 7B,C**). The spectrum of the fully discharged electrode at 3.0V displays a small amount of lithium assigned to the partial irreversibility of the reaction during the first cycle and is also found to be in agreement with the first cycle of the CV. Due to the amount of lithium inserted in the materials, the signal to noise ratio remains relatively low even for a large

number of scans. For this reason, spectra with a narrower linewidth and thus better resolution, were not possible. Thus, it is difficult to conclude as to the number of lithium sites, even at the fully charged state, as only one apparent resonance is observed in ⁷Li MAS NMR. Taken together, the combination of *ex situ* NMR and self-discharge provide convincing evidence that lithium ions are inserted in this perovskite material, most probably in the vacant A site.

The cycling characteristics for Ag_{1-3x}La_xNbO₃ were determined as cycle life is a key property for the development of batteries based on high rate electrode materials. As observed in **Figure 8**, all the materials exhibit exceptional stability upon cycling. After 800 cycles at 2 mV s⁻¹, Ag_{0.85}La_{0.05}NbO₃, Ag_{0.70}La_{0.10}NbO₃, Ag_{0.55}La_{0.15}NbO₃, and Ag_{0.40}La_{0.20}NbO₃ show a capacity retention of 95, 95, 95, 97 and 88%, respectively. The *in situ* XRD experiments and *b*-value calculation, which show zero-strain materials and non-diffusion limited charge storage mechanisms, respectively, are consistent with the outstanding cyclability observed for these materials.

In contrast to the classical design of insertion materials, our approach was to synthesize an oxide with vacancies in order to create potential sites for cation insertion in a perovskite. As proven by *ex situ* MAS NMR, lithium ions can be reversibly stored in the A site of Ag_{0.70}La_{0.10}NbO₃ and by extension to every Ag_{1-3x}La_xNbO₃ composition. To further demonstrate this point, **Supplementary Figure S3A–D** presents the difference between lithium and sodium insertion by cyclic voltammetry at different scan rates. While Li⁺ insertion leads to characteristic redox peaks, in the case of Na⁺, no redox reaction can be observed. It is likely that sodium ions cannot be inserted into the structure of Ag_{0.70}La_{0.10}NbO₃ and therefore cannot generate redox reactions due to the larger ionic radius. This is also the case for the pseudocapacitive T-Nb₂O₅, which shows highly reversible Li-ion intercalation but negligible Na-ion insertion (Kim et al., 2012). Moreover, kinetic analysis provides compelling evidence that a not diffusion-limited insertion occurs during the charge and discharge processes.

CONCLUSION

This work presents the partial substitution of AgNbO₃ perovskite by lanthanum in the A-site, resulting in the creation of cationic vacancies. We report on a gradual increase of the capacity at low scan rates as a function of the increase of the substitution. In addition, the different oxides present excellent behavior at high scan rates. At 50 mV.s⁻¹ Ag_{0.70}La_{0.10}NbO₃ retains 64% of its capacity measured at 0.1 mV s⁻¹. Moreover, the combination of *ex situ* MAS NMR and *in situ* XRD experiments confirm that the insertion of lithium ions in the A site of the perovskite is responsible for the observed capacity and does not cause any structural change of the material. Together, these observations help to explain the good cycling behavior observed. In addition to structural insight, kinetic analysis indicates a non-diffusion limited ion insertion process for these oxides.

Nevertheless, some questions still remain. A better understanding of the solvation/desolvation occurring at the

surface of particles during alkali ion insertion is critical towards understanding the small limitation of diffusion in charge storage process (Wang et al., 2019). Further experiments such as EQCM or *operando* atomic force microscopy can provide more insight in the charge storage mechanism. From another point of view, the promising observations reported here should be explored with other vacancy-designed materials and with different alkali cations. Moreover, these oxides present a charge storage mechanism which are between double layer capacitor and battery type electrodes (as observed for MnO₂ (Toupin et al., 2004; Brousse et al., 2006), T-Nb₂O₅ (Augustyn et al., 2013; Griffith et al., 2016) or MXenes (Naguib et al., 2012; Anasori et al., 2017) and represent an interesting model material for fundamental understanding in general.

In conclusion, the new approach reported in this work presents a different type of material design which widens the opportunities for creating the next generation of negative electrodes for high power Li-ion batteries. Although the oxide presented here contains silver, we believe this study can open the way toward the search of more practical materials for high-power battery electrodes.

DATA AVAILABILITY STATEMENT

The raw data supporting the conclusion of this article will be made available by the authors, without undue reservation.

AUTHOR CONTRIBUTIONS

ELC: Investigation, Methodology, Writing—review and editing. JCEA and ND: Investigation, Writing—review. BD and GW: Writing—review. OC and TB: Conceptualization, Methodology, Supervision, Writing—review and editing.

FUNDING

Nantes Université/NExT program (ANR-16-IDEX-0007, DISCUSS project).

ACKNOWLEDGMENTS

The authors want to thank University of Nantes and NExT program for financial funding. They also thank Eric Gautron for TEM/STEM images as well as Stéphane Grolleau for specific surface area measurement.

SUPPLEMENTARY MATERIAL

The Supplementary Material for this article can be found online at: <https://www.frontiersin.org/articles/10.3389/fchem.2022.873783/full#supplementary-material>

REFERENCES

- Anasori, B., Lukatskaya, M. R., and Gogotsi, Y. (2017). 2D Metal Carbides and Nitrides (MXenes) for Energy Storage. *Nat. Rev. Mater.* 2 (2), 16098. doi:10.1038/natrevmats.2016.98
- Armand, M., and Tarascon, J.-M. (2008). Building Better Batteries. *Nature* 451 (7179), 652–657. doi:10.1038/451652a
- Augustyn, V., Come, J., Lowe, M. A., Kim, J. W., Taberna, P.-L., Tolbert, S. H., et al. (2013). High-rate Electrochemical Energy Storage through Li⁺ Intercalation Pseudocapacitance. *Nat. Mater.* 12 (6), 518–522. doi:10.1038/nmat3601
- Brousse, T., Toupin, M., Dugas, R., Athouël, L., Crosnier, O., and Bélanger, D. (2006). Crystalline MnO₂ as Possible Alternatives to Amorphous Compounds in Electrochemical Supercapacitors. *J. Electrochem. Soc.* 153 (12), A2171. doi:10.1149/1.2352197
- Burnham, A., Dufek, E. J., Stephens, T., Francfort, J., Michelbacher, C., Carlson, R. B., et al. (2017). Enabling Fast Charging - Infrastructure and Economic Considerations. *J. Power Sourc.* 367 (novembre), 237–249. doi:10.1016/j.jpowsour.2017.06.079
- Butts, D., Schoiber, J., Choi, C., Redhammer, G. J., Hüsing, N., Donne, S., et al. (2021). Fe-Substituted Sodium β''-Al₂O₃ as a High-Rate Na-Ion Electrode. *Chem. Mater.* 33 (15), 6136–6145. doi:10.1021/acs.chemmater.1c01680
- Choi, C., Ashby, D. S., Butts, D. M., DeBlock, R. H., Wei, Q., Lau, J., et al. (2020). Achieving High Energy Density and High Power Density with Pseudocapacitive Materials. *Nat. Rev. Mater.* 5 (1), 5–19. doi:10.1038/s41578-019-0142-z
- Chun, S., Grudinin, D., Lee, D., Kim, S.-H., Yi, G.-R., and Hwang, I. (2009). Roll-to-Roll Printing of Silver Oxide Pastes and Low Temperature Conversion to Silver Patterns. *Chem. Mater.* 21 (2), 343–350. doi:10.1021/cm802475m
- Colclasure, A. M., Dunlop, A. R., Trask, S., Polzin, B. J., Jansen, A. N., and Smith, K. (2019). Requirements for Enabling Extreme Fast Charging of High Energy Density Li-Ion Cells while Avoiding Lithium Plating. *J. Electrochem. Soc.* 166 (8), A1412–A1424. doi:10.1149/2.0451908jes
- Come, J., Augustyn, V., Kim, J. W., Rozier, P., Taberna, P.-L., Gogotsi, P., et al. (2014). Electrochemical Kinetics of Nanostructured Nb₂O₅ Electrodes. *J. Electrochem. Soc.* 161 (5), A718–A725. doi:10.1149/2.040405jes
- Farid, U., Khan, H. U., Avdeev, M., Whittle, T. A., and Kennedy, B. J. (2019). Preparation and High Resolution Structural Studies of Li_xAg_{1-x}NbO₃ lead Free Piezoelectrics. *J. Solid State. Chem.* 269 (janvier), 401–408. doi:10.1016/j.jssc.2018.10.007
- Gao, J., Liu, Q., Dong, J., Wang, X., Zhang, S., and Li, J.-F. (2020). Local Structure Heterogeneity in Sm-Doped AgNbO₃ for Improved Energy-Storage Performance. *ACS Appl. Mater. Inter.* 12 (5), 6097–6104. doi:10.1021/acsami.9b20803
- Gao, J., Zhang, Y., Zhao, L., Lee, K.-Y., Liu, Q., Studer, A., et al. (2019). Enhanced Antiferroelectric Phase Stability in La-Doped AgNbO₃: Perspectives from the Microstructure to Energy Storage Properties. *J. Mater. Chem. A* 7 (5), 2225–2232. doi:10.1039/C8TA09353A
- Gogotsi, Y., and Simon, P. (2011). True Performance Metrics in Electrochemical Energy Storage. *Science* 334 (6058), 917–918. doi:10.1126/science.1213003
- Griffith, K. J., Forse, A. C., Griffin, J. M., and Grey, C. P. (2016). High-Rate Intercalation without Nanostructuring in Metastable Nb₂O₅ Bronze Phases. *J. Am. Chem. Soc.* 138 (28), 8888–8899. doi:10.1021/jacs.6b04345
- Griffith, K. J., Seymour, I. D., Hope, M. A., Butala, M. M., Lamontagne, L. K., Preefer, M. B., et al. (2019). Ionic and Electronic Conduction in TiNb₂O₇. *J. Am. Chem. Soc.* 141 (42), 16706–16725. doi:10.1021/jacs.9b06669
- Griffith, K. J., Wiaderek, K. M., Cibin, G., Marbella, L. E., and Grey, C. P. (2018). Niobium Tungsten Oxides for High-Rate Lithium-Ion Energy Storage. *Nature* 559 (7715), 556–563. doi:10.1038/s41586-018-0347-0
- Huang, K., Feng, M., and Goodenough, J. B. (1996). Sol-Gel Synthesis of a New Oxide-Ion Conductor Sr- and Mg-Doped LaGaO₃ Perovskite. *J. Am. Ceram. Soc.* 79 (4), 1100–1104. doi:10.1111/j.1151-2916.1996.tb08554.x
- Huizar-Félix, A. M., Hernández, T., de la Parra, S., Ibarra, J., and Kharisov, B. (2012). Sol-gel Based Pechini Method Synthesis and Characterization of Sm_{1-x}Ca_xFeO₃ Perovskite 0.1 ≤ x ≤ 0.5. *Powder Techn.* 229 (octobre), 290–293. doi:10.1016/j.powtec.2012.06.057
- Juang, Y., Chu, S.-Y., and Wang, K. S. (2016). Phase Transition and Dielectric Properties of Sr-Doped AgNbO₃ Ceramics. *Ferroelectrics* 493 (1), 54–61. doi:10.1080/00150193.2016.1133216
- Kim, J. W., Augustyn, V., and Dunn, B. (2012). The Effect of Crystallinity on the Rapid Pseudocapacitive Response of Nb₂O₅. *Adv. Energ. Mater.* 2 (1), 141–148. doi:10.1002/aenm.201100494
- Leriche, J. B., Hamelet, S., Shu, J., Morcrette, M., Masquelier, C., Ouvrard, G., et al. (2010). An Electrochemical Cell for Operando Study of Lithium Batteries Using Synchrotron Radiation. *J. Electrochem. Soc.* 157 (5), A606. doi:10.1149/1.3355977
- Li, G., Kako, T., Wang, D., Zou, Z., and Ye, J. (2009). Enhanced Photocatalytic Activity of La-Doped AgNbO₃ under Visible Light Irradiation. *Dalton Trans.* 0 (13), 2423–2427. doi:10.1039/B810126D
- Li, M., Feng, M., Luo, D., and Chen, Z. (2020). Fast Charging Li-Ion Batteries for a New Era of Electric Vehicles. *Cel Rep. Phys. Sci.* 1 (10), 100212. doi:10.1016/j.xcrp.2020.100212
- Li, Y., Yao, S., Wen, W., Xue, L., and Yan, Y. (2010). Sol-gel Combustion Synthesis and Visible-Light-Driven Photocatalytic Property of Perovskite LaNiO₃. *J. Alloys Comp.* 491 (1), 560–564. doi:10.1016/j.jallcom.2009.10.269
- Marschilok, A. C., Kozarsky, E. S., Tanzil, K., Zhu, S., Takeuchi, K. J., and Takeuchi, E. S. (2010). Electrochemical Reduction of Silver Vanadium Phosphorous Oxide, Ag₂VO₂PO₄: Silver Metal Deposition and Associated Increase in Electrical Conductivity. *J. Power Sourc.* 195 (19), 6839–6846. doi:10.1016/j.jpowsour.2010.04.033
- Massiot, D., Fayon, F., Capron, M., King, I., Le Calvé, S., Alonso, B., et al. (2002). Modelling One- and Two-Dimensional Solid-State NMR Spectra. *Magn. Reson. Chem.* 40 (1), 70–76. doi:10.1002/mrc.984
- Naguib, M., Come, J., Dyatkin, B., Presser, V., Taberna, P.-L., Simon, P., et al. (2012). MXene: a Promising Transition Metal Carbide Anode for Lithium-Ion Batteries. *Electrochemistry Commun.* 16 (1), 61–64. doi:10.1016/j.elecom.2012.01.002
- Prakash, A. S., Manikandan, P., Ramesha, K., Sathiy, M., Tarascon, J.-M., and Shukla, A. K. (2010). Solution-Combustion Synthesized Nanocrystalline Li₄Ti₅O₁₂ as High-Rate Performance Li-Ion Battery Anode. *Chem. Mater.* 22 (9), 2857–2863. doi:10.1021/cm100071z
- Randles, J. E. B. (1948). A Cathode ray Polarograph. Part II.-The Current-Voltage Curves. *Trans. Faraday Soc.* 44 (0), 327–338. doi:10.1039/TF9484400327
- Sauvage, F., Bodenez, V., Tarascon, J.-M., and Poeppelmeier, K. R. (2010). Room-Temperature Synthesis Leading to Nanocrystalline Ag₂V₄O₁₁. *J. Am. Chem. Soc.* 132 (19), 6778–6782. doi:10.1021/ja1009713
- Sciau, P., Kania, A., Dkhil, B., Suard, E., and Ratuszna, A. (2004). Structural Investigation of AgNbO₃ Phases Using X-ray and Neutron Diffraction. *J. Phys. Condens. Matter* 16 (16), 2795–2810. doi:10.1088/0953-8984/16/16/004
- Ševčík, A. (1948). Oscillographic Polarography with Periodical Triangular Voltage. *Collection Czechoslovak Chem. Commun.* 13, 349–377.
- Shannon, R. D., and Prewitt, C. T. (1969). Effective Ionic Radii in Oxides and Fluorides. *Acta Crystallogr. Sect B* 25 (5), 925–946. doi:10.1107/S0567740869003220
- Shannon, R. D. (1976). Revised Effective Ionic Radii and Systematic Studies of Interatomic Distances in Halides and Chalcogenides. *Acta Cryst. Sect A* 32 (5), 751–767. doi:10.1107/S0567739476001551
- Shin, D.-Y., Yi, G.-R., Lee, D., Park, J., Lee, Y.-B., Hwang, I., et al. (2013). Rapid Two-step Metallization through Physicochemical Conversion of Ag₂O for Printed "black" Transparent Conductive Films. *Nanoscale* 5 (11), 5043–5052. doi:10.1039/C3NR00962A
- Sivakkumar, S. R., Nerkar, J. Y., and Pandolfo, A. G. (2010). Rate Capability of Graphite Materials as Negative Electrodes in Lithium-Ion Capacitors. *Electrochimica Acta* 55 (9), 3330–3335. doi:10.1016/j.electacta.2010.01.059
- Song, K., Seo, D.-H., Jo, M. R., Kim, Y.-I., Kang, K., and Kang, Y.-M. (2014). Tailored Oxygen Framework of Li₄Ti₅O₁₂ Nanorods for High-Power Li Ion Battery/Tailored Oxygen Framework of Li₄Ti₅O₁₂ Nanorods for High-Power Li Ion Battery. *J. Phys. Chem. Lett.* 5 (8), 1368–1373. doi:10.1021/jz5002924
- Takeda, T., Takahashi, Y., Wada, N., and Sakabe, Y. (2003). Effects of Substitution of Na and K Ions for Ag Ion in (Ag,Li)NbO₃ Ceramics. *Jpn. J. Appl. Phys.* 42 (Part 1, No. 9B), 6023–6026. doi:10.1143/jjap.42.6023
- Thackeray, M. M., and Amine, K. (2021). Li₄Ti₅O₁₂ Spinel Anodes. *Nat. Energy* 6 (6), 683. doi:10.1038/s41560-021-00829-2

- Toupin, M., Brousse, T., and Bélanger, D. (2004). Charge Storage Mechanism of MnO₂ Electrode Used in Aqueous Electrochemical Capacitor. *Chem. Mater.* 16 (16), 3184–3190. doi:10.1021/cm049649j
- Valant, M., Axelsson, A.-K., Zou, B., and Alford, N. (2007). Oxygen Transport during Formation and Decomposition of AgNbO₃ and AgTaO₃. *J. Mater. Res.* 22 (6), 1650–1655. doi:10.1557/JMR.2007.0196
- Wang, X., Mathis, T. S., Li, K., Lin, Z., Vlcek, L., Torita, T., et al. (2019). Influences from Solvents on Charge Storage in Titanium Carbide MXenes. *Nat. Energ.* 4 (3), 241–248. doi:10.1038/s41560-019-0339-9
- West, K., and Crespi, A. M. (1995). Lithium Insertion into Silver Vanadium Oxide, Ag₂V₄O₁₁. *J. Power Sourc.* 54 (2), 334–337. doi:10.1016/0378-7753(94)02095-K
- Wu, W., Liang, S., Chen, Y., Shen, L., Yuan, R., and Wu, L. (2013). Mechanism and Improvement of the Visible Light Photocatalysis of Organic Pollutants over Microcrystalline AgNbO₃ Prepared by a Sol-Gel Method. *Mater. Res. Bull.* 48 (4), 1618–1626. doi:10.1016/j.materresbull.2013.01.011

Conflict of Interest: The authors declare that the research was conducted in the absence of any commercial or financial relationships that could be construed as a potential conflict of interest.

Publisher's Note: All claims expressed in this article are solely those of the authors and do not necessarily represent those of their affiliated organizations, or those of the publisher, the editors and the reviewers. Any product that may be evaluated in this article, or claim that may be made by its manufacturer, is not guaranteed or endorsed by the publisher.

Copyright © 2022 Le Calvez, Espinosa-Angeles, Whang, Dupré, Dunn, Crosnier and Brousse. This is an open-access article distributed under the terms of the Creative Commons Attribution License (CC BY). The use, distribution or reproduction in other forums is permitted, provided the original author(s) and the copyright owner(s) are credited and that the original publication in this journal is cited, in accordance with accepted academic practice. No use, distribution or reproduction is permitted which does not comply with these terms.