

MAGNETIC AND ELECTRONIC PROPERTIES OF NEPTUNIUM AND PLUTONIUM COMPOUNDS

P. Burlet, J. Fournier, E. Pleska, S. Quezel, J. Rossat-Mignod, J. Spirlet, J.
Rebizant, O. Vogt

► **To cite this version:**

P. Burlet, J. Fournier, E. Pleska, S. Quezel, J. Rossat-Mignod, et al.. MAGNETIC AND ELECTRONIC PROPERTIES OF NEPTUNIUM AND PLUTONIUM COMPOUNDS. Journal de Physique Colloques, 1988, 49 (C8), pp.C8-469-C8-474. <10.1051/jphyscol:19888214>. <jpa-00228371>

HAL Id: jpa-00228371

<https://hal.archives-ouvertes.fr/jpa-00228371>

Submitted on 1 Jan 1988

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

MAGNETIC AND ELECTRONIC PROPERTIES OF NEPTUNIUM AND PLUTONIUM COMPOUNDS

P. Burlet ⁽¹⁾, J. M. Fournier ⁽¹⁾, E. Pleska ⁽¹⁾, S. Quezel ⁽¹⁾, J. Rossat-Mignod ⁽¹⁾, J. C. Spirlet ⁽²⁾, J. Rebizant ⁽²⁾ and O. Vogt ⁽³⁾

⁽¹⁾ *Centre d'Etudes Nucléaires, DRF/SPh-MDN, 85 X, 38041 Grenoble Cedex, France*

⁽²⁾ *T.U.I. Karlsruhe, Postfach 2266, 7500 Karlsruhe, F.R.G.*

⁽³⁾ *Laboratorium für Festkörperphysik, E.T.H. Zürich, 8093 Zürich, Switzerland*

Abstract. – The magnetic and electrical transport properties of the U, Np and Pu mononictides and monochalcogenides are reviewed. The results of single crystal measurements on Np and Pu compounds are emphasized. Measurements on a single crystal of NpRu₂Si₂ are summarized.

The actinides form a transition serie characterized by the progressive filling of the 5f shell. They differentiate from the lanthanides, except the anomalous ones as Ce, by a more extended nature of the 5f wave function. Depending on the actinide element, the interactinide spacing and the actinide environnement in compounds, properties ranging from itinerant (3d like) to localized systems can occur. The properties of the actinides have been recently reviewed in the "Handbook on the Physics and Chemistry of the Actinides" which gives an exhaustive description of the studies performed up to 1984 concerning bulk properties [1], Mössbauer spectroscopy [2], elastic [3] and inelastic neutron scattering [4] to which the reader can refer for bibliography. It is clear that a large number of uranium compounds have been extensively studied for a long time but much less has been done on neptunium and plutonium compounds and the studies on transplutoniums are rather seldom. This is obviously a consequence of the high activity of Np and Pu and transplutonium elements the latter furthermore being available only in very small quantities. A big effort has been devoted during the last ten years, to the sample preparation and crystal growth of Np and Pu compounds [5]. One of the most important progress, due to the joint efforts of Vogt at ETH Zurich and of Spirlet and Rebizant at EITU Karlsruhe, consists in the synthesis of large, good quality, single crystals of rock-salt Np and Pu compounds which allowed to perform many physical studies on these systems.

In this paper we will describe the properties of the structurally simple NaCl type mononictides and monochalcogenides AnX with special attention to the transuranium Np and Pu compounds. The results obtained on NpRu₂Si₂ will be presented to illustrate the interest of the ternary actinide compounds AnM₂X₂ (isomorphous with the Ce counterparts). All these results are derived from magnetic measurements (susceptibility and magnetization), Mössbauer spectroscopy, electrical transport measurements and neutron scattering experiments. The scope of this paper is limited

and we apologize that many interesting studies on actinides are not covered.

Uranium mononictides and monochalcogenides

The magnetic properties of the AnX mononictides and monochalcogenides are summarized in table I.

All the uranium mononictides are antiferromagnets with Neel temperature and ordered magnetic moments increasing from the nitride to the bismuthide, i.e. with interuranium spacing. The magnetic ordering of all these compounds is characterized by wave vectors along the cubic axes $\mathbf{k} = \langle k\ 0\ 0 \rangle$ and a longitudinal polarization corresponding to Fourier components $\mathbf{m}(\mathbf{k})$ parallel to \mathbf{k} . A similar situation occurs also in the cerium mononictides CeBi and CeSb [6]. In these last compounds as in the U counterparts it is now well established that this is a consequence of highly anisotropic exchange interactions due to the proximity of the 4f (or 5f) electrons to the Fermi energy and to the hybridization of the f electrons with band electrons [7]. In some cases this anisotropy of \mathbf{k} and $\mathbf{m}(\mathbf{k})$ disagrees with magnetization measurements which indicate another easy axis ([110], or [111]). This discrepancy is explained by the occurrence of planar double- \mathbf{k} or multiaxial triple- \mathbf{k} structures instead of the collinear single- \mathbf{k} ordering. All the uranium monochalcogenides are ferromagnets with magnetization along the [111] direction. From US to UTe the Curie temperature decreases while the ordered magnetic moments increase. Solid solutions of mononictides and monochalcogenides can be easily formed as, for instance, USb_{1-x}Te_x [3], or UAs_{1-x}Se_x [8] in which a progressive evolution from the antiferromagnetic behaviour of the pnictide to the ferromagnetism of the chalcogenide can be studied. As regards to their electrical transport properties all the UX compounds are metallics. The evolution of the electrical resistivity, from US to UTe, indicates a progressive lo-

Table I. - *Magnetic properties of U, Np, and Pu mononictides and monochalcogenides.*

	a (Å)	T_N (K)	T_c (K)	k	ordering	Easy axis	$m(T=0)$ μ_B	Ref.
UN	4.890	53		$\langle 001 \rangle$	1 - k type I	$\langle 001 \rangle$	0.75	1, 3
UP	5.589	122		$\langle 001 \rangle$	1 - k type I	$\langle 001 \rangle$	1.7	1, 3
		22		$\langle 001 \rangle$	2 - k type I	$\langle 110 \rangle$	1.9	1, 3
UAs	5.779	124		$\langle 001 \rangle$	1 - k type I	$\langle 001 \rangle$	1.9	1, 3
		62		$\langle 001/2 \rangle$	2 - k type IA	$\langle 110 \rangle$	2.2	1, 3
USb	6.191	213		$\langle 001 \rangle$	3 - k type I	$\langle 111 \rangle$	2.85	1, 3
NpN	4.897		87	0	ferro	$\langle 111 \rangle$	1.4	13
NpP	5.615	130		$\langle 000.36 \rangle$	Inc	$\langle 001 \rangle$		13
		74		$\langle 001/3 \rangle$	+++---	$\langle 001 \rangle$	2.2	
NpAs	5.838	173		$\langle 001/4 - \epsilon \rangle$	1 - k , Inc	$\langle 001 \rangle$		13, 15
		154		$\langle 001/4 \rangle$	4+, 4-, 1 - k	$\langle 001 \rangle$		16
		138		$\langle 001 \rangle$	3 - k , type I	$\langle 111 \rangle$	2.5	
NpSb	6.254	202		$\langle 001 \rangle$	3 - k , type I	$\langle 111 \rangle$	2.5	13, 14
PuN	4.905	13?						20, 21
PuP	5.550		126	0	ferro	$\langle 100 \rangle$	0.75	22
PuAs	5.780		125	0	ferro	$\langle 100 \rangle$	0.67	23
PuSb	6.240	85		$\langle 000.13 \rangle$	1 - k , Inc	$\langle 100 \rangle$		24
		70		0	ferro	$\langle 100 \rangle$	0.74	
PuBi	6.350	58		$\langle 000.23 \rangle$	1 - k , Comm	$\langle 100 \rangle$	0.50	27
US	5.489		170	0	ferro	$\langle 111 \rangle$	1.70	1, 3
USe	5.750		160	0	ferro	$\langle 111 \rangle$	2.0	1, 3
UTe	6.155		104	0	ferro	$\langle 111 \rangle$	2.25	1, 3
NpS	5.527	23		$\langle 1/2 1/2 1/2 \rangle$	Type II		0.9	17
NpSe	5.804	41		?	?		1.35	18, 19
NpTe	6.198	30		?	?		≈ 2	18, 19
PuS	5.536	Modified CW		behaviour,	$T_N = 4.5?$			28
PuSe	5.775	TIP						29
PuTe	6.151	TIP						30, 31

calization of the 5f electrons with a pronounced Kondo anomaly in UTe [9]. In the case of the mononictides the resistivity above T_N is nearly constant. This is mainly due to spin fluctuation scattering and, in contrast with the monochalcogenides no evidence for a Kondo-type behaviour is observed. In the ordered state the behaviour of the electrical resistivity is rather complicated, reflecting the complexity of the magnetic phase diagram of these compounds [9]. In particular it has been found through measurements under high magnetic fields [10] or uniaxial stress [11] that the magnetic contribution to the electrical resistivity of UP and UAs is highly anisotropic and this can be related to the anisotropy of their magnetic properties. In the case of USb the triple- k magnetic ordering leads to a gap opening in the Fermi surface from which results a very large maximum in $\rho(T)$ below T_N [9, 12].

Np and Pu mononictides and monochalcogenides

The neptunium nitride is a ferromagnet, NpP and NpAs order at $T_N = 130$ and 173 K respectively in incommensurate phases, still characterized by longitudinal waves with propagation vectors along the cubic axes and exhibit low temperature lock-in transition towards commensurate structures [13]. NpSb is a simple antiferromagnet with a triple- k type I structure at any temperature below $T_N = 202$ K [14]. The case of NpAs is particularly illustrative. A tetragonal distortion is associated with the ordering transition at T_N but this distortion vanishes at $T_0 = 138$ K, where a transition takes place from long period (4+, 4-) ordering toward antiferromagnetic type I ordering, with an apparent cubic symmetry [13], figure 1. Moreover the mag-

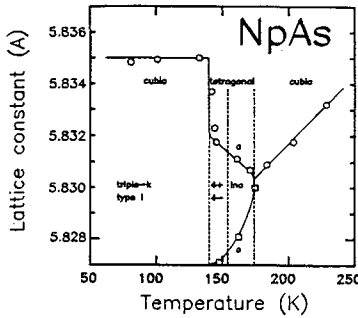


Fig. 1. - Cell parameters versus temperature in NpAs from reference [13].

netization measurements, on single crystals indicate several metamagnetic transitions toward ferrimagnetic and ferromagnetic phases [15], figure 2. These transitions are strongly dependent on temperature and magnetic field direction yielding to different phase diagrams for field applied along the [001], [110] or [111] directions. Neutron diffraction experiments on NpAs single crystal [16] have established that, in zero field, an incommensurate, sinusoidally modulated phase of wave vector $(0, 0, 1/4 - \epsilon)$ develops from $T_N = 173$ K down to a lock-in transition at $T_{IC} = 154$ K where a commensurate $(4+, 4-)$ phase ($\mathbf{k} = (0, 0, 1/4)$) takes place. The development below T_{IC} only of third order harmonics indicates a squaring of the moment modulation. At $T_0 = 138$ K another transition leads to the type I antiferromagnetic phase ($\mathbf{k} = (0, 0, 1)$). Whatever the temperature the three symmetry equivalent \mathbf{k} -vectors are observed in zero field but in cooling under a small field $H = 6$ kOe // [110] only the wave vector perpendicular to \mathbf{H} is observed in the two high temperature phases confirming the collinear nature of these phases evidenced by the tetragonal distortion of the unit cell. At T_0 the three equivalent Fourier components develop with equal amplitude establishing the triple- \mathbf{k} nature of the low temperature type I phase and

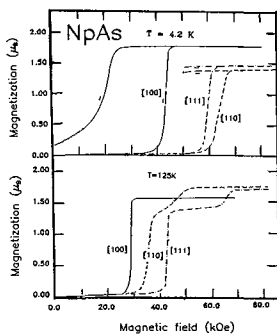


Fig. 2. - Magnetization at $T = 4.2$ and 125 K versus magnetic field along the [100], [110], and [111] directions of a single crystal of NpAs.

thus explaining the reentrance to the cubic symmetry. In larger field parallel to [110], figure 3, the incommensurate and $(4+, 4-)$ phases are relatively unstable with respect to a ferromagnetic state. Just above the critical field the magnetization aligns along a cubic axis and rotates progressively towards the field direction ($\mathbf{m} \parallel \mathbf{H}$). The antiferromagnetic triple- \mathbf{k} type I phase also transforms into this ferromagnetic phase only in a small temperature range, just below T_0 , but becomes much more stable at low temperature. Below 100 K no change occurs until a critical field of about 60 kOe where a ferrimagnetic state is induced. This state is characterized by an antiferromagnetic component perpendicular to \mathbf{H} and a ferromagnetic one, along a cubic axis at 45° from \mathbf{H} . This anisotropy of the ferromagnetic component is large, indeed the magnetization measured at 4.2 K in a field of 80 kOe along the [110] direction is only $1/\sqrt{2}$ the value of the ferromagnetic component deduced from neutron diffraction and moreover the critical fields in the [100] (40 kOe) and [110] (60 kOe) directions are in about the same ratio. To explain this magnetic properties of NpAs one must consider highly anisotropic exchange interactions from which results the quenching of the wave vector and of the Fourier components along the cubic axis. The value of $|k|$ depends essentially on the relative strength of the interactions between first (J_1) and second neighbours (J_2) and in NpAs the minimum of $\mathbf{J}(\mathbf{k})$ arises for $k = 1/4 - \epsilon$ and an incommensurate ordering develops at T_N . On cooling the saturation of the magnetic moment is responsible for the lock-in transition to the commensurate k value $1/4$. To account for the significant tetragonal distortion associated with these collinear phases large magnetoelastic terms must be considered. To drive the transition from a single- \mathbf{k} to a triple- \mathbf{k} structure higher order terms than bilinear ones must be important, the transition occurring when these fourth or higher order terms overcome the magnetoelastic energy. The subsequent turn back to cubic symmetry modifies the interplane distances, and then the corresponding exchange interactions, allowing for the change of the k value. Finally the very large anisotropy of the ferromagnetic component in the low temperature ferrimagnetic phase induced by the field is more difficult to interpret. It can have its origin




Fig. 3. - Magnetic phase diagram (H, T) of NpAs in a field along the [110] direction.

in an anisotropy of the interactions ($J(k=0)$ being minimum for $\mathbf{m}(k=0) \parallel (100)$) because it is difficult to imagine another way to compensate the loss of magnetization energy when \mathbf{H} is along [110]. The neptunium monochalcogenides are antiferromagnets. Up to now only NpS has been studied [17], it exhibits a type II ($\mathbf{k} = (1/2 \ 1/2 \ 1/2)$) antiferromagnetic ordering fundamentally different from that observed in the U monpnictides. Very recently Mössbauer experiments [18] and susceptibility measurements have shown that NpSe and NpTe order below $T_N = 41$ and 30 K respectively with a complex magnetic ordering still to be determined by neutron diffraction.

The nitride PuN exhibits a modified Curie-Weiss behaviour, with an anomaly in the susceptibility at about 13 K [19], but no magnetic ordering has been detected at low temperature [20]. PuP [21] and PuAs [22, 23] are simple, strongly anisotropic ferromagnets. PuSb [23] orders in an incommensurate phase, again characterized by wave vector $[0 \ 0 \ k]$ and $\mathbf{m}(k) \parallel \mathbf{k}$. k varies continuously from $k = 0.130$ at T_N down to $k = 0.090$ at $T_{IC} = 70$ K where a ferromagnetic ordering takes place. The high temperature incommensurate phase is rather unstable with respect to an applied field. In moderate field ($H \leq 12$ kOe) a commensurate ordering with a wave vector $k = 1/8$ is stabilized in a finite temperature range and larger fields induce a ferromagnetic state (Fig. 4). PuSb has also been investigated by critical neutron scattering [24] and inelastic neutron scattering [25]. These studies evidence the strong anisotropy of the exchange interactions, very similar to that observed in many Ce and uranium isomorphous compounds. PuBi develops at any temperature below $T_N = 58$ K a long period incommensurate ordering [26]. The results relative to Pu monochalcogenides PuS [27] and PuSe [28] are limited. The telluride PuTe has been studied by magnetization measurement [29] and polarized neutron diffraction [30]. The susceptibility is very small, nearly constant with temperature in contrast with the expected behaviour for a Pu^{3+} ion suggested by the value of the lattice parameter ($a = 6.15 \text{ \AA}$). The polarized neutron experiments confirm that only a very small magnetic moment ($5 \times 10^{-3} \mu_B/\text{Pu}$) can be field induced. Taking into account the behaviour of PuSb and PuTe, the investigation of the solid solutions $\text{PuSb}_{1-x}\text{Te}_x$ is particularly interesting. An anomaly occurs in the variation of




Fig. 4. - Magnetic phase diagram (H, T) of PuSb in a field along the [100] direction.

the lattice constant which exhibits a maximum around $x = 0.05$ [31]. Very small Te substitution (2 %) affects significantly the magnetic behaviour of PuSb. For larger tellurium concentrations the magnetic susceptibility can be interpreted by a modified Curie-Weiss law. On increasing x the effective moment and the paramagnetic Curie temperature decrease while the temperature independent susceptibility χ_0 increases almost linearly with a tendency to saturate at the value observed in PuTe (Fig. 5). Mössbauer experiments [32] also indicate the loss of the localized magnetic moment on going from PuSb to PuTe.

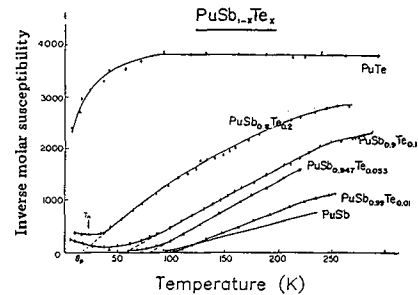


Fig. 5. - Inverse susceptibility of solid solutions $\text{PuSb}_{1-x}\text{Te}_x$ from Reference [29].

The study of the electrical properties of transuranium AnX compounds, using single crystals, is only beginning. The first measurements on a NpX compounds, namely NpTe is presented at this conference [33]. The resistivity of NpTe exhibits a logarithmic dependence at high temperature ($T \geq 50$ K), the ordering temperature is detected at $T = 30$ K and a large residual resistivity is observed at low temperature. Thus NpTe seems to behave like a heavy fermion system which develops a magnetic ordering at low temperature.

The plutonium compounds PuSe, PuTe and PuSb as well as $\text{PuSb}_{1-x}\text{Te}_x$ solid solutions have been investigated [34] (Fig. 6). The chalcogenides PuSe, and PuTe behave as semiconductors with very small gap (≤ 20 meV). PuSb is a semi-metal displaying Kondo effect. The $\text{PuSb}_{1-x}\text{Te}_x$ solid solutions evidence the development of a small hybridization gap as x increases




Fig. 6. - Resistivity versus temperature for solid solution $\text{PuSb}_{1-x}\text{Te}_x$.

(Fig. 6). The same trend is observed in the tellurides on going from UTe to PuTe through NpTe (Fig. 7).




Fig. 7. - Resistivity versus temperature of single crystal of UTe, NpTe, PuTe.

Actinides compounds with the ThCr_2Si_2 type structure

Since the discovery of heavy fermion behaviour and superconductivity in CeCu_2Si_2 [35] the tetragonal compounds with the ThCr_2Si_2 type structure especially those of cerium have been the object of many extensive studies. Ternary actinide compounds AnM_2X_2 where $\text{M} = \text{Ru}, \text{Rh}$ and $\text{X} = \text{Ge}$ or Si can be formed. Among them URu_2Si_2 is especially interesting [36-38], the low temperature specific heat coefficient $\gamma = 180 \text{ mJ/mole. K}^2$ is rather large. At $T_N = 17.5 \text{ K}$ URu_2Si_2 orders with a antiferromagnetic structure ($\mathbf{k} = (001)$) but with an extremely low moment value ($0.05 \mu_B/\text{U}$). Furthermore a superconducting transition occurs at $T = 1.1 \text{ K}$. Therefore the study of the Np isomorphous is quite interesting. The results of Mössbauer spectroscopy and neutron diffraction experiments reported at this conference [39] show that NpRu_2Si_2 orders at $T_N = 27.5 \text{ K}$ in a sinusoidally incommensurate modulated phase. The wave vector of the modulation, along the tetragonal axis, varies continuously with temperature and no lock-in transition has been detected down to 1.5 K . On cooling some squaring of the modulation develops but even at 1.5 K ($T_N/20$) the magnetic moments are not fully saturated. Preliminary magnetic and resistivity measurements have been performed, on a small single crystal ($\approx 0.8 \text{ mg}$) [40]. At high temperature the magnetic susceptibility follows a modified Curie-Weiss law. The very small weight of the crystal prevents an accurate

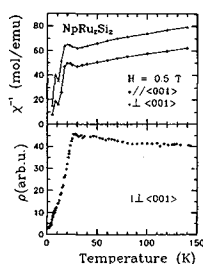


Fig. 8. - Inverse susceptibility and resistivity of a single crystal of NpRu_2Si_2 .

determination of χ_0 ($\approx 10^{-2} \text{ emu/mole}$) and of the effective moment ($\mu_{\text{eff}} \approx 4 \mu_B$). At low temperature the Neel temperature is detected at $T_N = 29 \pm 1 \text{ K}$. Below T_N an anomaly is observed at $T = 6 \text{ K}$ both in magnetization and electrical resistivity curves (Fig. 8) which has not been detected in neutron and Mössbauer measurements.

Conclusion

Presently many informations about the magnetic behaviour of U, Np and Pu monpnictides have been obtained. Except for the nitrides in which the interactinide distance is small and just below the Hill limit for occurrence of localized magnetism all the other compounds are characterized by highly anisotropic exchange interactions resulting from their electronic structure allowing large hybridization effects. Beside this common feature many different properties are observed ranging from ferromagnetic to antiferromagnetic behaviour through incommensurate and long period ordering, from collinear to planar (double-k) and multiaxial (triple-k) magnetic arrangements. This is a consequence of the details of the magnetic interactions along the direction of the propagation vector and of the competition between exchange anisotropy, single ion anisotropy (CEF) and magneto-elastic term. A theoretical study of these systems has been developed by Cooper *et al.* [41] very consistent with the present experimental results.

The monochalcogenides exhibit also rather complex properties ranging from ferromagnetism in uranium compounds to complex orderings and to weak magnetism in neptunium and plutonium compounds. Clearly more detailed studies are needed in order to understand their exciting properties.

The recent results on the ternary compound NpRu_2Si_2 indicate that the physical properties of intermetallic transuranium systems are quite interesting to be investigated in a near future.

Acknowledgements

We would like to thank H. Bartholin, M. Bogé, B. R. Cooper, M. Kuznietz, G. H. Lander, K. Mattenberger, J. P. Sanchez, J. Schoenes and W. G. Stirling for fruitful collaborations.

- [1] Fournier, J. M., Troc, R., Handbook on the physics and chemistry of actinides, Eds. A. J. Freeman and G. H. Lander (North Holland, Amsterdam) Vol. 2 (1985) 29.
- [2] Dunlap, B. D., Kalvius, G. M., Handbook on the physics and chemistry of the actinides, Eds. A. J. Freeman and G. H. Lander (North Holland Amsterdam) Vol. 2 (1985) 329.
- [3] Rossat-Mignod, J., Lander, G. H., Bulet, P.,

- Handbook on the physics and chemistry of the actinides, Eds. A. J. Freeman and G. H. Lander (North Holland Amsterdam) Vol. 1 (1984) 415.
- [4] Buyers, W. J. L., Holden, T. M., Handbook on the physics and chemistry of the actinides, Eds. A. J. Freeman and G. H. Lander (North Holland Amsterdam) Vol. 2 (1985) 239.
- [5] Spirlet, J. C., Vogt, O., Handbook on the physics and chemistry of the actinides, Eds. A. J. Freeman and G. H. Lander (North Holland Amsterdam) Vol. 2 (1985) 79.
- [6] Rossat-Mignod, J., Burlet, P., Quezel, S., Efantin, J. M., Delacote, D., Bartholin, H., Vogt, O., Ravot, D., *J. Magn. Magn. Mater.* **31-34** (1983) 398.
- [7] Cooper, B. R., Siemann, R., Yang, D., Thayamballi, P., Banerjee, A., Handbook on the physics and chemistry of the actinides, Eds. A. J. Freeman and G. H. Lander (North Holland Amsterdam) Vol. 2 (1985) 435.
- [8] Kuznietz, M., Burlet, P., Rossat-Mignod, J., Vogt, O., *J. Magn. Magn. Mater.* **69** (1987) 12.
- [9] Schoenes, J., Frick, B., Vogt, O., *Phys. Rev. B* **30** (1984) 6578.
- [10] Therond, P. G., Fournier, J. M., Schoenes, J., Vogt, O., *J. Magn. Magn. Mater.* **66** (1987) 45.
- [11] Breandon, C., Bartholin, H., Tchapotian, R., Therond, P. G., Schoenes, J., Vogt, O., *J. Magn. Magn. Mater.* **63-64** (1987) 162.
- [12] Frick, B., Schoenes, J., Vogt, O., Allen, J. A., *Solid State Commun.* **42** (1982) 331.
- [13] Aldred, A. T., Dunlap, B. D., Harvey, A. R., Lam, D. J., Lander, G. H., Mueller, M. H., *Phys. Rev. B* **9** (1974) 3766.
- [14] Sanchez, J. P., Burlet, P., Quezel, S., Bonnisseau, D., Rossat-Mignod, J., Spirlet, J. C., Rebizant, J., Vogt, O., *Solid State Commun.* **67** (1988) 999.
- [15] Rebizant, J., Spirlet, J. C., Mattenberger, K., Vogt, O., Proc. of the 14^e Journées des actinides, Ed. J. Schoenes (Davos, Switzerland) 1984.
- [16] Burlet, P., Bonnisseau, D., Quezel, S., Rossat-Mignod, J., Spirlet, J. C., Rebizant, J., Vogt, O., *J. Magn. Magn. Mater.* **63-64** (1987) 151.
- [17] Lam, D. J., Dunlap, B. D., Harvey, A. R., Muller, M. H., Aldred, A. T., Nowik, I., Lander, G. H., Proc. Inter. Conf. Magnetism (1973) Vol. 4 (Nauka, Moscow).
- [18] Sanchez, J. P., Rebizant, J., Spirlet, J. C., Vogt, O., Proc. of 17^e Journées des actinides, Lausanne (1987) Ed. P. Erdos.
Bonnisseau, D., Thèse, Grenoble (1987).
- [19] Raphael, G., de Novion, C. H., *Solid State Commun.* **7** (1969) 791.
- [20] Boeuf, A., Fournier, J. M., Manes, L., Rebizant, J., Rustichelli, F., Proc. of 11^e Journées des actinides, Venice (1982) Ed. G. Bombieri.
- [21] Lander, G. H., Lam, D. J., *Phys. Rev. B* **14** (1976) 4064.
- [22] Cooper, B. R., Thayamballi, P., Spirlet, J. C., Mueller, W., Vogt, O., *Phys. Rev. Lett.* **51** (1983) 2418.
- [23] Burlet, P., Quezel, S., Rossat-Mignod, J., Spirlet, J. C., Rebizant, J., Mueller, W., Vogt, O., *Phys. Rev. B* **30** (1984) 6660.
- [24] Burlet, P., Rossat-Mignod, J., Lander, G. H., Spirlet, J. C., Rebizant, J., Vogt, O., *Phys. Rev. B* **36** (1987) 5306.
- [25] Lander, G. H., Stirling, W. G., Rossat-Mignod, J., Spirlet, J. C., Rebizant, J., Vogt, O., *Physica* **136B** (1986) 409.
- [26] Burlet, P., Quezel, S., Rossat-Mignod, J., Spirlet, J. C., Rebizant, J., Vogt, O., *J. Magn. Magn. Mater.* **63-64** (1987) 145.
- [27] Raphael, G., de Novion, C. H., *J. Phys. France* **30** (1969) 261.
- [28] Allbutt, M., Dell, R., Junkinson, A. R., The Chemistry of extended defects in non-metallc solids (North Holland Amsterdam) p. 124.
- [29] Mattenberger, K., Vogt, O., Spirlet, J. C., Rebizant, J., *J. Common Met.* **121** (1986) 285.
- [30] Lander, G. H., Rebizant, J., Spirlet, J. C., Delapalme, A., Brown, P. J., Vogt, O., Mattenberger, K., *Physica B* **146** (1987) 341.
- [31] Rebizant, J., private communication.
- [32] Sanchez, J. P., Spirlet, J. C., Rebizant, J., Vogt, O., *J. Magn. Magn. Mater.* **63-64** (1987) 139.
- [33] Pleska, E., Fournier, J. M., Chiapusio, J., Rossat-Mignod, J., Spirlet, J. C., Rebizant, J., Vogt, O., this conference.
- [34] Therond, P. G., Blaise, A., Fournier, J. M., Rossat-Mignod, J., Spirlet, J. C., Rebizant, J., Vogt, O., *J. Magn. Magn. Mater.* **63-64** (1987) 142.
- [35] Steglich, F., Aarts, J., Bredl, C. D., Lieke, W., Meschede, D., Franz, W., Schaffer, H., *Phys. Rev. Lett.* **43** (1979) 1892.
- [36] Palstra, M., Menovski, A. A., Van den Berg, J., Prikmaat, A. J., Kees, P. H., Nieuwenhuyse, G. H., Mydosh, J. A., *Phys. Rev. Lett.* **55** (1985) 2727.
- [37] Schlabit, W., Baumann, J., Rauswhwalbe, U., Ahleim, U., Bredl, C. D., *Z. Phys. B* **62** (1986).
- [38] Broholm, C., Kjems, J. K., Buyer, W. J. L., Matthews, P., Palstra, T. T. M., Menovski, A. A., Mydosh, J. A., *Phys. Rev. Lett.* **58** (1987) 1467.
- [39] Bonnisseau, D., Burlet, P., Boge, M., Quezel, S., Rossat-Mignod, J., Spirlet, J. C., Rebizant, J., this conference.
- [40] Wulff, M., Pleska, E., private communication.
- [41] Cooper, B. R., Hu, G. J., Kiousis, N., Wills, J. M., *J. Magn. Magn. Mater.* **63, 64** (1987) 121.